

Retrospective clinical evaluation of posterior monolithic zirconia restorations after 1 to 3.5 years of clinical service

郡家, 浩人

<https://doi.org/10.15017/1931835>

出版情報：九州大学, 2017, 博士（歯学）, 課程博士
バージョン：
権利関係：



Original

Retrospective clinical evaluation of posterior monolithic zirconia restorations after 1 to 3.5 years of clinical service

Hiroto Gunge¹⁾, Yoichiro Ogino¹⁾, Masafumi Kihara¹⁾,
Yoshihiro Tsukiyama²⁾, and Kiyoshi Koyano¹⁾

¹⁾Section of Implant and Rehabilitative Dentistry, Division of Oral Rehabilitation,
Faculty of Dental Science, Kyushu University, Fukuoka, Japan

²⁾Section of Dental Education, Division of Oral Biological Sciences,
Faculty of Dental Science, Kyushu University, Fukuoka, Japan

(Received May 1, 2017; Accepted June 21, 2017)

Abstract: This retrospective study analyzed clinical outcomes of monolithic zirconia restorations (MZR) and factors related to restoration success. Patient records were searched to identify those provided MZR (Cercon ht) for premolars or molars between April 2012 and March 2016. All MZR were placed according to a standardized protocol. Kaplan-Meier analysis was used to assess MZR performance and failure after recall appointments at 1 year or later. In total, 101 patients received 148 MZR. Mean duration of follow-up was 25.0 ± 9.9 months. Six MZR required replacement: three because of pulpal complications, one because of root fracture of an abutment tooth, one because of restoration fracture, and one because the tooth was used as an abutment tooth for a fixed partial denture after root fracture of an adjacent tooth. The cumulative MZR survival (success) rate at 3.5 years was 91.5% (95% confidence interval, 82.1% to 100%). The findings of this short-term retrospective study indicate that posterior MZR are a therapeutic option for certain patients. In addition, several clinical procedures contribute to MZR success, including preparation design and

occlusal and adhesive surface treatments.

Keywords: monolithic zirconia restoration; preparation design; surface treatment.

Introduction

Ceramic restorations, especially traditional metal-ceramic restorations, have been widely used for many years (1-3). Patient demands for superior aesthetic and metal-free tooth-colored restorations have spurred development of ceramic restorations, which benefit from technologies such as computer-assisted design/computer-assisted manufacturing (CAD/CAM). The outcomes for these restorations have been good (1-5). Previous studies of the mechanical and optical properties of current ceramic materials (6-8) indicate that no ceramic system is ideal for all clinical situations. However, development and improvement of ceramic materials is ongoing and exhaustive. Because of its superior mechanical properties, zirconium dioxide (ZrO_2 , known as zirconia) was introduced to dentistry and has attracted considerable attention as a framework material (3,9). Previous studies reported that zirconia restorations elicit favorable soft tissue responses (9). Although zirconia frameworks that are veneered with translucent feldspathic or glass ceramic materials for aesthetic reasons have been successful, their most common shortcoming is cohesive failure of the veneering porcelain, especially chipping (1,3,10). Strategies to prevent this limitation, including improvements in framework design and sintering, have been evaluated (11-13), but previous studies reported higher rates of

Correspondence to Dr. Yoichiro Ogino, Section of Implant and Rehabilitative Dentistry, Division of Oral Rehabilitation, Faculty of Dental Science, Kyushu University, 3-1-1 Maidashi, Higashi-ku, Fukuoka 812-8582, Japan
Fax: +81-92-642-6380 E-mail: ogino@dent.kyushu-u.ac.jp

Color figures can be viewed in the online issue at J-STAGE.
doi.org/10.2334/josnusd.17-0176
DN/JST.JSTAGE/josnusd/17-0176

veneer chipping in zirconia-based restorations than in metal-ceramic restorations, as the reasons for chipping are multifactorial (9,14,15).

Monolithic zirconia restorations (MZR) without veneering were recently introduced to avoid chipping (16). The single-layer design and favorable mechanical properties of such restorations require less tooth preparation, which improves pulpal response in vital teeth. However, several concerns remain regarding preparation design, wear resistance and antagonist wear, bonding effectiveness, and the inherent opaque color of the material. Recent *in vitro* studies of the basic properties and clinical performance of zirconia restorations yielded promising findings (17-28). Although several clinical reports have highlighted the effectiveness of MZR, including single restorations and fixed partial dentures for teeth and implants (29-31), few studies have investigated the outcomes of MZR. This study retrospectively assessed MZR outcomes and describes MZR treatment modalities in light of the present findings.

Materials and Methods

This study was conducted at a private dental practice in Fukuoka, Japan, after receiving ethics approval for the study protocol from Kyushu University (#28-240). The inclusion criteria for the present study were age older than 20 years, MZR of a molar(s) or premolar(s) between April 2012 and March 2016, and at least one post-MZR follow-up visit by September 2016. Exclusion criteria included presence of probable bruxism and severe periodontal disease. Before prosthetic treatment, all patients received full-mouth periodontal examination and therapy, endodontic treatment, and caries treatment. Some patients underwent occlusal adjustment. For natural teeth, the preparation design was based on zirconia restorations suggested by the manufacturer, i.e., a chamfer margin with an occlusal reduction of 0.5 mm and an axial reduction of at least 0.5 mm. After conventional silicone impressions and preparation of stone models, wax patterns of the restorations were scanned by CAD (3 Shape Dental System, Dentsply Sirona K.K., Tokyo, Japan), and MZR (Cercon ht, Dentsply Sirona K.K.) were machined from zirconia blanks with a CAM (Cercon brain, Dentsply Sirona K.K.) milling procedure. After the milling procedure, the restorations were sintered at 1,500°C for 8.5 h in a high-temperature sinter furnace until reaching 1,540°C for 12 h. The sintered restorations were glazed at 875°C for 15 min.

When the restorations were ready for delivery, the provisional restorations were removed for the intraoral try-ins, and fit and occlusion were checked and adjusted

if necessary. Final extraoral polishing procedures were performed with solid polish (Zircon Bite, Dental Ventures of America Inc., Corona, CA, USA). MZR for natural teeth were treated with 10-methacryloyloxydecyl dihydrogen phosphate (MDP) primers (Clearfil Ceramic Primer, Kuraray Noritake Dental Inc., Tokyo, Japan) after low-pressure alumina-blasting (0.6 MPa, sandblaster: Jet Blaster II, BSA Nagoya, Japan, alumina: Hi Aluminas, Shofu, Kyoto, Japan) and were luted with a self-etch, dual-cure, composite cement system (Clearfil Esthetic Cement, Kuraray Noritake Dental Inc., Tokyo, Japan).

Clinical follow-up assessment and data collection were done by the same clinician (H.G.). Demographics (age, sex), prosthetic treatment records, and outcomes of the patients with MZR were ascertained during chart review. Clinical data included time in function and complications. MZR longevity was evaluated from the date the MZR was finally restored to the date of a complication or, if no complications occurred, the date of a follow-up examination at 1 year or later. A successful MZR was defined as one without complications. An MZR that was in situ and used at the follow-up visit, regardless of re-cementation or minor fracture, was defined as a surviving MZR. Data on successful and surviving MZR were analyzed with the Kaplan-Meier method.

Results

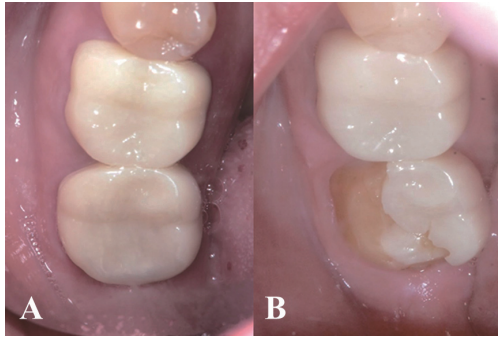
A total of 101 patients (30 men, 71 women; mean age 45.1 ± 10.1 years; 148 MZR) satisfied the inclusion criteria. Mean duration of follow-up was 25.0 ± 9.9 months. The distribution of zirconia restorations is presented in Table 1. No restorations were recemented or remained broken or damaged. Thus, no restorations were classified as surviving restorations, and only success rate was calculated. Overall, six MZR for natural teeth were lost: one because of hyperesthesia, one because of root fracture of an abutment tooth, one because of restoration fracture (Fig. 1A, B), and two because of pulpitis. In addition, one restoration was removed because the tooth was used as an abutment tooth for a fixed partial denture after root fracture of an adjacent tooth. No restorations were lost for implants. The detailed characteristics of the MZR are shown in Table 2. Kaplan-Meier curves are shown in Fig. 2. The cumulative survival, or success, rate was 91.5% (95% confidence interval, 82.1% to 100%) at 3.5 years.

Discussion

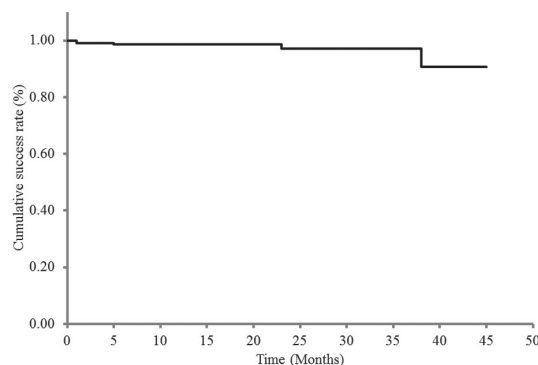
Previous reviews (3) reported estimated survival rates for ceramic restorations of 93.3% and about 95% at 5 years. The authors concluded that the survival rates for

Table 1 Distribution of monolithic zirconia restorations in dentition

| | | | | | | | | |
|-----------------|----|----|----|----|----|----|----|----|
| Number of teeth | 4 | 12 | 6 | 5 | 6 | 9 | 20 | 9 |
| Tooth number | 17 | 16 | 15 | 14 | 24 | 25 | 26 | 27 |
| | 47 | 46 | 45 | 44 | 34 | 35 | 36 | 37 |
| Number of teeth | 9 | 17 | 9 | 6 | 6 | 6 | 16 | 8 |

**Fig. 1** Fractured monolithic zirconia restoration (MZR). A, MZR at delivery. B, Fractured MZR, 38 months after delivery.**Table 2** Complications by type, timing, and location

| Complication | Number of cases | Period (months) | Tooth number |
|--|-----------------|-----------------|--------------|
| Severe hyperesthesia | 1 | 1 | 14 |
| Root fracture | 1 | 5 | 36 |
| Restoration fracture | 1 | 38 | 37 |
| Pulpitis | 2 | 1 and 1 | 35 and 36 |
| Abutment tooth for fixed partial denture | 1 | 23 | 35 |

**Fig. 2** Kaplan-Meier curve showing the cumulative survival rate. The cumulative survival, or success, rate was 91.5% (95% confidence interval, 82.1% to 100%) at 3.5 years.

most types of ceramic restorations were similar to those reported for metal-ceramic restorations, both in both the anterior and posterior regions. However, they suggested that zirconia-based restorations should not be considered as a primary option because of the high incidence of technical problems. Introduction of MZR has been regarded as a clinical option to address these problems, and data

from many studies indicate that MZR are successful. However, information on the clinical performance of MZR is insufficient. We evaluated outcomes of MZR for posterior teeth in this study, although we recognize that the analysis is limited by the retrospective design and short duration of follow-up.

Although the duration of observation was short, the success rate, i.e., cumulative survival, was 91.5% at 3.5 years. While present and past findings cannot be directly compared, the success rate of MZR in premolars and molars was similar to those reported previously (32,33). Before clinical evaluation of MZR and data analysis, restoration-associated complications must be described (34). These complications have been classified as biological and technical (1,3). Loss of abutment tooth vitality, abutment tooth fracture, and secondary caries were the most frequently reported biological complications. Framework fracture, ceramic fracture, ceramic chipping, marginal discoloration, loss of retention, and poor aesthetics were the technical problems reported. A previous study reported that the three most common complications were need for endodontic treatment, porcelain veneer fracture, and loss of retention (34). The present study showed that four MZR developed biological complications; the technical complication of restoration fracture was observed in only one MZR. Loss of retention was not observed in this study. Our treatment process and these results might be helpful in understanding several key factors regarding MZR success.

Preparation design for natural teeth

Previous studies showed that preparation design was significantly associated with MZR fracture strength (19,22,23,25,26). According to manufacturers' instructions, MZR can be applied at a minimum thickness of 0.5 mm. However, most previous studies evaluated the strength of MZR with a thickness greater than 0.5 mm (19,22,25). Previous findings suggest that MZR with a thickness greater than 1.0 mm had high fracture resistance (19). In our clinical experience it is sometimes difficult to provide anatomical tooth morphology when MZR thickness is less than 1.0 mm. Stober et al. used preparations that were 0.5-0.7 mm circular and 1.0-1.2 mm occlusal (31). In the present study most teeth had an MZR thickness greater than 1.0 mm, and only one MZR fractured, after 38 months of function. However, previous studies reported that zirconia was less translucent than glass ceramic and that thicker MZR impaired translucency and polymerization of resin cements, which resulted in poor aesthetic outcomes, decreased bonding, microleakage, and postoperative sensitivity (17,35,36).

A previous study showed that light irradiance and total irradiant energy varied by brand and thickness and that the minimum amount of light irradiance for the polymerization of resin cements can be used at thicknesses less than 1.65 mm (24). One MZR was lost because of hyperesthesia, and two were lost because of pulpitis, despite the absence of complications during provisional restorations. We suspect that poor curing of resin cement caused these failures, although the present resin cement is also a dual-cure composite cement system. An advantage of MZRs—the decreased need for tooth preparation—might not be applicable in these cases. These failures should be classified as combined biological/technical complications. Although more-detailed clinical guidelines and further studies of MZR preparation are needed, past and present evidence indicates that preparations should be designed with a thickness of 1.0-1.5 mm.

Occlusal surface manipulation

Chairside adjustment of MZRs is generally required for optimal occlusal contact. Previous studies suggest that well-polished surfaces are critical for minimizing wear (17,20,27). A previous clinical study of wear behavior reported that MZR use might be justified because MZRs exhibit less wear than other dental ceramics, although, as compared with natural teeth, monolithic zirconia results in significantly greater wear of natural antagonists (31). In the present study, all MZRs were polished after occlusal adjustments, as recommended in previous studies, and no patients reported occlusal discomfort or tooth wear. Thus, our treatment process appears to be clinically satisfactory.

MZR bonding essentials

Loss of retention is significantly greater for zirconia-based restorations than for other ceramic restorations (3). The methods necessary for creating strong adhesion to a zirconia surface are a matter of controversy. However, some previous studies reported that MZR retention depends on mechanical roughening of the inner surface and chemical treatments with adhesive monomer in primers for zirconia (21,28). Primers or adhesives containing MDP after low-pressure sandblasting are an excellent option for bonding to zirconia (37-39). These previous studies indicate that the combination of low-pressure Al₂O₃-sandblasting avoids surface damage and zirconia-specific transformation and that MDP-containing primers optimize adhesive performance. Although other alternative bonding methods have been introduced, such as tribochemical silica coating followed by silanization (21,28), our results show that the present

bonding procedure was clinically satisfactory, because no MZR came off or required recementing. However, previous studies focused on the correlation between bond strength and low-temperature degradation, which might be associated with long-term bonding (21,28). This association should be investigated in future clinical studies.

In conclusion, although our findings require confirmation in longer-term studies, MZRs seem to be a suitable treatment option in posterior regions.

Conflict of interest

None declared.

References

1. Pjetursson BE, Sailer I, Zwahlen M, Hammerle CH (2007) A systematic review of the survival and complication rates of all-ceramic and metal-ceramic reconstructions after an observation period of at least 3 years. Part I: single crowns. *Clin Oral Implants Res* 18, Suppl 3, 73-85.
2. Takeichi T, Katsoulis J, Blatz MB (2013) Clinical outcome of single porcelain-fused-to-zirconium dioxide crowns: a systematic review. *J Prosthet Dent* 110, 455-461.
3. Sailer I, Makarov NA, Thoma DS, Zwahlen M, Pjetursson BE (2015) All-ceramic or metal-ceramic tooth-supported fixed dental prostheses (FDPs)? A systematic review of the survival and complication rates. Part I: single crowns (SCs). *Dent Mater* 31, 603-623.
4. Segal BS (2001) Retrospective assessment of 546 all-ceramic anterior and posterior crowns in a general practice. *J Prosthet Dent* 85, 544-550.
5. Fasbinder DJ, Dennison JB, Heys D, Neiva G (2010) A clinical evaluation of chairside lithium disilicate CAD/CAM crowns: a two-year report. *J Am Dent Assoc* 141, 10S-14S.
6. Borba M, de Araújo MD, de Lima E, Yoshimura HN, Cesar PF, Griggs JA et al. (2011) Flexural strength and failure modes of layered ceramic structures. *Dent Mater* 27, 1259-1266.
7. Borba M, Cesar PF, Griggs JA, Della Bona A (2013) Step-stress analysis for predicting dental ceramic reliability. *Dent Mater* 29, 913-918.
8. Fabian Fonzar R, Carrabba M, Sedda M, Ferrari M, Goracci C, Vichi A (2017) Flexural resistance of heat-pressed and CAD-CAM lithium disilicate with different translucencies. *Dent Mater* 33, 63-70.
9. Zarone F, Russo S, Sorrentino R (2011) From porcelain-fused-to-metal to zirconia: clinical and experimental considerations. *Dent Mater* 27, 83-96.
10. Rinke S, Gersdorff N, Lange K, Roediger M (2013) Prospective evaluation of zirconia posterior fixed partial dentures: 7-year clinical results. *Int J Prosthodont* 26, 164-171.
11. Rosentritt M, Steiger D, Behr M, Handel G, Kolbeck C (2009) Influence of substructure design and spacer settings on the in vitro performance of molar zirconia crowns. *J Dent* 37, 978-983.
12. Tan JP, Sederstrom D, Polansky JR, McLaren EA, White SN

- (2012) The use of slow heating and slow cooling regimens to strengthen porcelain fused to zirconia. *J Prosthet Dent* 107, 163-169.
13. Raigrodski AJ, Hillstead MB, Meng GK, Chung KH (2012) Survival and complications of zirconia-based fixed dental prostheses: a systematic review. *J Prosthet Dent* 107, 170-177.
 14. Heintze SD, Rousson V (2010) Survival of zirconia- and metal-supported fixed dental prostheses: a systematic review. *Int J Prosthodont* 23, 493-502.
 15. Augstin-Panadero R, Fons-Font A, Roman-Rodriguez JL, Granell-Ruiz M, del Rio-Highsmith J, Sola-Ruiz MF (2012) Zirconia versus metal: a preliminary comparative analysis of ceramic veneer behavior. *Int J Prosthodont* 25, 294-300.
 16. Guess PC, Schultheis S, Bonfante EA, Coelho PG, Ferencz JL, Silva NR (2011) All-ceramic systems: laboratory and clinical performance. *Dent Clin North Am* 55, 333-352.
 17. Kim MJ, Oh SH, Kim JH, Ju SW, Seo DG, Jun SH et al. (2012) Wear evaluation of the human enamel opposing different Y-TZP dental ceramics and other porcelains. *J Dent* 40, 979-988.
 18. Nejatidanesh F, Savabi O, Shahtoosi M (2013) Retention of implant-supported zirconium oxide ceramic restorations using different luting agents. *Clin Oral Implants Res* 24, Suppl A100, 20-24.
 19. Sun T, Zhou S, Lai R, Liu R, Ma S, Zhou Z et al (2014) Load-bearing capacity and the recommended thickness of dental monolithic zirconia single crowns. *J Mech Behav Biomed Mater* 35, 93-101.
 20. Amer R, Kürklü D, Kateeb E, Seghi RR (2014) Three-body wear potential of dental yttrium-stabilized zirconia ceramic after grinding, polishing, and glazing treatments. *J Prosthet Dent* 112, 1151-1155.
 21. Inokoshi M, Poitevin A, De Munck J, Minakuchi S, Van Meerbeek B (2014) Bonding effectiveness to different chemically pre-treated dental zirconia. *Clin Oral Investig* 18, 1803-1812.
 22. Nakamura K, Harada A, Inagaki R, Kanno T, Niwano Y, Milleding P et al. (2015) Fracture resistance of monolithic zirconia molar crowns with reduced thickness. *Acta Odontol Scand* 73, 602-608.
 23. Nordahl N, Vult von Steyern P, Larsson C (2015) Fracture strength of ceramic monolithic crown systems of different thickness. *J Oral Sci* 57, 255-261.
 24. Sulaiman TA, Abdulmajeed AA, Donovan TE, Ritter AV, Vallittu PK, Närhi TO et al. (2015) Optical properties and light irradiance of monolithic zirconia at variable thicknesses. *Dent Mater* 31, 1180-1187.
 25. Mitov G, Anastassova-Yoshida Y, Nothdurft FP, von See C, Pospiech P (2016) Influence of the preparation design and artificial aging on the fracture resistance of monolithic zirconia crowns. *J Adv Prosthodont* 8, 30-36.
 26. Sorrentino R, Triulzio C, Tricarico MG, Bonadeo G, Gherlone EF, Ferrari M (2016) In vitro analysis of the fracture resistance of CAD-CAM monolithic zirconia molar crowns with different occlusal thickness. *J Mech Behav Biomed Mater* 61, 328-333.
 27. Kim HK, Kim SH, Lee JB, Ha SR (2016) Effects of surface treatments on the translucency, opalescence, and surface texture of dental monolithic zirconia ceramics. *J Prosthet Dent* 115, 773-779.
 28. Xie H, Li Q, Zhang F, Lu Y, Tay FR, Qian M et al. (2016) Comparison of resin bonding improvements to zirconia between one-bottle universal adhesives and tribochemical silica coating, which is better? *Dent Mater* 32, 403-411.
 29. Limmer B, Sanders AE, Reside G, Cooper LF (2014) Complications and patient-centered outcomes with an implant-supported monolithic zirconia fixed dental prosthesis: 1 year results. *J Prosthodont* 23, 267-275.
 30. Mundhe K, Jain V, Pruthi G, Shah N (2015) Clinical study to evaluate the wear of natural enamel antagonist to zirconia and metal ceramic crowns. *J Prosthet Dent* 114, 358-363.
 31. Stober T, Bermejo JL, Schwindling FS, Schmitter M (2016) Clinical assessment of enamel wear caused by monolithic zirconia crowns. *J Oral Rehabil* 43, 621-629.
 32. Cehreli MC, Kökat AM, Akça K (2009) CAD/CAM Zirconia vs. slip-cast glass-infiltrated Alumina/Zirconia all-ceramic crowns: 2-year results of a randomized controlled clinical trial. *J Appl Oral Sci* 17, 49-55.
 33. Ortorp A, Kihl ML, Carlsson GE (2009) A 3-year retrospective and clinical follow-up study of zirconia single crowns performed in a private practice. *J Dent* 37, 731-736.
 34. Goodacre CJ, Bernal G, Rungcharassaeng K, Kan JY (2003) Clinical complications in fixed prosthodontics. *J Prosthet Dent* 90, 31-41.
 35. Price RB, Rueggeberg FA, Labrie D, Felix CM (2010) Irradiance uniformity and distribution from dental light curing units. *J Esthet Restor Dent* 22, 86-101.
 36. Ilie N, Stawarczyk B (2015) Quantification of the amount of blue light passing through monolithic zirconia with respect to thickness and polymerization conditions. *J Prosthet Dent* 113, 114-121.
 37. Chen L, Suh BI, Brown D, Chen X (2012) Bonding of primed zirconia ceramics: evidence of chemical bonding and improved bond strengths. *Am J Dent* 25, 103-108.
 38. Amaral M, Belli R, Cesar PF, Valandro LF, Petschelt A, Lohbauer U (2014) The potential of novel primers and universal adhesives to bond to zirconia. *J Dent* 42, 90-98.
 39. Inokoshi M, De Munck J, Minakuchi S, Van Meerbeek B (2014) Meta-analysis of bonding effectiveness to zirconia ceramics. *J Dent Res* 93, 329-334.