

3D Visualization and Topographical Analysis in Turning of Hybrid MMC By CNC Lathe SPRINT 16TC Made of BATLIBOI

Ashish Kumar Srivastava

G L Bajaj Institute of Technology and Management, Greater Noida

Shashi Prakash Dwivedi

G L Bajaj Institute of Technology and Management, Greater Noida

Nagendra Kumar Maurya

G L Bajaj Institute of Technology and Management, Greater Noida

Maurya, Manish

Accurate Institute of Management and Technology, Greater Noida

<https://doi.org/10.5109/4055217>

出版情報 : Evergreen. 7 (2), pp.202-208, 2020-06. 九州大学グリーンテクノロジー研究教育センター
バージョン :

権利関係 : Creative Commons Attribution-NonCommercial 4.0 International



3D Visualization and Topographical Analysis in Turning of Hybrid MMC By CNC Lathe SPRINT 16TC Made of BATLIBOI

Ashish Kumar Srivastava¹, Shashi Prakash Dwivedi¹, Nagendra Kumar Maurya¹, Manish Maurya^{2*}

¹G L Bajaj Institute of Technology and Management, Greater Noida, India

²Accurate Institute of Management and Technology, Greater Noida, India

*Author to whom correspondence should be addressed:

E-mail: manishmaurya33@gmail.com

(Received December 21, 2019; Revised May 23, 2020; accepted May 29, 2020).

Abstract: The performance evaluations of any manufacturing materials are significantly affected by their quality of surface as well as mechanical and metallurgical properties. MMCs are preferable material for the automobile and aircraft industries due to its excellent properties such as lightweight, high strength to weight ratio and high wear resistance. However, the presence of hard reinforcement particles in the matrix alloy makes it difficult to machine, which leads to the microstructural variation and extent of the subsurface damage. In the present study, three different rotational speed (varies from 200 rpm to 600 rpm) is used to turn the surface of previously in-house made hybrid MMC A359/2%B₄C/2%Al₂O₃ on CNC lathe SPRINT 16TC made by BATLIBOI. An attempt is made to examine the 3D surface visualization and generate the surface roughness report by Micro-Prof FRT optical profilometer, surface topographical by Olympus Lext OLS 3100 laser confocal microscope for surface characterization. The results reveal the smooth machined surface with surface roughness ranges between 1.5 µm to 2.9 µm. The topographical images revealed a flat surface full of repetitive cutting marks parallel to each other and along the direction of cutting. There are no significant topographical differences are varying rotational speed.

Keywords: Aluminum alloy A359; Metal matrix composite; 3D Surface visualization; Surface topography; CNC turning

1. Introduction

In Today's world, metal matrix composites (MMCs) are one of a suitable choice of material for most of the engineering application¹⁻⁴. The tremendous properties like lightweight, anti-corrosion and improved mechanical and thermal properties increase its demand in the manufacturing industries⁵⁻⁸. However, the behaviour under machinability is also an important way of characterization of MMCs. These are hard to cut materials possess high hardness⁹⁻¹¹. Due to high hardness and the presence of hard ceramic particle which is abrasive proves poor results in the machining of MMCs generating high tool wear¹²⁻¹³. Hence the study still searches for better machining method for such materials. The common types of machining operations such as cutting, milling, drilling and turning can be applied on MMCs¹⁴⁻¹⁵. In turning operation, conventional turning is widely used for most of the MMCs. The conventional turning of MMCs includes the turning via simple lathe or CNC lathe¹⁶. The cutting

operation includes the physical contact of the tool with the rotating workpiece, and the removal of material is done in the form of continuous or discontinuous chips¹⁷⁻¹⁸. The mechanism of cutting is shown in Figure 1. There are several challenges involves in turning of MMCs like accuracy in dimensions, improved machining results like better surface finishing and high metal removal rate (MRR), improved surface characterization properties, high tool life as well as low-cost¹⁹⁻²⁰. Most of the tool materials like high-speed steels and ceramics cannot be effectively applied for the machining of such hard MMCs because of the rapid wear due to the presence of hard reinforcement particles²¹. However, coated carbides tools can withstand the tool to wear for a short time of machining²²⁻²³. Most of the authors have reported that polycrystalline diamond (PCD) tools can be applied for the MMCs because of the capability of valuable tool life²⁴. It is to be noted that PCD is harder than SiC, B₄C or Al₂O₃ and it possesses a non-chemically reactive tendency with work material but the main disadvantage of PCD tool is its high cost due to

the diamond particle bonded ²⁵⁾.

In the machining operation, the quality of the machined surface plays an important role in deciding the suitable machining process for a particular material. In the present study, three different rotational speed (varies from 200 rpm to 600 rpm) is used to turn the surface of previously in-house made hybrid MMC A359/2%B₄C/2%Al₂O₃ on CNC lathe SPRINT 16TC made by BATLIBOI. An attempt is made to examine the 3D surface visualization and generate the surface roughness report by Micro-Prof FRT optical profilometer, surface topographical by Olympus Lext OLS 3100 laser confocal microscope for surface characterization.

2. Experimental Details

The material selected for the study purpose is previously in-house developed hybrid metal matrix composite A359/2%B₄C/2%Al₂O₃ produced by electromagnetic stir casting process. After testing the mechanical properties of the samples are given in Table 1.

Table 1. Basic mechanical properties of the tested hybrid MMCs.

Sample	Strength (MPa)	Hardness (HRC)	Toughness (J/m ²)
A359/2%B ₄ C/2%Al ₂ O ₃	112.6	52.5	10.6

The experimental work is performed on CNC lathe SPRINT 16TC made by BATLIBOI (Figure 2). Rotational speed was selected as a variable parameter in the range of 200 rpm to 600 rpm. The reason behind the selection of this range is obtained from the pilot runs. The rotational speed out of the range (lower than 200 rpm and higher than 600 rpm) was significantly affected the surface topography of the machined surface and it increases the surface defects like tool marks, chattering etc. So that in the present work, the rotational speed of the workpiece was kept 200 rpm, 400 rpm and 600 rpm for turning processes. The effect of rotational speed on surface characterization is also observed. The other process parameters of the machining process are fixed. Table 2 shows the technological conditions of turning in CNC lathe. The experiments are conducted at a given set of rotational speed, and three separate surfaces are created for each type of experimental run. The diameter of the workpiece samples was taken 20 mm.

The elements of surface integrity such as roughness parameters (Ra, Rq, Rz), 3D surface visualization, surface topography, are discussed to understand the behaviour of the machined surface.

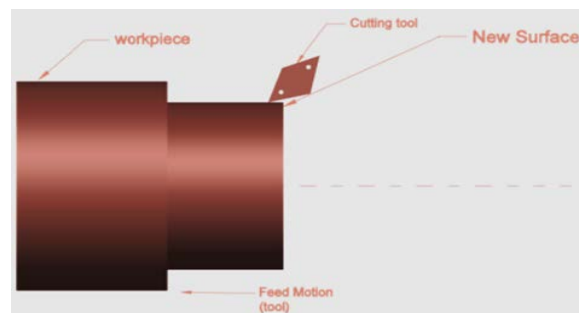


Figure 1. Cutting mechanisms in turning on CNC lathe

3. Result and Discussion

The turning process at three different speeds was successfully performed on the hybrid MMC workpiece. Figure 3 shows the surface created by turning processes. In visual observation, the surface texture of CNC lathe samples is shiny and free from defects like porosity and voids. Tool marks in the form of cutting lines, but no specific pattern is observed. These cutting lines are found significantly low when increasing the rotational speed.

Table 2. Technological conditions of turning operation

Parameters	Values
Number of rotation (rpm)	200, 400, 600
Workpiece diameter (mm)	20
Depth of cut (mm)	0.2
Feed rate (mm/rev)	0.050
Coolant type	SAE20W40
Tool insert	Coated Carbide
Tool type	TNMG (Kyocera)

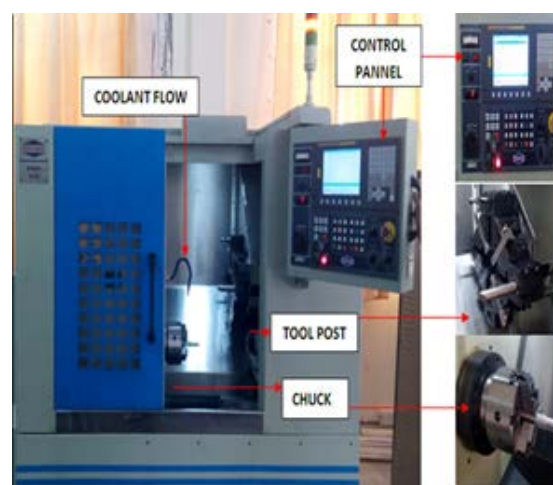


Figure 2. Sprint 16 TC CNC lathe machine

The surface roughness report was generated for each turned surface using an optical profilometer. ISO 4287 standard has been applied to measure the roughness parameters along ten parallel lines on the circumferential surface of the cylindrical workpiece. The specifications of optical profilometer are as follows: Noise filter cut-off A similar pattern has been observed for other roughness parameters (R_q and R_z). The lowest range ($1.5\mu\text{m}$ to $2.9\mu\text{m}$) of average surface finish (R_a) has been observed in the turning process. Improved surface finishing at higher rotational speed is attributed to the reduction in built-up edge (BUE) formation of cutting insert.

Micro proof FRT optical profilometer is also used to capture the surfaces produced by the turning process. Figure 4 shows the 2D and 3D visualization of the machined surface created by CNC lathe at a given set of rotational speeds.

At a glance, it is challenging to differentiate all three surfaces which are similar in appearance. However, some of the observations are found on which they differ to each other. Images show the perfectly rolled surface and free from defects like porosity, voids or cracks. The surface texture shows the repetitive tool marks in the direction of feed and along the cutting direction. At the lower rotational speed (Figure 4 (a)), the tool marks are observed approximately parallel to each other. However, the small scale of the micro-pores appears on the surface. It is attributed to the effect of high thermal energy and mechanical stresses per unit time per unit area of the circumferential length due to which the formation of the larger built-up edge of tool insert is found during turning. At this stage, the tendency of dislodgment of reinforcement particles from the machined surface is increased and creates small-scale voids and porosity. At the medium range of rotational speed (400 rpm) shown in Figure 4 (b).

It is observed the undulation on the surface, and tools

$8\mu\text{m}$, evaluation length 7.5 mm , sampling length 2.5 mm , cut-off wavelength $2.5\mu\text{m}$ and the number of cut-offs 3. Three parameters of roughness R_a , R_q , and R_z are measured, and their values are given in Table 3. It is observed from the values that a better surface finishing can be found at an increasing trend of rotational speed. marks are slightly inclined. However, due to high contact stresses and heat, the surface porosity decreases. At higher rotational speed the formation of the built-up edge is reduced which makes the smooth surface as shown in Figure 4 (c).

Surface topography of all the machined surfaces is studied by images captured by OLYMPUS Lext OLS 3100 laser confocal microscope. Figure 5 shows the 2D and 3D surface topographical images of CNC lathe machined surfaces. The images revealed a flat surface full of repetitive cutting marks parallel to each other and along the direction of cutting. There are no significant topographical differences are varying rotational speed. At each set of rotational speed, approximately similar surface with few peaks and valleys are observed.

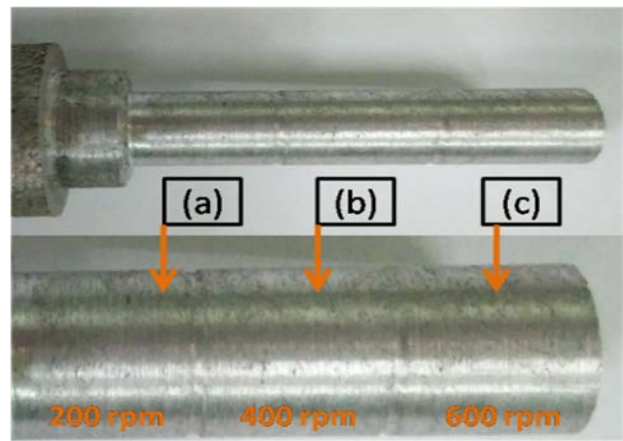


Figure 3. Machined samples of CNC lathe

Table 3. Surface Roughness report

	Rotational speed →	200 rpm			400 rpm			600 rpm		
	Reading numbers ↓	R_a	R_q	R_z	R_a	R_q	R_z	R_a	R_q	R_z
CNC Lathe	1	2.463	2.958	14.671	1.870	2.342	13.638	1.602	1.991	11.428
	2	2.240	2.894	17.184	1.873	2.301	12.925	1.645	2.090	13.641
	3	2.432	3.242	19.357	1.524	1.948	12.368	1.577	1.973	13.282
	4	2.619	3.394	22.213	1.856	2.232	12.474	1.510	1.887	12.491
	5	2.658	3.332	17.406	1.906	2.276	11.527	1.530	1.922	12.034
	6	3.011	3.632	17.807	2.023	2.604	15.206	1.723	2.118	10.670
	7	2.755	3.458	18.334	2.262	2.822	17.049	1.633	2.034	12.162
	8	2.693	3.481	20.387	2.267	2.806	14.652	1.637	2.012	10.818
	9	2.964	3.699	22.391	2.122	2.660	13.904	1.538	1.919	11.132
	10	2.869	4.614	30.524	2.277	2.985	16.183	1.644	2.077	15.296
	Avg	2.6704	3.4704	20.0274	1.998	2.4976	13.9926	1.603	2.0023	12.2954



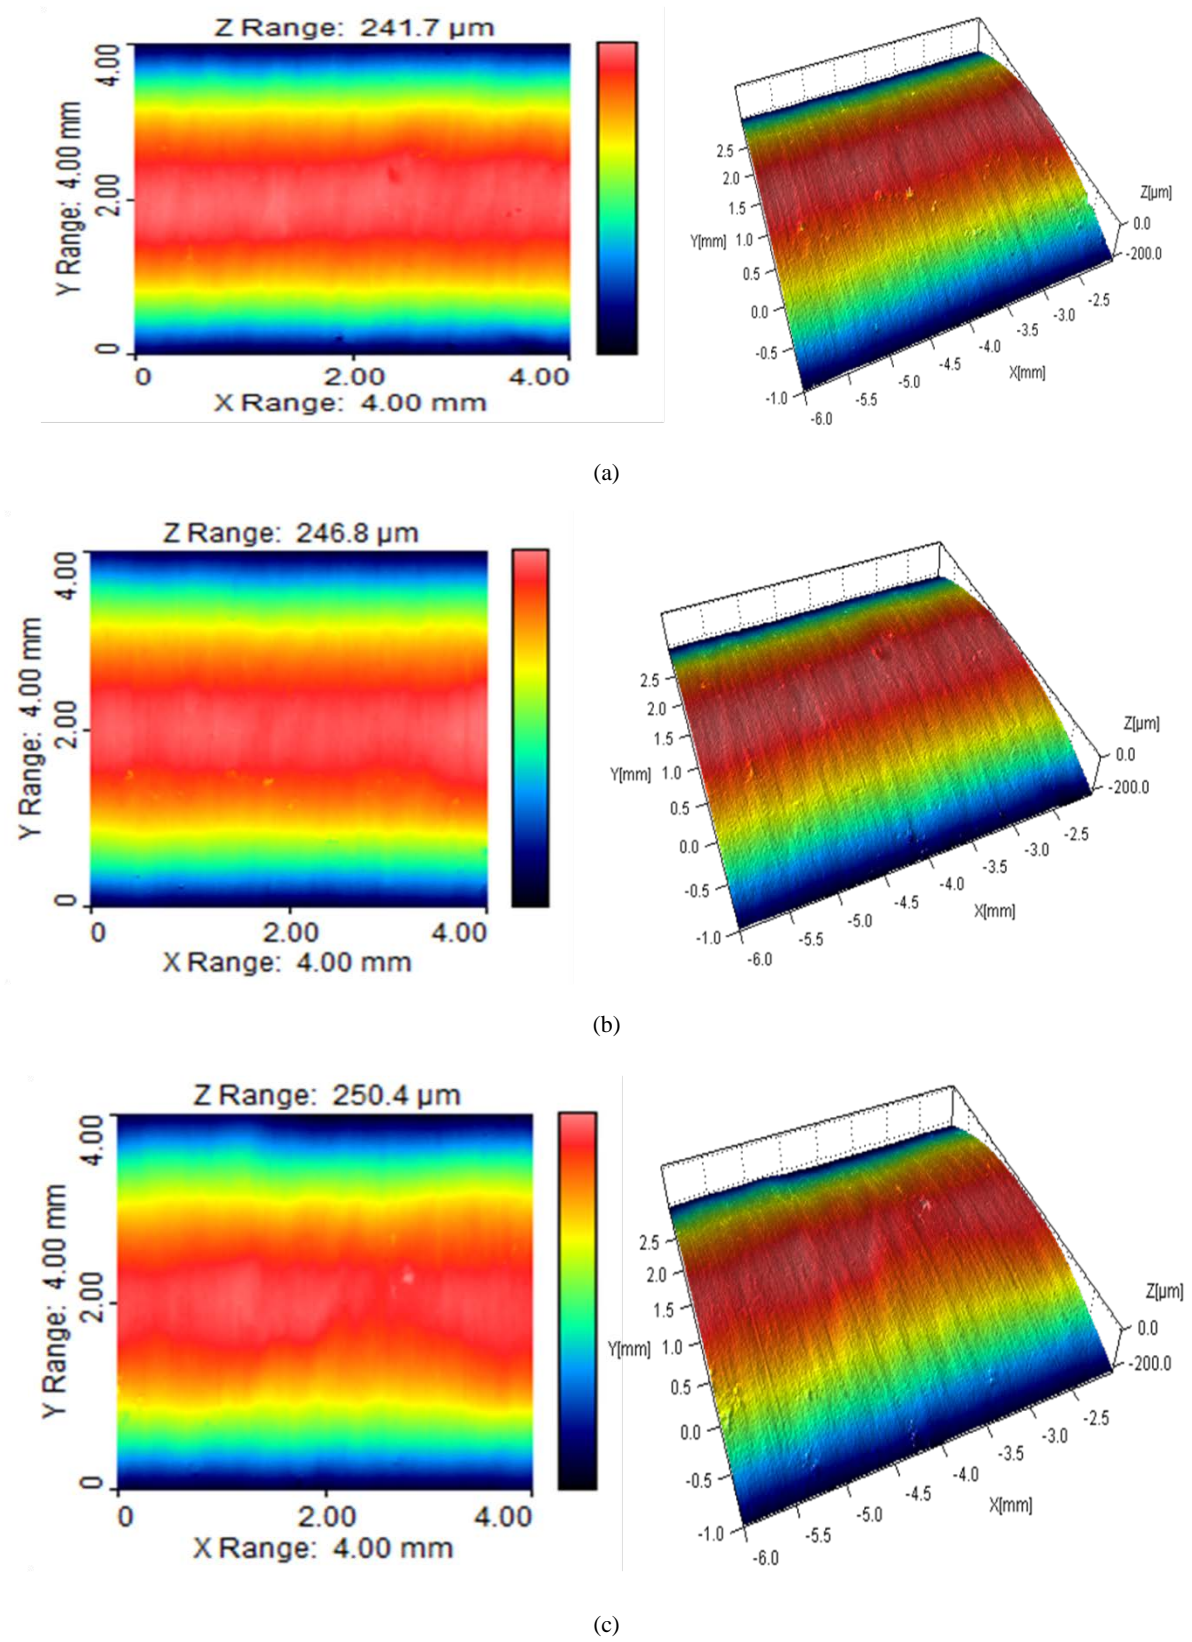



Figure 4. Surface visualisation produced by CNC lathe at (a) 200 rpm (b) 400 rpm (c) 600 rpm

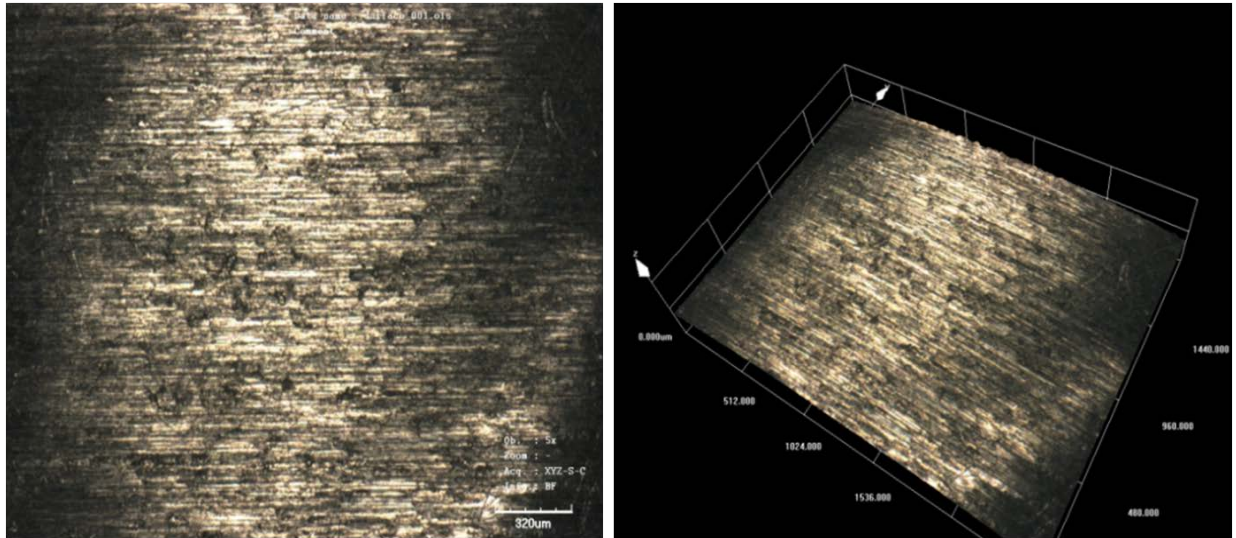

(a)

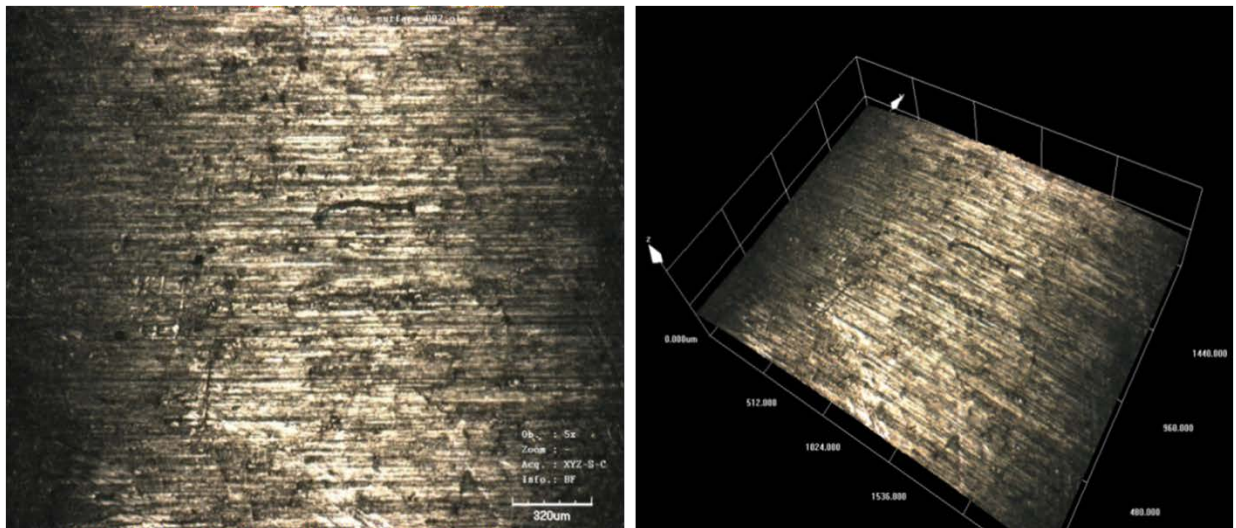

(b)

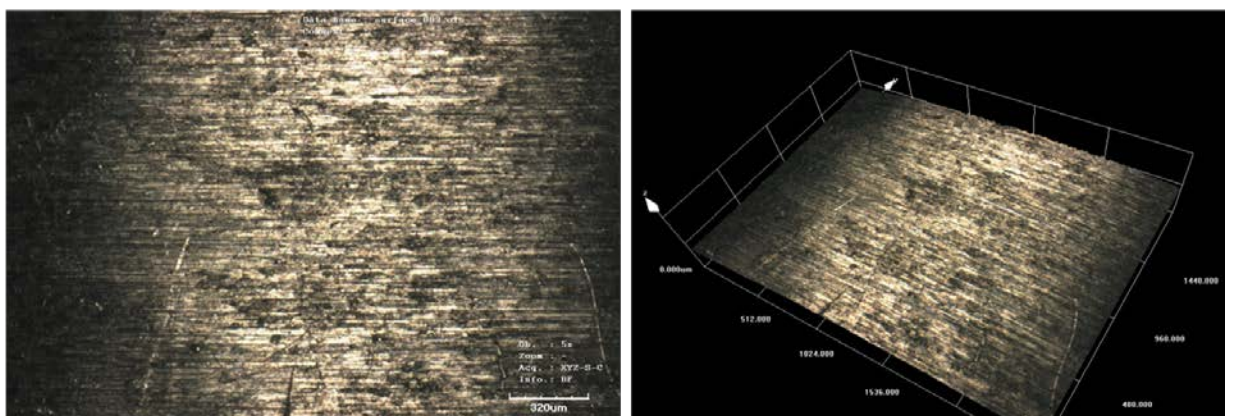

(c)

Figure 5. Surface topography by CNC Lathe surfaces (a) 200 rpm, (b) 400 rpm, (c) 600 rpm

4. Conclusion

The present work highlights the outcome of turning operation on A359/2%B₄C/2%Al₂O₃ by CNC lathe (SPRINT 16TC BATLIBOI). The study includes the measurement of surface roughness parameters namely Ra, Rq and Rz and the topographical study of the turned surface by 3D surface visualization images and topographical images. Based on observations the following conclusion has suggested:

1. The range of surface roughness value lies between 1.5 μ m to 2.9 μ m during the turning operation at varying rotational speed from 200 rpm to 600 rpm. The Improved surface finishing at higher rotational speed is observed which is attributed to the reduction in built-up edge (BUE) formation of cutting insert.
2. 3D surface images show the perfectly rolled and free from defects like porosity, voids or cracks. The surface texture shows the repetitive tool marks in the direction of feed and along the cutting direction. 2D and 3D surface topographical images revealed a flat surface full of repetitive cutting marks parallel to each other and along the direction of cutting. There are no significant topographical differences are varying rotational speed.
3. At the lower rotational speed, the tool marks are observed approximately parallel to each other, while at higher rotational speed the formation of the built-up edge is reduced which makes the smooth surface. The small scale of the micropores appears on the surface. It is attributed to the effect of high thermal energy and mechanical stresses per unit time per unit area of the circumferential length. At this stage, the tendency of dislodgment of reinforcement particles from the machined surface is increased and creates small-scale voids and porosity.

Declaration of conflicting interest

The author(s) declared no potential conflicts of interest concerning the research, authorship, and/or publication of this article.

Acknowledgement

The author(s) received no financial support for the research, authorship, and/or publication of this article.

References

- 1) S. P. Dwivedi, M. Maurya, N. K. Maurya, A. K. Srivastava, S. Sharma, A. Saxena. Utilization of Groundnut Shell as Reinforcement in Development of Aluminum Based Composite to Reduce Environment Pollution: a review. *EVERGREEN Joint Journal of Novel Carbon Resource Sciences & Green Asia Strategy*. 7,15, (2020).
- 2) M. Maurya, S. Kumar, V. Bajpai and N. K. Maurya, Process parameters, development and applications of stir cast composite: A review, *Materials Testing*. 62,196 (2020).
- 3) Manish Maurya, Sudhir Kumar, and Vivek Bajpai, Assessment of the mechanical properties of aluminium metal matrix composite: A review, *Journal of Reinforced Plastics and Composites*, 38,267 (2019)
- 4) Sashi Prakash Dwivedi, Nagendra Kumar Maurya and Manish Maurya, Assessment of hardness on AA 2014/Eggshell composite produced via stir casting method. *Evergreen Joint Journal of Novel Carbon Resource Sciences & Green Asia Strategy*, 6, 285, (2019).
- 5) Maurya, N.K., Maurya, M., Srivastava, A.K., Dwivedi, S.P., Kumar, A., Chauhan, S. Investigation of mechanical properties of Al 6061/SiC composite prepared through stir casting technique. *Materials Today: Proceedings*. (2019).<https://doi.org/10.1016/j.matpr.2019.09.003>.
- 6) Manish Maurya, Nagendra Kumar Maurya and Vivek Bajpai, Effect of SiC reinforced particle parameters in the development of aluminium based metal matrix composite. *Evergreen Joint Journal of Novel Carbon Resource Sciences & Green Asia Strategy*, 6, 200 (2019)
- 7) Nag A, Srivastava AK, Dixit AR, Mandal A, Das AK, Surface integrity analysis of wire-EDM on in-situ hybrid composite A359/Al₂O₃/B₄C, *Materials today Proceedings*, 5, 24632, (2018).
- 8) S. P. Dwivedi, N. K. Maurya, A. K. Srivastava, M. Maurya, Microstructure and mechanical properties of Al6061/Al₂O₃/flyash composite fabricated through stir casting, *Annales de Chimie-Science des Materiaux* 43, 341-346 (2019)
- 9) I. Narasimha Murthy, D. Venkata Rao, J.Babu Rao, Microstructure and mechanical properties of aluminium-fly ash nanocomposites made by ultrasonic method, *Materials & Design*, 35, 55 (2012).
- 10) S.T. Mavhungu, E. T. A. Kinlabi, M. A. Onitiri, F.M. Varachia. AMC for industrial use: Advances and Trends. *Procedia Manufacturing*, 7,178, (2016).
- 11) Rajesh Kumar Bhushan, Sudhir Kumar, Optimization of porosity of 7075 Al alloy 10% SiC composite produced by stir casting process through Taguchi method. *Int. J. Materials Engineering Innovation*, 1,116 (2009).
- 12) J. Hashim, L. Looney, M.S.J. Hashmi. Metal matrix composites: production by the stir casting method. *Journal of Materials Processing Technology*, 92,1(1999).
- 13) Srivastava. A Dixit. A.R., Tiwari. S, A Review on Fabrication and Characterization of Aluminium Metal, Matrix Composite (AMMC), *International Journal of Advanced Research and Innovation*, 2, 516, (2014).

- 14) Nag A, Srivastava AK, Dixit AR, Chattopadhyaya S, Mandal A, P. Hlavacek, D. Klichova M. Zelenak, S. Hloch, Influence of Abrasive Water Jet Turning Parameters on Variation of Diameter of Hybrid Metal Matrix Composite. In: Singh M., Kushvah B., Seth G., Prakash J. (eds) *Applications of Fluid Dynamics. Lecture Notes in Mechanical Engineering*. Springer, Singapore, (2018). https://doi.org/10.1007/978-981-10-5329-0_36.
- 15) Ashish Kumar Srivastava, Statistical optimization of wire-EDM during the processing of hybrid MMC, *International Journal of Mechanical and Production Engineering Research and Development*, **8**, 783 (2018).
- 16) AK Srivastava, AR Dixit, S Tiwari, A Review on the intensification of metal matrix composites and its non-conventional machining, *Science and Engineering of composite materials*, (2016). DOI: <https://doi.org/10.1515/secm-2015-0287>.
- 17) Ashish Kumar Srivastava, S.P. Dwivedi, Abhishek Sharma, Nagendra Kumar Maurya, Prabhat Ranjan, *International Journal of Engineering & Technology*, **7**, 434 (2018).
- 18) Garg H. K., Verma Ketan, Manna Alakesh and Kumar Rajesh, *International Journal of Latest Research in Science and Technology*, **1**, 36, (2012).
- 19) Sasimurugan T. and Palanikumar K., Analysis of the machining characteristics on surface roughness of a hybrid aluminium metal matrix composite (Al6061-SiC-Al₂O₃), *Journal of Minerals & Materials Characterization & Engineering*, **10**, 1213 (2011).
- 20) Baki, N., Reddy, A.C., Rao, T.B., Selection of optimal process parameters in wire electrical discharge turning while machining TI-6AL-4V ALLOY, *International Conference on Advanced Materials and Manufacturing Technologies (AMMT)* (2014).
- 21) Boujelbene, M., Bayraktar, E., Tebni, W., Salem, S. Ben, 2009, Influence of machining parameters on the surface integrity in electrical discharge machining. *Arch. Mater. Sci. Eng.* **37**, 110.
- 22) Das, A.K., Kumar, P., Sethi, A., Singh, P.K., Hussain, M., 2016. Influence of process parameters on the surface integrity of micro-holes of SS304 obtained by micro-EDM. *J. Brazilian Soc. Mech. Sci. Eng.* **38**, 2029.
- 23) Davim, J.P., 2010. Surface integrity in machining, e-ISBN 978-1-84882-874-2, DOI 10.1007/978-1-84882-874-2, Springer. (2010)
- 24) Grzesik, W., Rech, J., Wanat, T., Surface integrity of hardened steel parts in hybrid machining operations. *J. Achiev. Mater. Manuf. Eng.* **18**, 367 (2006).
- 25) Srivastava, A.K., Nag, A., Dixit, A.R., Tiwari, S., Scucka, J., Zelenak, M., Hloch, S., Hlavacek, P., Surface integrity in tangential turning of hybrid MMC A359/B 4 C/Al₂O₃ by abrasive water jet. *J. Manuf. Process.* **28**, 11 (2017).