

Local deformation and fracture behavior of high-strength aluminum alloys under hydrogen influence

Shimizu, Kazuyuki

Department of Mechanical Engineering, Kyushu University

Toda, Hiroyuki

Department of Mechanical Engineering, Kyushu University

Uesugi, kentaro

Japan Synchrotron Radiation Institute (JASRI)

Takeuchi, Akihisa

Japan Synchrotron Radiation Research Institute(JASRI)

<https://hdl.handle.net/2324/4483196>

出版情報 : Metallurgical and Materials Transactions A. 51 (1), pp.1-19, 2020-01. Springer
バージョン :
権利関係 :



Title:

Local deformation and fracture behavior of high-strength aluminum alloys under hydrogen influence

Authors:

Kazuyuki Shimizu^{*a}, Hiroyuki Toda^a, Kentaro Uesugi^b, Akihisa Takeuchi^b,

Affiliations:

a Department of Mechanical Engineering, Kyushu University, Fukuoka, 819-0395, Japan

b Japan Synchrotron Radiation Research Institute, Hyogo, 679-5198, Japan

Corresponding author:

Name: Kazuyuki SHIMIZU

Affiliation: Department of Mechanical Engineering, Kyushu University, Motooka 744, Nishi-ku, Fukuoka-city, Fukuoka, 819-0395, Japan

Phone: +81-92-802-3300

E-mail: kshimizu@kyudai.jp

Abstract

The local deformation and fracture behavior of high-Zn Al-Zn-Mg(-Cu) alloys under hydrogen influence were investigated by in situ tests through synchrotron X-ray tomography. Intergranular and quasi-cleavage fractures were induced by hydrogen, and strain localization by the presence of cracks was not observed by 3D strain mapping. This result suggests that the strain localization at the crack tip is smaller than the measurement limit of 3D strain mapping. The average crack-tip-opening displacements, which are one of the crack driving forces specified by fracture mechanics, directly measured from the tomographic slice were 0.14 and 0.23 μm for intergranular cracks and quasi-cleavage cracks, respectively. The crack driving force of the intergranular and quasi-cleavage cracks was small. The local deformation behavior at the crack tips was analyzed based on fracture mechanics. The local deformation field of the crack tip, which was characterized using the Rice-Drugan-Sham (RDS) solution rather than the Hutchinson-Rice-Rosengren (HRR) solution, was located within 20 μm of the crack tip, and its size was limited. The results of this work clarify that the intergranular and quasi-cleavage crack growth are caused by small driving forces; however, this behavior is not perfectly brittle, accompanying local deformation at the crack tip.

Keywords:

aluminum alloys; hydrogen embrittlement; X-ray tomography; intergranular crack; quasi-cleavage crack

1. Introduction

Al-Zn-Mg(-Cu) alloys are high-strength aluminum alloys that are widely used in aircraft and rolling stock, which require high strength-to-weight ratios. When the Zn or Mg content is increased to improve strength, susceptibility to stress corrosion cracking (SCC) increases, leading to delayed fracture ^[1-3]. Therefore, the SCC susceptibility of commercial alloys is suppressed both by adding trace elements such as Cr and Zr and by heat treatments such as overaging and retrogression-and-reaging treatments; the latter is a three-step heat treatment consisting of pre-aging, retrogression, and re-aging ^[4]. The SCC of Al-Zn-Mg(-Cu) alloys, particularly for crack growth behavior, has been speculated to be strongly related to hydrogen embrittlement (HE) ^[1,5]. The SCC and HE of aluminum alloys have been investigated by a slow strain rate test (SSRT) ^[6-8]. The degradation of mechanical properties by hydrogen depends on the strain rates in the SSRT. Kuramoto *et al.* reported that the true fracture strain of Al-4.9Zn-2.2Mg-1.3Cu alloy is approximately 17% at a strain rate of $1.67 \times 10^{-4} \text{ s}^{-1}$ but decreases to less than 5% at a strain rate of $1.67 \times 10^{-7} \text{ s}^{-1}$ in air ^[8]. Although SSRT is not employed, the HE of Al-Zn-Mg(-Cu) alloys is observed in tensile tests at strain rates of 10^{-4} to 10^{-3} s^{-1} when the tensile loading is periodically held ^[9]. When the holding time is longer, the embrittlement is more prominent. When the holding time increases from 0 to 2.1 ks, the fracture strain decreases from 23% to 10%, and the areal fraction of quasi-cleavage fracture increases from 0% to 20%. In the SSRT and holding-time tests, the diffusible hydrogen in the material is repartitioned during the plastic deformation, inducing time-dependent fracture ^[10-12]. That is, the localization of the hydrogen distribution inside the material strongly influences the mechanical properties in the aforementioned HE experiment.

The hydrogen distribution in a material is not uniform, even without any external stress ^[13]. The hydrogen is partitioned into trap sites such as vacancies, solute atoms,

1 dislocations, grain boundaries, particles, and pores ^[14]. The hydrogen partitioning in
 2 aluminum alloys is modeled as follows:

$$C_H = \theta_L N_L + \sum \theta_i N_i + C_{\text{pore}} \quad (1)$$

3 where C_H is the total hydrogen content in a material and θ_L and θ_i are the occupancies of
 4 the interstitial sites and i -th trap sites, respectively. N_L and N_i are the trap densities in the
 5 normal interstitial lattice sites and i -th trap sites, respectively. C_{pore} is the total molecular
 6 hydrogen content in the pores. Molecular hydrogen is widely understood to fill micron-
 7 sized holes, which are called pores, in aluminum alloys ^[14-17]. In aluminum alloys, pores
 8 are also present due to the hydrogen solubility gap between the liquid phase and solid
 9 phase, even in wrought materials ^[14]. It is hypothesized that the pores are filled with
 10 molecular hydrogen. The occupancy of hydrogen in each trap site, θ_i , is expressed by Eq.
 11 (2) based on Oriani's theory, which describes the local thermal equilibrium between
 12 interstitial and other trap sites ^[13]:

$$\frac{\theta_i}{1 - \theta_i} = \theta_L \exp\left(\frac{E_b}{RT}\right) \quad (2)$$

13 where E_b is the binding energy between hydrogen and the i -th trap site, R is the gas
 14 constant, and T is the temperature. The binding energy is experimentally derived by
 15 subtracting the activation energy of hydrogen diffusion in a lattice from the desorption
 16 energy measured by thermal desorption analysis (TDA). The binding energies in steel are
 17 often evaluated by TDA ^[18]; however, such analyses are not straightforward in the case
 18 of aluminum alloys ^[19,20] because the trap sites of hydrogen easily change with the
 19 increasing temperature. Therefore, the binding energy of each type of trap site in
 20 aluminum has been investigated by first-principles simulation (FPS), and the energies are
 21 0.02-0.19, 0.3, and 0.45-0.60 eV at the grain boundaries, vacancies, and surfaces,
 22 respectively ^[21]. According to Eqs. (1) and (2), the hydrogen partitioned to each trap site

increases as the trap-site density and binding energy increase. Unlike the binding energy, the trap site density readily varies because of the thermal history and deformation^[2,13,14,20]. As the dislocation density increases from 5.36×10^{12} to $2.86 \times 10^{14} \text{ m}^{-2}$ under a 6% plastic strain, the trap-site density of the dislocations is estimated to increase from 3.39×10^{22} to $1.81 \times 10^{24} \text{ site/m}^3$ ^[20]. In general, when plastic strain is applied to a material, the plastic strain (i.e., dislocation) is localized to the grain boundaries, phase boundaries, particles, crack tips, etc. under the influence of the microstructure and cracks. Therefore, if hydrogen migrates from other sites or from the environment, the hydrogen content in the dislocations increases, and the hydrogen distribution is expected to localize further. To understand HE from the viewpoint of hydrogen localization, the visualization of the hydrogen distribution in materials is essential. However, hydrogen is the smallest element, and embrittlement occurs on the order of mass ppm. Because direct observation is extremely challenging, hydrogen is indirectly visualized using a hydrogen microprint technique in the many studies on aluminum alloys. The principle of the hydrogen microprint technique is that a silver halide emulsion is coated on the specimen surface, and the hydrogen that migrates from the inside to the surface reduces the silver ions in this emulsion. The observation of the silver particles thus indirectly enables the visualization of the hydrogen distribution on this surface. Silver particles (corresponding to hydrogen) are detected at the grain boundaries^[22], particles^[23,24], slip bands^[25], and cracks^[26] after plastic deformation, indicating that the hydrogen distribution is localized by loading. The localization of hydrogen and deformations mutually influence each other. Bhuiyan *et al.* reported that the synergistic effect of the tensile stress and high hydrogen content at the crack tip leads to local flow stress reduction and facilitates localized deformation^[9].

To explain the HE mechanism, frameworks such as the hydrogen-enhanced

1 localized plasticity (HELP), hydrogen-enhanced decohesion (HEDE), and hydrogen-
2 enhanced strain-induced vacancy (HESIV) mechanisms have long been considered [27].
3 HELP describes the interaction between dislocations and hydrogen, HEDE describes the
4 reduction of the cohesive bond energy between atoms by hydrogen accumulation, and
5 HESIV describes that hydrogen contributes to the formation of vacancies during
6 deformation. Nevertheless, the discussion continues, and the findings on HE sometimes
7 differ among researchers. First, as a specific example, findings on hydrogen trapping at a
8 grain boundary, which is considered the origin of grain boundary fracture, are described.
9 Yamaguchi *et al.* reported that hydrogen is strongly trapped at a high-angle grain
10 boundary, where the Σ value and the grain boundary energy are high [28,29]. In addition,
11 Mine *et al.* suggested that high-angle grain boundaries are not effective trap sites but that
12 hydrogen is strongly trapped at low-angle grain boundaries [30]. Subsequently, Nagumo *et*
13 *al.* observed that in quasi-cleavage cracks, the excess vacancies stabilized by hydrogen
14 grow into nanovoids and that cracks are initiated by coarsening nanovoids [31]. Neeraj *et*
15 *al.* documented the presence of nanodimples on quasi-cleavage facets [32]. Martin *et al.*
16 concluded that the initiation and growth of voids along the slip band intersection leads to
17 quasi-cleavage fracture based on transmission electron microscopy (TEM) images of the
18 region just below the quasi-cleavage facet [33]. Their claims are similar at first sight.
19 However, Neeraj *et al.* concluded that the vacancy-induced nanovoid nucleation and
20 coalescence is a failure mechanism, while Martin *et al.* concluded that plastic processes,
21 which are enhanced and accelerated by the presence of hydrogen, widen voids, producing
22 a fracture surface.

23 Intergranular and quasi-cleavage cracking constitute well-known HE behavior,
24 but the influence of hydrogen on crack growth and the crack driving forces are not well
25 understood, as mentioned above. Much of the typical evaluation of HE is based on

1 simulations with extremely simplified microstructures or observations after
2 loading/fracture. For a further understanding of HE, it is desirable to observe in situ the
3 hydrogen-induced fracture behavior, i.e., intergranular fracture and quasi-cleavage
4 fracture behavior, and quantitatively examine it with parameters such as strains and the
5 crack driving force. To achieve this purpose, 2D observation is insufficient because the
6 stress/strain state is different between the inside and the surface of the material. The direct
7 observation of the 3D fracture behavior is preferred. The in situ observation of the fracture
8 behavior by synchrotron X-ray tomography is suitable for this. In recent years, the spatial
9 resolution of projection-type tomography has reached 1.25 μm , approaching the physical
10 limit ^[34]. This spatial resolution is enough to observe cracks inside the material. With the
11 3D strain mapping via X-ray tomography developed by Kobayashi *et al.*, it is also
12 possible to analyze the 3D elemental strains inside the material ^[35].

13 In this study, we experimentally clarify the intergranular/quasi-cleavage fracture
14 behavior of Al-Zn-Mg(-Cu) alloys under the influence of hydrogen. For this purpose, the
15 elemental strains at the vicinity of the crack tip were directly analyzed by synchrotron X-
16 ray tomography, which enables 3D strain mapping inside a material. Furthermore, the
17 crack morphologies were visualized by imaging-type tomography, developed in recent
18 years, and the crack driving force was analyzed based on the fracture mechanics
19 parameters. In addition, the pores influence the mechanical properties of the aluminum
20 alloys. Toda *et al.* have clarified that the growth and coalescence of pores is the dominant
21 factor leading to the ductile fracture of aluminum alloys ^[17]. The origin of the pores is
22 supersaturated hydrogen in the aluminum, and the hydrogen can thus be interpreted as
23 indirectly affecting the mechanical properties through the pores. In this study, both the
24 atomic hydrogen in the matrix and the pores (i.e., molecular hydrogen) were evaluated as
25 factors responsible for the HE.

2. Methodology

2.1 Specimens

The materials used in this study were Al-10.1Zn-1.2Mg alloy and modified A7150 alloy. The modified A7150 alloy had a chemical composition (in mass %) of 9.9 Zn, 2.3 Mg, 1.4 Cu, 0.06 Si, 0.05 Fe, 0.04 Ti, 0.15 Zr, and balance Al (hereinafter, Al-9.9Zn-2.3Mg-1.4Cu alloy). An Al-10.1Zn-1.2 Mg alloy containing trace iron (< 0.01 mass % Fe) was also prepared. The Al-10.1Zn-1.2Mg alloy was prepared by homogenization at 773 K for 7.2 ks after casting, hot rolling at 723 K with a rolling reduction of 50%, and solution treatment at 773 K for 7.2 ks. Immediately after the solution treatment, aging was carried out for 144 ks at 393 K and 25.2 ks at 453 K to overage. The preparation process of the Al-9.9Zn-2.3Mg-1.4Cu alloy was the same as Material MH described in the literature^[9], and this aging condition was also an overaged one. After aging, all tensile test pieces were processed using wire-cut electrical discharge machining (EDM). The shape of the tensile test pieces is the same as that reported in the literature^[9,36]. The gauge length of the tensile test piece was 0.7 mm, and the cross-sectional area was 0.6×0.6 mm². Here, EDM also served as a means of hydrogen charging. Other authors have confirmed that the hydrogen content increases from 0.14 mass ppm to 6.97 mass ppm by EDM in water^[9,12]. In addition, a high-hydrogen Al-10.1Zn-1.2 Mg alloy was prepared with a hydrogen content higher than the typical hydrogen charge through performing EDM twice on the surface. After EDM, the test piece was considered to have a high hydrogen content on its surface. To distribute the hydrogen to the interior of the specimens, the specimens were stored in acetone for approximately 4 days and subjected to both tomographic experiments and TDA, which is described later. Assuming that the diffusion coefficient of the hydrogen in aluminum at room temperature was 2.1×10^{-13} m²/s^[37,38],

the diffusion distance after 4 days was estimated to be 0.38 mm. This diffusion distance is larger than half of the specimen size, and the hydrogen is thus assumed to diffuse from the surface to the center of the specimens. The aforementioned diffusivity of 2.1×10^{-13} m²/s was determined by using pure aluminum. The effective diffusivity of the overaged Al-6.9%Zn-2.65%Mg-0.06%Cu alloy has been reported to be 1.05×10^{-11} m²/s at 298 K [39]. The diffusion distance after 4 days calculated from this effective diffusivity was 2.7 mm. The diffusion distance calculated from the diffusivity determined for the alloy similar in composition to the one used in this study is sufficiently larger than the specimen size. Therefore, we assumed that hydrogen diffused into the specimen, even if the surface hydrogen concentration slightly changed. In view of this, we speculate that the aforementioned diffusivity of 2.1×10^{-13} m²/s is conservative.

In addition, four Al-10.1Zn-1.2Mg alloys (Fig. 1 (a-d)) were prepared to separate and evaluate the influence of pores and hydrogen in the matrix on fracture behavior. The four Al-10.1Zn-1.2Mg alloys differ in their volume fraction of pores, V_f , and their hydrogen content, C_H . As shown in Fig. 1 (b-d), to vary the volume fraction of pores and the hydrogen content, thermal cycle (TC) processes were performed in air and in a vacuum. The temperature range of the thermal cycle was 653-753 K, the heating rate was 0.028 K/s, and the number of cycles was set to 10. The TC process was carried out in air (during which the volume fraction of pores increased) or in a vacuum of 10^{-5} Pa (during which the hydrogen content and the volume fraction of pores decreased).

A thermal desorption apparatus equipped with a gas chromatograph (NISSHA FIS, Inc., PDHA-1000) was used to measure the hydrogen content in the prepared Al-10.1Zn-1.2Mg alloys. The temperature range of TDA was from room temperature to 853 K and the heating rate was 0.025 K/s. In TDA of Al-10.1Zn-1.2 Mg alloys, all hydrogen in the material was not desorbed in a single analysis. When TDA was performed ten consecutive

times on the same specimen, all of the hydrogen was still not desorbed, and 0.1 mass-ppm of hydrogen remained in the specimen. This is because the molecular hydrogen that filled the pores (with the highest binding energy among the trap sites ^[21,40]) is not easily desorbed during TDA. As it is time-consuming to perform TDA ten times for all specimens, the hydrogen content was defined using the total amount of hydrogen desorbed in one analysis in this study.

2.2 Synchrotron X-ray imaging and in situ tests

In situ observations of fracture behavior via synchrotron X-ray tomography were performed on BL20XU and BL37XU of SPring-8, Japan. The projection-type tomography configuration shown in Fig. 2 (a) was employed to evaluate the fracture behavior of the entire material. To observe the intergranular and quasi-cleavage crack tip with higher resolution, the imaging-type tomography configuration shown in Fig. 2 (b) was used. The theoretical resolution was 1 μm and 100 nm for the projection-type and imaging-type tomography, respectively. The field of view of the projection-type tomography was $1024 \times 1024 \times 1024 \mu\text{m}^3$, and the entire gauge-length region ($600 \times 600 \times 700 \text{ mm}^3$) of the specimen can be visualized completely in 3D. Although the resolution of imaging-type tomography is superior to that of projection-type tomography, its field of view is limited to a cylindrical region with a diameter of 83 μm and a height of 59 μm . Therefore, imaging-type tomography was used to visualize the vicinity of the crack tips of the intergranular and quasi-cleavage cracks in 3D. The X-ray was monochromated by a Si(111) double-crystal monochromator, and the energy was tuned to 20 keV. The detector consisted of a 2048×2048 pixel CMOS camera, an optical lens, and a scintillator. In the projection-type tomography, a $\text{Lu}_2\text{Al}_5\text{O}_{12}:\text{Ce}$ single crystal was used for the scintillator, and $\text{GdO}_2\text{S}:\text{Tb}$ was used in the imaging-type tomography. The distances

1 between the specimen and the detector were 20 mm and 23.5 m in projection-type and
2 imaging-type tomography, respectively. In addition, a condenser zone plate was used to
3 locally improve X-ray flux, and an apodization Fresnel zone plate was used to focus the
4 X-ray in the imaging-type tomography. These X-ray imaging elements were developed at
5 SPring-8 for ultrahigh resolution X-ray imaging; the details are described elsewhere ^[41,42].

6 A small material testing machine (CT500, Deben UK Ltd.,) was installed on the
7 rotation stage of the X-ray tomography system, and the in situ observation of the fracture
8 behavior was performed. In the tensile test, the initial strain rate was set at $3 \times 10^{-3} \text{ s}^{-1}$ by
9 displacement control, and the test was performed at room temperature. This strain rate
10 corresponds to the lowest setting of the in situ testing machine used and was measured
11 from the tomographic images of tensile test-piece before and after loading. It was
12 necessary to temporarily stop the tensile loading and hold the displacement during
13 tomography observation. Here, the holding time was 0.9 ks, and in situ tests were also
14 performed in which the holding time was changed to 0.3 ks or 2.7 ks. In this experiment,
15 in situ observations were carried out while holding the displacement for tensile strain
16 increases of approximately 3%, which were repeated until fracture. The fracture surface
17 was observed by a scanning electron microscope (SEM) after the tomographic
18 experiments. A total of 1800 projection images were captured as the specimen was rotated
19 by 180 degrees in steps of 0.1 degrees in tomographic observation, and these images were
20 reconstructed into a 3D image by a convolution backprojection algorithm.

21 In addition, 2D projection images of growing cracks were continuously observed
22 using both an in situ testing machine and a projection-type tomography system. This in
23 situ 2D imaging was performed to visualize the intergranular crack growth of an Al-
24 10.1Zn-1.2 Mg alloy.

2.3 3D Image analysis

Intergranular and quasi-cleavage cracks were extracted from 3D tomographic data and analyzed for morphology and crack tip opening displacement (CTOD). The CTOD was directly measured from 2D virtual cross-sections of the extracted 3D crack image based on a report in the literature describing the measurement of the CTOD from a 3D tomographic image [43]. In the 2D virtual cross-sections of cracks, (i) the point of the crack tip was measured, (ii) lines were drawn upward and downward at 45 degrees from the crack tip until the lines contact the upper and lower surfaces of the crack, and (iii) the distance between the aforementioned contact points of the upper and lower crack surfaces was defined as the CTOD. The locations where the CTOD was measured depended on the morphology of the crack and were approximately 1 to 5 μm behind the crack tip. The details of the CTOD analysis of the crack inside the material are available elsewhere [43].

Furthermore, all the pores and particles in the specimens were analyzed in 3D, and their center of gravity, volume fraction, diameter, and surface area were calculated by the marching cubes algorithm that creates a 3D triangle model from a tomographic image [44]. The molecular hydrogen content in the pores, C_{pore} , was estimated from the analyzed pore diameter [12,14,17] and can be expressed by the energy balance of the surface energy and the internal pressure of hydrogen, $P = 4\gamma/d$, as follows:

$$C_{\text{pore}} = \sum \frac{2\pi\gamma d_i^2}{3RT} \quad (3)$$

where d_i is the diameter of the i th pore, R is the gas constant, T is the temperature, and γ is the surface energy (1.16 J/m², which is the measured value for an Al(111) face [14]). Recent FPSs revealed that the other surface energies are approximately 10–20% greater than that of the (111) surface [45]. Because the (111) face of aluminum has the lowest surface energy, the estimation yields conservative lower limit values. Recent FPSs have clarified that the pore surface is a hydrogen adsorption trap site; however, this factor is

not considered in Eq. (3) ^[45], which applies only to the estimation of the molecular hydrogen inside the pores.

3D strain mapping inside the material was achieved using the physical displacements of the pores and particles, which were visualized by X-ray tomography ^[35]. This calculation procedure of the strains is outlined below. First, identical pores and particles were tracked throughout loading using the matching parameter method ^[35]. Next, tetrahedra with tracked particles as vertices were formed by Delaunay tessellation. Subsequently, various strain components were calculated from the deformation of a tetrahedron and indicated its center of gravity. Further details of the matching parameter method and 3D strain mapping are available elsewhere ^[35].

3. Results

3.1 Hydrogen embrittlement behavior

3.1.1 Microstructure and pores

Fig. 3 shows the microstructure of the unloaded Al-10.1Zn-1.2Mg alloy as observed through projection-type tomography. The preparation process of the specimen shown in Fig. 3 (a-d) corresponds to subfigures (a-d) in Fig. 1, respectively. Here, virtual cross-sections of four representative specimens are shown, and each figure shows the volume fraction of pores, V_f , and the hydrogen content, C_H , as measured by TDA. Fig. 3 (a) shows a typical specimen without a thermal cycle. C_H is increased by EDM, and V_f is low. Second-phase particles on the micrometer scale were not observed. Relatively spherical pores were observed in Figs. 3 (c) and (d), on which thermal cycling was performed before solution treatment. The pores grew and C_H decreased during thermal cycling. The specimen shown in Fig. 3 (d) exhibited high V_f and low C_H because thermal

cycling was applied after the EDM of the test piece. Thus, the combination of thermal cycling and EDM enabled us to prepare specimens with different V_f and C_H .

The mechanism by which the volume fraction of the pores changes during the TC process is considered as follows. As described in Section 2.3, the internal pressure of the pore is estimated by $P = 4\gamma/d$. Assuming that the diameter of the pore is 3 μm and the surface energy is 1.16 J/m², the pressure is estimated as 1.5 MPa at room temperature. In the case of the TC process in air, it is believed that this internal pressure increases in a high-temperature environment to induce local creep deformation, causing the growth of pores^[46]. In contrast, in a TC process in vacuum, hydrogen is released from the specimen, and the pore pressure is also reduced according to Sieverts' law^[40]. In the TC process in vacuum, the internal pressure of the pores gradually decreases according over time, and therefore the morphology of the pores is considered to have shrunk.

3.1.2 Changes due to the hydrogen content and the holding time

In this subsection, first, the changes in the HE behavior due to the hydrogen content are discussed based on the results of using specimens with a low V_f and high C_H and with low V_f and low C_H , as shown in Fig. 3 (a) and (b), respectively. Fig. 4 (a) shows the nominal stress-nominal strain curves in the tomographic in situ tensile test. It is found that the fracture strain was increased upon reducing the hydrogen content by the TC process. As shown in Fig. 5(a-b), a reduction in the area fraction of intergranular and quasi-cleavage fracture was observed on the fracture surface due to the reduction of the hydrogen content. However, intergranular and quasi-cleavage fracture still occurred in the alloy with reduced hydrogen content. The hydrogen content of this alloy was 0.41 mass ppm, and it was found that HE occurs at a hydrogen content that represents a practical level^[47].

Next, the changes in the HE behavior due to the holding time are discussed based on the results of using the specimen with low V_f and high C_H , as shown in Fig. 3 (a). Fig. 4 (b) shows the nominal stress-nominal strain curves in the tomographic in situ tensile test. The three curves differ in the holding time of the tensile test. As described in the experimental section, it is necessary to hold the load and fix the displacement during the tomographic scan. The holding times were set to 0.3, 0.9, and 2.7 ks, as shown in Fig. 4 (b). The fracture strain was found to decrease with increasing holding time. Cracks may grow during holding, which was observed in particular with a holding time of 2.7 ks. These fracture surfaces are shown in Fig. 6. As shown in Fig. 6 (a-c), the area fraction of intergranular and quasi-cleavage fracture increased with increasing holding time and decreasing fracture strain. At holding times of 0.3, 0.9, and 2.7 ks, the area fractions of quasi-cleavage fracture were 24%, 19% and 38%, respectively, and the area fractions of intergranular fracture were 19%, 58% and 61%, respectively.

The strain at which the cracks initiated was 15.8%, 13.2% and 3.5% at holding times of 0.3, 0.9 and 2.7 ks, respectively. With increasing holding time, the strain at which cracks initiated decreased. Cracks observed through projection-type tomography are superimposed on the fracture surface, as shown in Fig. 6 (d-f). Three cracks captured at different strains are superimposed on each fracture surface in Fig. 6 (d-f). The crack that initially occurred, indicated by yellow, grows into the cracks indicated by green and blue depending on the loading. After the initial cracking, the increment of the applied displacement was 0.02 mm for three holding-time tests. Even though the applied displacement is the same, it was found that the crack grew rapidly as the holding time increased. All the initial cracks were intergranular cracks shown in the yellow crack in Fig. 6 (d-f), which transitioned to quasi-cleavage cracks and ductile cracks due to subsequent loading. The characteristic aspect of visualized crack growth is that the crack

grew gradually in response to the given displacement rather than instantaneously advancing on one grain boundary or one facet.

The relation between the holding time and crack growth of the Al-9.9Zn-2.3Mg-1.4Cu alloy was previously investigated ^[9,12,36]. The embrittlement became prominent as the holding time increased, similar to the behavior observed for the present Al-10.1Zn-1.2Mg alloy. However, in the cracks that formed the fracture surface, the initial crack was a quasi-cleavage crack. The influence of the holding time on the HE behavior is related to the local accumulation of hydrogen around the crack tips.

To investigate the relationship between the hydrogen accumulation and intergranular fracture more deeply, a high-hydrogen Al-10.1Zn-1.2 Mg alloy was subjected to EDM twice on the surface. The hydrogen content of this specimen, as measured by TDA, was 25.4 mass ppm. No blisters formed on the surface, even with twice the hydrogen charging, and hydrogen was considered to be present in matrix trap sites such as the grain boundaries, vacancies, and dislocations. This specimen with a high hydrogen content was mounted onto an in situ tensile test machine, and the intergranular crack growth under constant displacement was 2D-imaged. A monotonic tensile load was applied to the specimen until cracking occurred. The applied strain measured from the projection images was 4.5%. Then, the loading was stopped, and X-ray projection images continued to be captured under constant displacement. The X-ray projection images of the specimen before and after cracking are shown in Fig. 7. The times shown in Fig. 7 (b-d) are the time elapsed after the displacement was fixed. As is evident in Fig. 7 (a-b), the monotonic tensile load introduced multiple cracks into the specimen. Figs. 7 (c) and (d) show 2D projection images after 65 and 130 s elapsed from Fig. 7 (b) with the displacement fixed. As indicated by the red arrows, continuous intergranular crack progression was observed even when the displacement was fixed. The growth rate was

approximately 1 $\mu\text{m/s}$, and the crack tip was sharp. The influence of the holding time and the hydrogen content on the HE behavior is related to the local accumulation of hydrogen around the crack tips, which is discussed in detail later.

3.1.3 Effect of particles

Fig. 8 (a) and (b) show tomographic virtual cross-sections of the Al-10.1Zn-1.2Mg alloy without and with trace iron, respectively. Fig. 8 (c) and (d) show their fracture surfaces after the tensile test at a holding time of 0.9 ks. The emission spectrochemical analysis of this specimen was performed, but the increased Fe content was outside the detection range of the device (i.e., below 0.01 mass %). The existence of the particles shown with white contrast in Fig. 8 (b) is confirmed. As a result of the SEM-EDX analysis, the average chemical composition of the particles was determined to be $\text{Al}_{79}\text{Fe}_{14}\text{Zn}_7$. Homogenization and solution treatment of Al-10.1Zn-1.2Mg were performed at 773 K. On the basis of the isothermal section at 773 K of the Al-Zn-Fe ternary phase diagram^[48], this particle is presumed to be Zn-bearing $\text{Fe}_4\text{Al}_{13}$. The volume fractions of pores and particles and the hydrogen content were 0.08%, 0.41%, and 2.08 mass ppm, respectively. The number density of particles was also analyzed three-dimensionally from the tomographic volume and was found to be $8.35 \times 10^{13} \text{ m}^{-3}$. If the particles are assumed to be uniformly dispersed inside a specimen, the average nearest-neighbor distance of the particles is 28 μm .

The fracture surface shown in Fig. 8 (d) is remarkably different from that in Fig. 8 (c), although the volume fraction of pores and the hydrogen content are equivalent to those of the alloy without trace iron. Relative to Fig. 8 (c), the intergranular and quasi-cleavage fracture areas in Fig. 8 (d) were reduced, and a dimple fracture was observed. TDA was conducted to evaluate the change of the fracture surfaces with and without

particles from the viewpoint of hydrogen trapping on particles. The hydrogen desorption curves of these specimens are shown in Fig. 9. Identification of the TDA peaks of aluminum alloys is not simple. For example, interpretations differ among researchers as to whether the maximum peak at approximately 830 K is the peak of hydrogen desorbed from pores or that of hydrogen desorbed from vacancies ^[19,49,50]. The heat of dissolution of molecular hydrogen, the binding energy of adsorbed hydrogen on aluminum surface and the binding energy of vacancies have been calculated by recent first-principles calculations as 0.68 eV, 0.60 eV at maximum, and 0.30 eV, respectively ^[21]. Given the aforementioned order, this maximum peak likely corresponds to the hydrogen desorbed from the pores. Pores often heterogeneously nucleate on micron-scale particles in aluminum alloys during heat treatment ^[14,17,51]. The volume fraction of pores increased from 0.06% to 0.08% because the micron-scale particles (i.e., the nucleation sites of pores) increased in the Al-Zn-Mg alloy with trace iron, leading to the peak at approximately 830 K in Fig. 9 (a). Furthermore, as evident in Fig. 9 (b), a broad peak was observed in the temperature range from 650 to 730 K in the Al-Zn-Mg alloy. In this temperature range, vacancy concentration, dislocation density, and grain size change. We considered that both the change in the trap-site densities and the hydrogen desorption from the trap sites occurred, resulting in several overlapping desorption peaks observed as a broad peak. On the other hand, the peak at 714 K observed for the Al-Zn-Mg alloy with trace iron is sharp compared with the broad peak for the Al-Zn-Mg alloy without iron. Particles in the Al-Zn-Mg alloy with trace iron were formed during solidification and were not dissolved in the matrix during homogenization and solution treatment at 773 K for 7.2 ks. Therefore, in the temperature range of 650 to 730 K, the structural variation of particles is considered to be minor relative to the variations of vacancies, dislocations and grain sizes. Given the aforementioned viewpoints, diffusible hydrogen trapped at

1 grain boundaries, dislocations or vacancies partitioning to particles would explain the
2 changes in the hydrogen desorption curves in Fig. 9 (b) due to particles.

3 The results from Figs. 8 and 9 indicate that intergranular and quasi-cleavage
4 fracture can be suppressed by preferentially trapping hydrogen in the particles even
5 though the hydrogen content in the whole material is constant. Regarding suppression of
6 intergranular and quasi-cleavage fracture by particles, the same tendency as the present
7 result also appeared in an Al-9.9Zn-2.3Mg-1.4Cu alloy. Su *et al.* investigated the
8 influence of particles on HE behavior by preparing Al-9.9Zn-2.3Mg-1.4Cu alloys with
9 different Fe and Si contents [36]. Based on their tensile tests, the area fractions of quasi-
10 cleavage fracture were 38%, 30% and 28% in the specimens having both Fe and Si
11 contents of 0.01, 0.05 and 0.3 mass %, respectively. In specimens where the content of
12 Fe and Si is high and Al₇Cu₂Fe and Mg₂Si particles are distributed at high density,
13 intergranular and quasi-cleavage fracture are suppressed. For this reason, Su *et al.*
14 considered that the amount of hydrogen trapped at dislocations and at the crack tip
15 decreases in a relative sense depending on the particles. Therefore, the quasi-cleavage
16 fracture could be suppressed, which is consistent with the present experimental results
17 using Al-10.1Zn-1.2Mg alloys.

18 The hydrogen trap sites of Al₇Cu₂Fe and Mg₂Si are still unclear. Hydrogen trap
19 sites related to particles include sites inside the particles, at
20 coherent/semicoherent/incoherent interfaces, and within strain fields around the particles
21 [52–56], but the ones that apply to Al₇Cu₂Fe and Mg₂Si are not yet understood. Currently,
22 we are promoting research focusing on the possibility of hydrogen trapping inside
23 particles, and the results will be published in the future.

3.1.4 Influence of atomic hydrogen and pores

As mentioned in the introduction, pores in aluminum have been reported to affect the mechanical properties [17]. This report revealed the role of pores in ductile fracture, but the role of the pores in HE is still unclear. The inside of the pore is filled with molecular hydrogen, and its hydrogen content is expressed by Eq. (3). Therefore, the pores in aluminum alloys can be regarded as containing molecular hydrogen. In this subsection, the effects of atomic hydrogen and molecular hydrogen are separately evaluated from the viewpoint of the HE behavior.

Tomographic in situ tensile tests were performed by means of several specimens with different volume fractions of pores and hydrogen content in the matrix, as shown in Fig. 3. The four specimens shown in Fig. 3 are representative, and eight other specimens (Two specimens for each step in the process of (a) to (d) in Fig. 1) were also prepared. Tomographic in situ tests were not performed on these eight specimens, but the tomographic observation of the pores was performed to estimate the molecular hydrogen content at no loading. After that, the hydrogen embrittlement behavior was investigated in the laboratory under the same tensile conditions as those of the tomographic in situ tests. Here, the holding time was set to 0.3 ks. After this holding time, the fracture surfaces were observed by SEM, and the area fraction of the intergranular and quasi-cleavage fracture surfaces was analyzed. The hydrogen content in each specimen was also analyzed by TDA, and the area fraction of intergranular and quasi-cleavage fracture, total hydrogen content, and molecular hydrogen content in a total of 12 specimens were investigated. To evaluate the effects of atomic hydrogen and molecular hydrogen on the HE, the hydrogen content in the matrix, C_{mat} , was defined as follows:

$$C_{\text{mat}} = C_{\text{total}} - C_{\text{pores}} \quad (4)$$

where C_{total} is the total hydrogen content of each specimen as measured by TDA.

The area fractions of ductile, quasi-cleavage, and intergranular fractures are summarized in terms of the hydrogen content in the matrix and the pores, and the results are described in Fig. 10. Here, a contour map shows the area fractions of each fracture mode. Ductile fracture in Fig. 10 was defined as a fracture surface that is neither intergranular fracture nor quasi-cleavage fracture. As the hydrogen content in the matrix increases, the ductile fracture transitions to a quasi-cleavage fracture. When the content increases further, intergranular fracture tends to occur. In contrast, it has been clarified that the role of the hydrogen content in pores is minor in the transition of fracture modes. With regard to the ductile fracture of an AA2024 alloy at room temperature and an AA5086 alloy at high temperature, it has been reported that the growth and coalescence of pores dominate the fracture behavior^[17,51]. Even with the same aluminum-based alloys, the high-hydrogen Al-10.1Zn-1.2Mg alloy undergoes HE, resulting in intergranular and/or quasi-cleavage fracture. It can be concluded that the influence of pores on fracture is small since HE occurs before the growth and coalescence of pores.

3.2 Local deformation and fracture behavior around cracks

3.2.1 3D strain mapping ahead of the crack tip

As described in Section 3.1, it was found that the Al-10.1Zn-1.2Mg alloy exhibits HE, which is dominated by the hydrogen content in the matrix. However, the fracture behavior is not completely brittle. The SS curves in Fig. 4 and the crack growth behavior in Fig. 6 imply that intergranular and quasi-cleavage crack growth of Al-10.1Zn-1.2Mg alloy accompany plastic deformation. Because the region where the fracture occurs is a crack tip, it is important to quantitatively evaluate the local plastic deformation near crack tips.

In this study, various strain components around the crack tips were analyzed using a 3D strain mapping technique ^[35]. In situ holding-time-tests of Al-10.1Zn-1.2Mg alloy and Al-9.9Zn-2.3Mg-1.4Cu alloy were performed to initiate intergranular cracks and quasi-cleavage cracks, respectively. After the cracks were initiated, 3% strain was applied to analyze the strain distribution ahead of the crack tips. The length of the visualized cracks was approximately 70 μm and 50 μm for the intergranular and quasi-cleavage cracks, respectively. Figs. 11 (a) and (b) show the 3D scatter plots of hydrostatic strain, equivalent strain, and normalized-equivalent strain ahead of crack tips when 3% strain was applied after cracking. Here, normalized-equivalent strain means the equivalent strain, which is divided by the average equivalent strain of the whole material to investigate the strain localization. As described in the methodology, each strain component inside materials was calculated on the basis of the physical displacements of pores and particles. Hydrostatic strain, equivalent strain, and normalized-equivalent strain were plotted at the position corresponding to the center of gravity of the tetrahedron with pores and particles as vertices in Fig. 11. The color of the markers in each plot corresponds to the value of each strain component displayed in the color bar. The coordinates in Figs. 11 (a) and (b) are the absolute coordinates of the 3D region captured by projection-type tomography, and the right side of the figures is located at the specimen surface.

In the intergranular crack shown in Fig. 11 (a), localization of each strain component could not be analyzed in the vicinity of the crack tip or the regions distant from the crack. There were regions where equivalent and normalized-equivalent strains were high, as shown in the quasi-cleavage crack shown in Fig. 11 (b). Note that this localization of strain does not depend on the presence of a crack. As in the previous findings for the Al-9.9Zn-2.3Mg-1.4Cu alloy ^[12], a strain-localized region was first

1 formed, and a crack grew along the localized region. Thus, localization of the strain
2 caused by the crack appeared in neither intergranular nor quasi-cleavage cracks.

3 4 **3.2.2 3D crack morphology**

5 Morphologies of intergranular and quasi-cleavage cracks were visualized in
6 detail by imaging-type tomography. In situ holding-time-tests were performed until the
7 intergranular and the quasi-cleavage crack initiation in Al-10.1Zn-1.2Mg alloy and Al-
8 9.9Zn-2.3Mg-1.4Cu alloy, respectively, and then, their crack tips were visualized in 3D.
9 The spatial resolution of imaging-type tomography is improved fivefold compared with
10 that of projection-type tomography; however, the field of view is limited. Because the
11 entire specimen could not be visualized, the applied strain could not be measured from
12 the tomographic image; however, displacements were applied until the crack initiation in
13 Al-10.1Zn-1.2Mg alloy and Al-9.9Zn-2.3Mg-1.4Cu alloy were 0.08 and 0.19 mm,
14 respectively. The vicinities of the tips of an intergranular crack and a quasi-cleavage crack
15 are shown in Figs. 12 and 13, respectively. In the imaging-type tomography, the field of
16 view is a cylindrical region (i.e., 83 μm in diameter, 59 μm in length) near the crack tip
17 because the region of interest inside the specimen was imaged. Therefore, the
18 semicircular contours in Figs. 12 (a) and 13 (a) are the edges of the field of view, and the
19 crack tip is the zigzag edge located in the upper region.

20 The 3D image and the 2D virtual cross-section shown in Figs. 12 (a-b) and (c-e),
21 respectively, show that the tip of the intergranular crack is sharp and flat compared with
22 the quasi-cleavage crack shown in Fig. 13. Crack deflection was observed near the crack
23 tip in Fig. 12 (d-e); conceivably, however, the crack may have grown through the
24 neighboring grain. The deflection point corresponds to the triple junction point of the
25 grain boundary. The quasi-cleavage crack shown in Fig. 13 exhibits a tortuous

morphology relative to the intergranular crack. The appearance of the crack propagating while repeatedly blunting locally and sharpening was visualized. The crack tip and the intergranular crack are sharp, whereas the quasi-cleavage crack exhibits a rugged surface. Fig. 14 (a) shows the fracture surface of Al-9.9Zn-2.3Mg-1.4Cu alloy observed by SEM, and Fig. 14 (b) shows an image obtained by superimposing the crack of Fig. 13 and the enlarged fracture surface of Fig. 14 (a). The rugged surface morphology of the quasi-cleavage crack shown in Fig. 13 coincides with the quasi-cleavage facet. With regard to the mechanism of the quasi-cleavage facet formation of steel, the nucleation and growth of nanovoids at the intersection of the slip band ahead of the crack tip have been proposed [33]. However, as shown in Fig. 13, no void exceeding 300 nm is observed ahead of the quasi-cleavage crack tip for the Al-9.9Zn-2.3Mg-1.4Cu alloy. Approximately 5-30 nm nanovoids were observed in the strain-localized region in the TEM and the HAADF-STEM images of Al-9.9Zn-2.3Mg-1.4Cu alloy after 5% strain, as previously reported [12]. In addition, the growth behavior of nanovoids of Al-9.9Zn-2.3Mg-1.4Cu alloy has been analyzed using imaging-type tomography [57]. The nanovoids are uniformly distributed in the strain-localized region, and the accumulation and coalescence of nanovoids was not observed during deformation. We inferred that nanovoids mainly act as one of the main hydrogen trap sites in and play a significant role in the repartitioning behavior of hydrogen in the Al-9.9Zn-2.3Mg-1.4Cu alloy. We are currently investigating the origin of quasi-cleavage facets. One of the candidates is the interfacial decohesion of Al/MgZn₂ due to hydrogen accumulation at the Al/MgZn₂ interface. Tsuru *et al.* determined by FPS that the interfacial decohesion of MgZn₂ precipitates initiate when the trapped hydrogen at the Al/MgZn₂ interface reaches 18.9 atomH/nm² [58]. The experimental verification of the above calculation is ongoing and will be published in the future.

The CTOD was directly measured from the 2D virtual cross-section of the 3D crack visualized by imaging-type tomography ^[43]. Figs. 15 (a) and (b) show the distributions of the CTOD for mode I (hereinafter CTOD_I) along the crack front lines of Fig. 12 (a) and Fig. 13 (a), respectively. The average CTOD_I values of the intergranular and quasi-cleavage cracks were 0.14 and 0.23 μm, respectively. In the quasi-cleavage crack, CTOD_I was locally as high as approximately 1 μm in a blunted region, as shown in Fig. 13 (d). The results presented here imply that the HE crack growth of aluminum alloys occurs with small crack driving forces.

4. Discussion

4.1 Hydrogen accumulation and fracture behavior

The mechanism behind the increase in holding time and HE behavior, as observed in Figs. 4 and 6, is considered to be hydrogen accumulation and hydrogen repartitioning in the plastic zone. As mentioned in the introduction, hydrogen localizes to slip lines and grain boundaries by plastic deformation and accumulates over time at room temperature ^[22–26]. Understandably, the diffusion of hydrogen in aluminum is necessary for its accumulation at specific sites. Numerous reports on the diffusion coefficient of hydrogen in aluminum have appeared in the literature ^[37,38,50]. The coefficient derived by Eichenauer and Pebler is considered the most appropriate and is expressed as $D = 2.1 \times 10^{-5} \exp(-Q/RT)$ ^[37,38], where D (m²/s) is the diffusion coefficient of the hydrogen in aluminum and Q is the activation energy of diffusion, equal to 45.63 kJ/mol. The diffusivity at 298 K is 2.1×10^{-13} m²/s from this simple estimation; however, the effect of trapping on the hydrogen diffusion is ignored. Al-Zn-Mg alloys have various hydrogen trap sites such as vacancies and grain boundaries. As mentioned in Section 2.1, the effective diffusivity of overaged Al-6.9%Zn-2.65%Mg-0.06%Cu alloy has been

1 reported to be $1.05 \times 10^{-11} \text{ m}^2/\text{s}$ at 298 K ^[39]. In view of this, we speculate that the
2 aforementioned diffusivity of $2.1 \times 10^{-13} \text{ m}^2/\text{s}$ is conservative. The diffusion distance, l ,
3 in 2.7 ks, which is the holding time for the tomography in situ tensile loading, is estimated
4 to be $(2Dt)^{1/2}$, which is 34 μm at 298 K. Hydrogen is reasonably inferred to accumulate
5 at the crack tip by diffusion with a holding time of 2.7 ks, even at room temperature.
6 Notably, when cracks initiate during holding-time tests, stress-induced diffusion occurs
7 because a hydrostatic stress field appears at the crack tip ^[59]. Conceivably, hydrogen is
8 transported to the vicinity of the crack tip from the region more than 34 μm away during
9 holding, but this scenario is not considered. Again, the estimation of the diffusion in the
10 present work is conservative.

11 We show the crack growth behavior under a fixed displacement in the specimen
12 with a high hydrogen content in Fig. 7. We will discuss the influence of hydrogen on this
13 crack growth behavior. First, to measure the 3D morphology by X-ray tomography, it is
14 necessary to hold the specimen stationary during a tomographic scan. Spontaneously
15 propagating cracks, as in Fig. 7, cannot be observed by tomography, and that is why the
16 2D observation of projection images was performed. Ideally, this crack propagation
17 behavior should be analyzed quantitatively using fracture mechanics parameters.
18 However, there are multiple intergranular cracks shown in Fig. 7, and they are deflected.
19 The 3D morphology is also unclear, and quantitative evaluation is difficult. Therefore, the
20 crack growth behavior is qualitatively discussed below by considering the local stress
21 intensity factor of the crack tip, k . The stress intensity factor, K , which is one of the
22 fracture mechanics parameters that indicates the crack driving force, is expressed as $K =$
23 $F\sigma\sqrt{\pi a}$ using the geometrical factor, F , the stress, σ , and the crack length, a . The
24 mathematical definition of k is the same as K , but lowercase k is used as a local parameter
25 in this discussion. The local crack driving force, k , slightly increases if the crack grows

100 μm under constant stress. However, because the displacement was fixed in the experiment of Fig. 7, the stress dropped markedly due to crack growth, as shown in Fig. 4. Therefore, k at the crack tip shown in Fig. 7 decreased over time, but the crack did not arrest. The crack growth behavior indicated by the red arrow cannot be interpreted by the fracture mechanics parameters alone, suggesting that the accumulation of hydrogen reduced the local crack growth resistance at the grain boundary and that crack growth under constant displacement occurred. On the other hand, the intergranular crack indicated by black arrows did not grow. The difference in the behavior of intergranular crack growth can be attributed to the influence of the grain boundary character. Hirayama *et al.* investigated the relation between the intergranular cracking and the crystallographic properties of an Al-10.1-Zn-1.2Mg alloy of the same composition as used in the present study [60]. According to their study, intergranular cracks tended to initiate at the grain boundary, where both the relative misorientation and geometric angle to the tensile axis are large. That is, fracture easily occurs at the grain boundary where the local stress of mode I acts and traps hydrogen due to the high relative misorientation. Further crystallographic analysis is ongoing and will be published elsewhere [60].

An FPS that concluded that hydrogen segregation occurs at the grain boundary with a relatively high grain-boundary energy was reported for iron and aluminum [29]. Furthermore, a recent FPS revealed that as the trapped hydrogen in the grain boundary reaches 22 H atoms/nm², the grain-boundary cohesive energy decreases from 1.4 to 0.2 J/m², causing intergranular fracture in the aluminum [45]. In the results in Fig. 7, it is conceivable that the grain boundaries indicated by the red arrows tend to trap hydrogen and locally exhibit high hydrogen contents at the intergranular crack tips. Therefore, crack growth occurred even under fixed displacement. G. Bond *et al.* investigated crack growth under fixed displacements by using TEM specimens of A7075 alloy and pure aluminum

(99.999%) in a hydrogen environment. It was reported that crack growth occurred immediately when 3-11 kPa of hydrogen gas was introduced into the TEM sample chamber. The results in Fig. 7 and those of G. Bond *et al.* seem to be analogous, but the crack growth conditions are completely different in terms of the specimen size and hydrogen trap state. For the crack growth in Fig. 7, hydrogen trapped inside the material was the driving force, and growth was not governed by the gas environment outside the specimen. Furthermore, the crack growth was observed by means of the foil specimens, and not in the bulk. Crack growth behavior tends to be influenced by the geometry, the various internal stress and strain states, and the surface conditions of the test piece. Therefore, the behavior of the crack growth observed in the foil is not necessarily the same as that in the bulk. Fig. 7 is the experimental visualization of crack growth under fixed displacement by hydrogen accumulation using a bulk specimen.

4.2 Local deformation at the intergranular and quasi-cleavage crack tip

No strain components concentrated at the vicinity of the crack tip were observed in either the intergranular crack or the quasi-cleavage crack in the strain map shown in Fig. 11. This strain map is based on the microstructural feature tracking technique, where the changes in the displacement of pores and particles around the crack are tracked ^[35]. The nearest-neighbor distance of each pore and particle is approximately 18 μm in the materials used in this study. Therefore, the strain mapping shown in Fig. 11 cannot analyze a strain field smaller than 18 μm . The CTODs measured by imaging-type tomography were as small as 1 μm at the maximum, as shown in Fig. 15. The process zone of the crack tip is reasonably inferred to be smaller than 2 μm when the size of process zone is estimated as twice the CTOD. Thus, due to the sharp crack tip without blunting and the small process zone, the plastic region caused by the crack may be smaller

1 than 18 μm . Consequently, strain mapping based on microstructural feature tracking
 2 apparently could not assess the local displacement field at the crack tip.

3 The stress and strain field at the crack tip follows the Hutchinson-Rice-
 4 Rosengren (HRR) singularity in the stationary crack and Rice-Drugan-Sham (RDS)
 5 singularity in the growing crack [61–63]. The HRR solution is derived by elastoplastic
 6 analysis of the crack tip region based on total strain theory and is expressed as follows:

$$\delta = 2\alpha'\varepsilon_0 \left(\frac{J}{\alpha'\varepsilon_0\sigma_0 I_n} \right)^{n/(n+1)} r^{1/(n+1)} \tilde{u}(\pi) \quad (5)$$

7 where δ is the crack opening displacement (COD), ε_0 , n , and a_0 are the constants in the
 8 constitutive equation for a power-law hardening material, J is the J -integral, σ_0 is the flow
 9 stress, r is the distance behind a crack tip, I_n is an integral constant, and $\tilde{u}(\pi)$ is the value
 10 of a dimensionless normalization function at $\theta = \pi$. The J -integral was calculated based
 11 on equation (6) from the CTOD, δ , experimentally measured from the virtual cross-
 12 section of the cracks (slices A, B, and C in Figs. 12 and 13).

$$J = \frac{\sigma_0 \delta}{d_n} \quad (6)$$

13 where d_n is a dimensionless constant. The stress and strain in the crack tip region have a
 14 singularity of $r^{1/(n+1)}$ in this HRR solution. The RDS solution is expressed as follows:

$$\frac{E\delta}{\sigma_0 r} = \alpha T_R + \beta \ln \left(\frac{e R_p}{r} \right) \quad (7)$$

15 where E is Young's modulus, T_R is the material tearing modulus, e is Napier's constant,
 16 and R_p is the plastic zone diameter. T_R was calculated as follows^[64]:

$$T_R = \frac{\Omega}{3\alpha} - \frac{\beta}{\alpha} \ln \left(\frac{e\lambda\Omega}{3\alpha} \right) \quad (8)$$

with

$$\Omega = \frac{E\varepsilon_f}{\sigma_0}$$

17 where α , β and λ are constants and were assumed to be 0.65, 5.08, and 0.2 respectively
 18 ^[64]. The calculated T_R values were 12.5 and 8.7 for intergranular cracks and quasi-

cleavage cracks, respectively. According to Chan *et al.*, these calculated T_R values are classified as being within the "brittle fracture regime" ^[64]. The RDS solution shown in Eq. (7) is derived from the exact solution based on strain increment theory, and it shows a weak singularity proportional to $\ln(1/r)$. For the purpose of experimental evaluation of the above singularities, it is extremely challenging to measure the stress and strain in the local region of the crack tip inside the material. However, the singularity of the crack tip region can be evaluated by measuring the COD along the crack surface and comparing the value of δ derived from the HRR and RDS solutions. In addition, Toda *et al.* analyzed the transition of the singularity from HRR to RDS due to crack growth in three dimensions by using the COD profile directly measured by tomographic observation ^[61].

In this study, the displacement field (i.e., local deformation region) of the intergranular and quasi-cleavage crack tip region was analyzed in terms of the abovementioned singularities. The HRR and RDS singularities based on Eqs. (5) and (7) are applicable when the stress/strain field at the crack tip is a K -dominated or J -dominated region. The analysis based on Eqs. 5 and 7 cannot be applied if the stress/strain field at the crack-tip exhibits large-scale yielding. As shown in Figs. 11 to 15, the microcracks observed in this study were mostly 3D microcracks embedded in an elastic-plastic field. If large-scale yielding occurs at the crack tip, the measured CTOD corresponding to the size of the process zone at the crack tip would be large. As shown in Fig. 15, the CTOD of intergranular cracks and quasi-cleavage cracks was small, at most approximately 1 μm . At the tip of such a crack, it is unlikely that large-scale yielding has occurred. Thus, in the following discussion, it was rationally assumed that their crack tips were K -dominated or J -dominated regions.

The COD profiles obtained from Figs. 12 (c-e) and 13 (c-e) are shown in Fig. 16 (a) and (b), respectively. The kink in the COD profile, which is presumed to be due to

propagation of the adjacent grain boundary, was observed in the intergranular crack. Relative to an intergranular crack, the COD profiles of a quasi-cleavage crack vary frequently, which corresponds to facet structure on the fracture surface. Fig. 17 shows normalized COD profiles that were experimentally obtained from COD profiles in Fig. 16 and normalized COD profiles generated by the HRR and RDS solutions. Here, to compare the two solutions expressed as Eqs. (5) and (7), the distance from the crack tip, r , and the COD, δ , were normalized using the J -integral, flow stress, and Young's modulus. As a result, the stress and strain fields in both crack tip regions do not follow the HRR solution; they follow the RDS solution only in the quite limited range of the crack tip. The regions following the RDS solution in the intergranular crack and the quasi-cleavage crack were the regions where the normalized distance is equal to 0.2-0.3 (i.e., 15-20 μm from the crack tip) and 0.2 or less (i.e., 0.6-5 μm from crack tip), respectively. The RDS solution means that elastic unloading occurs above and below the crack surface when a sharp crack propagates into the plastic zone and that the stress and strain singularity in the crack tip region weaken in proportion to $\ln(1/r)$. The analysis shown in Fig. 17 suggests that strain has already been localized prior to crack initiation and that sharp cracks grow toward the strain-localized region. This important finding is consistent with the strain mapping ahead of the quasi-cleavage crack shown in Fig. 11 (b). Since the region following the RDS solution is within 5 μm of the crack tip, it can be concluded that the localization of the strain at the crack tip does not appear in the strain mapping of Fig. 11 (b). The region following the RDS solution of the intergranular crack is slightly larger than the quasi-cleavage crack and lies 15 to 20 μm from the crack tip. This result reveals the effect of heterogeneous deformation near the grain boundary, as the Al-10.1Zn-1.2 Mg alloy used had a coarse grain of approximately 330 μm , which imparts a loose plastic constraint from adjacent grains. In addition, the alloy has a coarse precipitate

and a precipitate-free zone on the grain boundaries ^[65]. Thus, in both intergranular and quasi-cleavage cracks, the local deformation, which follows the RDS solution, was quantitatively revealed in the region of 20 μm or less from the crack tip. Local plastic deformation occurs at the crack tip, and its plastic zone size is significantly more limited than that of a typical ductile crack.

5. Conclusion

The HE behavior of Al-10.1Zn-1.2 Mg alloy and Al-9.9Zn-2.3Mg-1.4Cu alloy were analyzed by means of in situ observation using synchrotron projection-type and imaging-type tomography. Similar to the already reported behavior of the Al-9.9Zn-2.3Mg-1.4Cu alloy, HE appeared significant when the holding time of the in situ test increased, and the area fraction of intergranular and quasi-cleavage fracture increased. However, the fracture was not completely brittle, and even the intergranular crack that grew on one grain boundary did not grow in a single step but instead grew progressively by tensile loading. When trace iron was added to the Al-10.1Zn-1.2Mg alloy, the area fraction of intergranular and quasi-cleavage fracture decreased, and HE was suppressed even if the hydrogen content of the material was approximately the same. Based on the TDA results, it was concluded that the hydrogen content in trap sites such as dislocation and grain boundaries decreased relatively and that HE was suppressed because the second-phase particles trapped hydrogen. In addition, it was found that these HE behaviors are dominated by hydrogen in the matrix and that pores filled with molecular hydrogen do not directly affect HE. The contribution of the plastic deformation to intergranular and quasi-cleavage crack growth has been examined in this study. 3D strain mapping could not visualize their strain fields because their size is smaller than 18 μm , and the RDS solution also suggests that the local deformation regions of the crack tip

were quite limited. Furthermore, intergranular cracks grown at fixed displacement were visualized in the specimen with extremely increased hydrogen content, and the crack driving force was attributed to hydrogen accumulation.

Acknowledgments

This research was supported by Japan Science and Technology Agency (JST) under Collaborative Research Based on Industrial Demand "Heterogeneous Structure Control: Towards Innovative Development of Metallic Structural Materials". This research was supported in part by a grant from the Light Metal Educational Foundation, Japan. The synchrotron radiation experiments were performed at the BL20XU and the BL37XU of SPring-8 with the approval of Japan Synchrotron Radiation Research Institute (JASRI) (Proposal Nos. 2016A1199, 2016B1081, 2016A0076, 2016B0076). The authors also thank Dr. Takahiro Shikama in KOBELCO and Japan Aluminium Association for providing and preparing materials used.

Reference

- 1 R.G. Song, W. Dietzel, B.J. Zhang, W.J. Liu, M.K. Tseng, and A. Atrens: *Acta Mater.*, 2004, vol. 52, pp. 4727–43.
- 2 M.S. Bhuiyan, H. Toda, Z. Peng, S. Hang, K. Horikawa, K. Uesugi, A. Takeuchi, N. Sakaguchi, and Y. Watanabe: *Mater. Sci. Eng. A*, 2016, vol. 655, pp. 221–8.
- 3 M. Hirano, K. Kobayashi, and H. Tonda: *J. Soc. Mater. Sci. Japan*, 2000, vol. 49, pp. 86–91.
- 4 R. Braun: *Materwiss. Werksttech.*, 2007, vol. 38, pp. 674–89.
- 5 D. Najjar, T. Magnin, and T.J. Warner: *Influence of Critical Surface Defects and Localized Competition between Anodic Dissolution and Hydrogen Effects during Stress Corrosion Cracking of a 7050 Aluminium Alloy*, vol. 238, 1997.
- 6 S. Osaki and S. Haruyama: *J. Japan Inst. Light Met.*, 2013, vol. 63, pp. 57–64.
- 7 S. Osaki, J. Ikeda, K. Kinoshita, Y. Sasaki, and A.M. Si: *J. Japan Inst. Light Met.*,

2006, vol. 56, pp. 721–7.

8 S. Kuramoto, J. Okahana, and M. Kanno: *Mater. Trans.*, 2001, 42, vol. 42.

9 M.S. Bhuiyan, Y. Tada, H. Toda, S. Hang, K. Uesugi, A. Takeuchi, N. Sakaguchi,
and Y. Watanabe: *Int. J. Fract.*, 2016, vol. 200, pp. 13–29.

10 M. Wang, E. Akiyama, and K. Tsuzaki: *Mater. Sci. Eng. A*, 2005, vol. 398, pp. 37–
46.

11 K. Takai and R. Watanuki: *ISIJ Int.*, 2003, vol. 43, pp. 520–6.

12 H. Su, H. Toda, R. Masunaga, K. Shimizu, H. Gao, K. Sasaki, M.S. Bhuiyan, K.
Uesugi, A. Takeuchi, and Y. Watanabe: *Acta Mater.*, 2018, vol. 159, pp. 332–43.

13 R.A. Oriani: *Acta Metall.*, 1970, vol. 18, pp. 147–57.

14 H. Toda, T. Hidaka, M. Kobayashi, K. Uesugi, A. Takeuchi, and K. Horikawa:
Acta Mater., 2009, vol. 57, pp. 2277–90.

15 M. Felberbaum and M. Rappaz: *Acta Mater.*, 2011, vol. 59, pp. 6849–60.

16 P.D. Lee and J.D. Hunt: *Acta Mater.*, 2001, vol. 49, pp. 1383–98.

17 H. Toda, H. Oogo, K. Horikawa, K. Uesugi, A. Takeuchi, Y. Suzuki, M. Nakazawa,
Y. Aoki, and M. Kobayashi: *Metall. Mater. Trans. A Phys. Metall. Mater. Sci.*,
2014, vol. 45, pp. 765–76.

18 W.Y. Choo and J.Y. Lee: *Metall. Trans. A*, 1982, vol. 13, pp. 135–40.

19 P. Chao and R.A. Karnesky: *Mater. Sci. Eng. A*, 2016, vol. 658, pp. 422–8.

20 S.W. Smith and J.R. Scully: *Metall. Mater. Trans. A Phys. Metall. Mater. Sci.*,
2000, vol. 31, pp. 179–93.

21 T. Enomoto, R. Matsumoto, S. Taketomi, and N. Miyazaki: *Zair. Soc. Mater. Sci.*
Japan, 2010, vol. 59, pp. 596–603.

22 K. Horikawa and K. Yoshida: *Mater. Trans.*, 2004, vol. 45, pp. 315–8.

23 K. Horikawa, H. Okada, H. Kobayashi, and W. Urushihara: *Mater. Trans.*, 2009,
vol. 50, pp. 759–64.

24 H. Matsunaga, T. Usuda, K. Yanase, and M. Endo: *Metall. Mater. Trans. A Phys.*
Metall. Mater. Sci., 2014, vol. 45, pp. 1315–26.

25 T. Izumi and G. Itoh: *Mater. Sci. Forum*, 2007, vol. 539–543, pp. 475–80.

26 K. Ichitani, M. Kanno, and S. Kuramoto: *ISIJ Int.*, 2003, vol. 43, pp. 496–504.

27 I.M. Robertson, P. Sofronis, A. Nagao, M.L. Martin, S. Wang, D.W. Gross, and
K.E. Nygren: *Metall. Mater. Trans. A Phys. Metall. Mater. Sci.*, 2015, vol. 46, pp.
2323–41.

28 M. Yamaguchi, K.I. Ebihara, M. Itakura, T. Kadoyoshi, T. Suzudo, and H.

Kaburaki: in *Metallurgical and Materials Transactions A: Physical Metallurgy and Materials Science*, vol. 42, Springer US, 2011, pp. 330–9.

29 M. Yamaguchi, J. Kameda, K.-I. Ebihara, M. Itakura, and H. Kaburaki: *Philos. Mag.*, 2012, vol. 92, pp. 1349–68.

30 Y. Mine, T. Tsumagari, and Z. Horita: *Scr. Mater.*, 2010, vol. 63, pp. 552–5.

31 M. Nagumo: *Mater. Sci. Technol.*, 2004, vol. 20, pp. 940–50.

32 T. Neeraj, R. Srinivasan, and J. Li: *Acta Mater.*, 2012, vol. 60, pp. 5160–71.

33 M.L. Martin, J. a. Fenske, G.S. Liu, P. Sofronis, and I.M. Robertson: *Acta Mater.*, 2011, vol. 59, pp. 1601–6.

34 H. Toda, K. Shimizu, K. Uesugi, Y. Suzuki, and M. Kobayashi: *Mater. Trans.*, 2010, vol. 51, pp. 2045–8.

35 M. Kobayashi, H. Toda, Y. Kawai, T. Ohgaki, K. Uesugi, D.S. Wilkinson, T. Kobayashi, Y. Aoki, and M. Nakazawa: *Acta Mater.*, 2008, vol. 56, pp. 2167–81.

36 H. Su, T. Yoshimura, H. Toda, M.S. Bhuiyan, K. Uesugi, A. Takeuchi, N. Sakaguchi, and Y. Watanabe: *Metall. Mater. Trans. A Phys. Metall. Mater. Sci.*, 2016, vol. 47, pp. 6077–89.

37 T. Ishikawa and R.B. McLellan: *Acta Metall.*, 1986, vol. 34, pp. 1091–5.

38 Japan Institute of Light Metals, ed.: *Structures and Properties of Aluminum*, Tokyo, 1991.

39 J.R. Scully, G.A. Young, and S.W. Smith: in *Gaseous Hydrogen Embrittlement of Materials in Energy Technologies: The Problem, its Characterisation and Effects on Particular Alloy Classes*, Woodhead Publishing, 2012, pp. 707–68.

40 M. Yamaguchi, T. Tsuru, K. Ebihara, and M. Itakura: *J. Japan Inst. Light Met.*, 2018, vol. 68, pp. 588–95.

41 A. Takeuchi, K. Uesugi, Y. Suzuki, S. Itabashi, and M. Oda: *J. Synchrotron Rad.*, 2017, vol. 24, pp. 586–94.

42 A. Takeuchi, K. Uesugi, and Y. Suzuki: *J. Phys. Conf. Ser.*, 2017, vol. 849, p. 012055.

43 H. Toda, S. Yamamoto, M. Kobayashi, K. Uesugi, and H. Zhang: *Acta Mater.*, 2008, vol. 56, pp. 6027–39.

44 W.E. Lorensen, H.E. Cline, W.E. Lorensen, and H.E. Cline: in *Proceedings of the 14th annual conference on Computer graphics and interactive techniques - SIGGRAPH '87*, vol. 21, ACM Press, New York, New York, USA, 1987, pp. 163–9.

- 1 45 M. Yamaguchi, K.-I. Ebihara, M. Itakura, T. Tsuru, K. Matsuda, and H. Toda:
2 *Comput. Mater. Sci.*, 2019, vol. 156, pp. 368–75.
- 3 46 H. Toda, P.C.C. Qu, S. Ito, K. Shimizu, K. Uesugi, A. Takeuchi, Y. Suzuki, and
4 M. Kobayashi: *Int. J. Cast Met. Res.*, 2014, vol. 27, pp. 369–77.
- 5 47 P.N. Anyalebechi: *Cast Met.*, 2016, vol. 3, pp. 182–201.
- 6 48 M.S.I.T. MSIT®: in *Light Metal Systems. Part 3*, Springer-Verlag,
7 Berlin/Heidelberg, pp. 1–21.
- 8 49 T. Izumi and G. Itoh: *Mater. Trans.*, 2011, vol. 52, pp. 130–4.
- 9 50 G.A. Young and J.R. Scully: *Acta Mater.*, 1998, vol. 46, pp. 6337–49.
- 10 51 H. Toda, Z.A. Bin Shamsudin, K. Shimizu, K. Uesugi, A. Takeuchi, Y. Suzuki, M.
11 Nakazawa, Y. Aoki, and M. Kobayashi: *Acta Mater.*, 2013, vol. 61, pp. 2403–13.
- 12 52 Y.S. Chen, D. Haley, S.S.A. Gerstl, A.J. London, F. Sweeney, R.A. Wepf, W.M.
13 Rainforth, P.A.J. Bagot, and M.P. Moody: *Science (80-.)*, 2017, vol. 355, pp.
14 1196–9.
- 15 53 J. Takahashi, K. Kawakami, and Y. Kobayashi: *Acta Mater.*, 2018, vol. 153, pp.
16 193–204.
- 17 54 H. Saitoh, Y. Iijima, and K. Hirano: *J. Mater. Sci.*, 1994, vol. 29, pp. 5739–44.
- 18 55 F.G. Wei, T. Hara, and K. Tsuzaki: *Metall. Mater. Trans. B*, 2004, vol. 35, pp.
19 587–97.
- 20 56 D. Nguyen, A.W. Thompson, and I.M. Bernstein: *Acta Metall.*, 1987, vol. 35, pp.
21 2417–25.
- 22 57 H. Gao, H. Su, K. Shimizu, C. Kadokawa, H. Toda, Y. Terada, K. Uesugi, and A.
23 Takeuchi: *Mater. Trans.*, 2018, vol. 59, pp. 1532–5.
- 24 58 T. Tsuru, M. Yamaguchi, H. Toda, and K. Shimizu: unpublished work.
- 25 59 P. Sofronis and R.M. McMeeking: *J. Mech. Phys. Solids*, 1989, vol. 37, pp. 317–
26 50.
- 27 60 K. Hirayama, Y. Sek, T. Suzuki, H. Toda, K. Uesugi, A. Takeuchi, and W. Ludwig:
28 in preparation.
- 29 61 H. Toda, E. Maire, S. Yamauchi, H. Tsuruta, T. Hiramatsu, and M. Kobayashi:
30 *Acta Mater.*, 2011, vol. 59, pp. 1995–2008.
- 31 62 J.R. RICE, W.J. DRUGAN, and T.L. SHAM: *Astm Stp 700*, 1980, pp. 189–221.
- 32 63 K.S. Chan: *Metall. Trans. A*, 1990, vol. 21, pp. 81–6.
- 33 64 K.S. Chan: *Acta Metall.*, 1989, vol. 37, pp. 1217–26.
- 34 65 T. Ogura, T. Otani, A. Hirose, and T. Sato: *Mater. Sci. Eng. A*, 2013, vol. 580, pp.

1 288–93.

2

3

4

Captions

Fig. 1. Schematic of the process used to prepare four different Al-10.1Zn-1.2Mg alloys with different volume fractions of pores, V_f , and different hydrogen contents, C_H , as shown in (a-d). Thermal cycle (TC) in air was used to increase V_f , and TC in vacuum was used to decrease C_H .

Fig. 2. Schematic of the (a) projection-type and (b) imaging-type tomography configurations performed on BL20XU and BL37XU of SPring-8, respectively.

Fig. 3. Virtual cross-sections of a 3D tomographic image at different volume fractions of pores, V_f , and hydrogen content, C_H , in Al-10.1Zn-1.2Mg alloys. Each image was captured in the unloaded state. The preparation processes in (a-d) correspond to Fig. 1 (a-d), respectively.

Fig. 4. Nominal stress-strain curves obtained by in situ tensile tests. The curves in Fig. 4 (a) were obtained from a low V_f and high C_H alloy and a low V_f and low C_H alloy shown in Fig. 3 (a) and (b), respectively, at the holding time of 0.9 ks. Fig. 4 (b) was obtained from low V_f and high C_H alloys shown in Fig. 3 (a) at the different holding times of 0.3, 0.9 and 2.7 ks.

Fig. 5. Fracture surfaces of the (a) low V_f and high C_H alloy and (b) low V_f and low C_H alloy shown in Fig. 3 (a) and (b) after in situ tensile tests, respectively, with a holding time of 0.9 ks.

Fig. 6. Fracture surface of tensile specimens at different holding times. In Fig. 6 (a-c), Intergranular and quasi-cleavage fractured regions are indicated in red and blue, respectively. In Fig. 6 (d-f), cracks visualized by projection-type tomography at each strain are superimposed as yellow, green, and blue. Nominal strains are also indicated when each crack was visualized by projection-type tomography.

Fig. 7. 2D projection images of specimen (a) before loading at (b) 0, (c) 65, and (d) 130 s after holding the displacement. The crack indicated by the black arrow was arrested, and the crack indicated by the red arrow grew even though the displacement was constant.

Fig. 8. Tomographic slices and fracture surfaces of Al-10.1Zn-1.2Mg alloys (a and c) without and (b and d) with trace iron, respectively. The fracture surface without trace iron corresponds to Fig. 6 (b). The intergranular and quasi-cleavage fractured regions are shown in red and blue, respectively.

Fig. 9. Thermal desorption curves of the Al-Zn-Mg alloy and Al-Zn-Mg alloy with trace iron. Fig. 9 (a) is an overall view of thermal desorption curves. Fig. 9 (b) is an enlarged view of Fig. 9 (a) in the temperature range 550-800 K.

Fig. 10. Contour map of the area fraction, A_f , of (a) ductile, (b) quasi-cleavage, and (c) intergranular fractured regions on the fracture surface. The hydrogen content in the pores was analyzed by 3D tomographic images; the hydrogen content in the matrix, C_{mat} , is equal to the total hydrogen content minus the hydrogen content in the pores.

Fig. 11. 3D strain mapping of hydrostatic, equivalent, and normalized-equivalent strains. Each strain component around a crack tip corresponding to (a) intergranular and (b) quasi-cleavage cracks is represented. The position of each marker is the position of the center of gravity of a tetrahedron composed of pores and particles; the color corresponds to the value of each strain component indicated by the color map.

Fig. 12. 3D tomographic images of an intergranular crack ((a) top and (b) side views). In Fig. 12 (c~e), the 2D virtual cross-sections of A, B, and C correspond to the dashed line in the top view.

Fig. 13. 3D tomographic images of a quasi-cleavage crack ((a) top and (b) side views). In Fig. 13 (c~e), the 2D virtual cross-sections of A, B, and C correspond to the dashed line in the top view.

Fig. 14. Fracture surface of Al-9.9Zn-2.3Mg-1.4Cu alloy observed by SEM. Fig. 14 (a) is the overall view of fracture surface and (b) is enlarged view of rectangular region in (a). In Fig. 14 (b), the quasi-cleavage crack captured by imaging-type tomography is superimposed.

Fig. 15. Variations in local crack driving forces, CTOD_I , along the (a) intergranular and (b) quasi-cleavage crack front line. CTOD_I is directly analyzed from the crack tip morphology.

Fig. 16. Variation of the crack opening displacement from the crack tip, which was obtained from slices A, B, and C in Figs. 12 and 13. Fig. 16 (a) and (b) correspond to intergranular and quasi-cleavage cracks, respectively.

Fig. 17. Normalized crack opening profile as a function of normalized distance for the (a) intergranular and (b) quasi-cleavage crack tips.

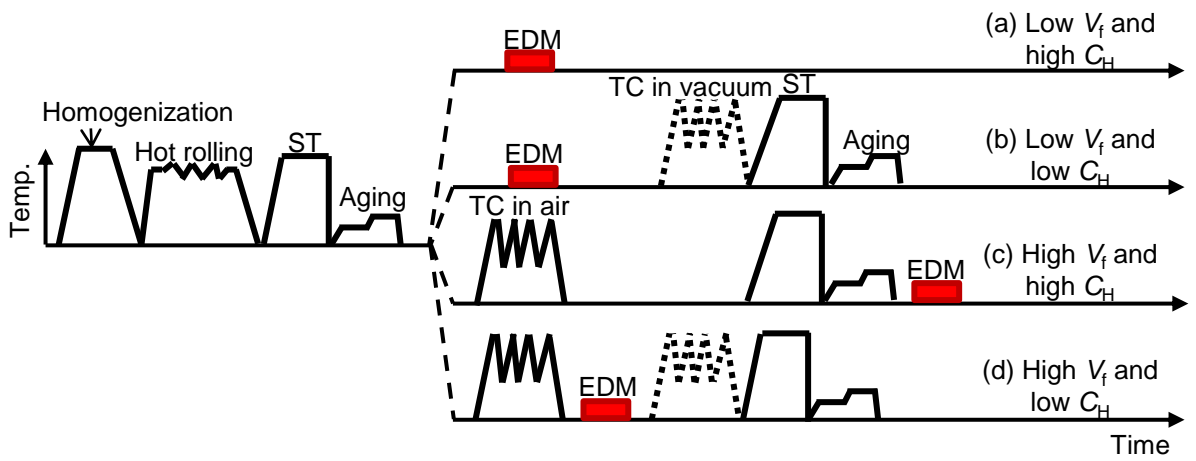


Fig. 1. Schematic of the process used to prepare four different Al-10.1Zn-1.2Mg alloys with different volume fractions of pores, V_f , and different hydrogen contents, C_H , as shown in (a-d). Thermal cycle (TC) in air was used to increase V_f and TC in vacuum was used to decrease C_H .

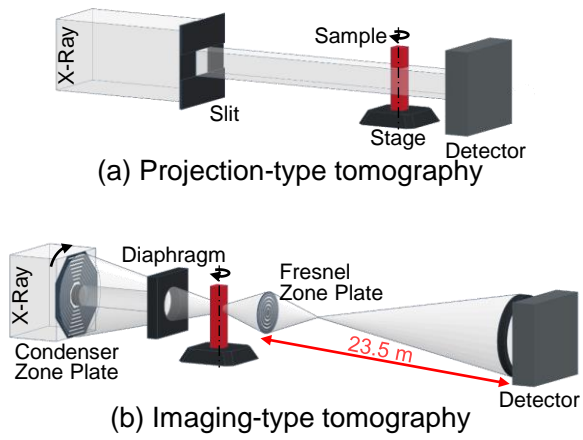


Fig. 2. Schematic of the (a) projection-type and (b) imaging-type tomography configurations performed on BL20XU and BL37XU of SPring-8, respectively.

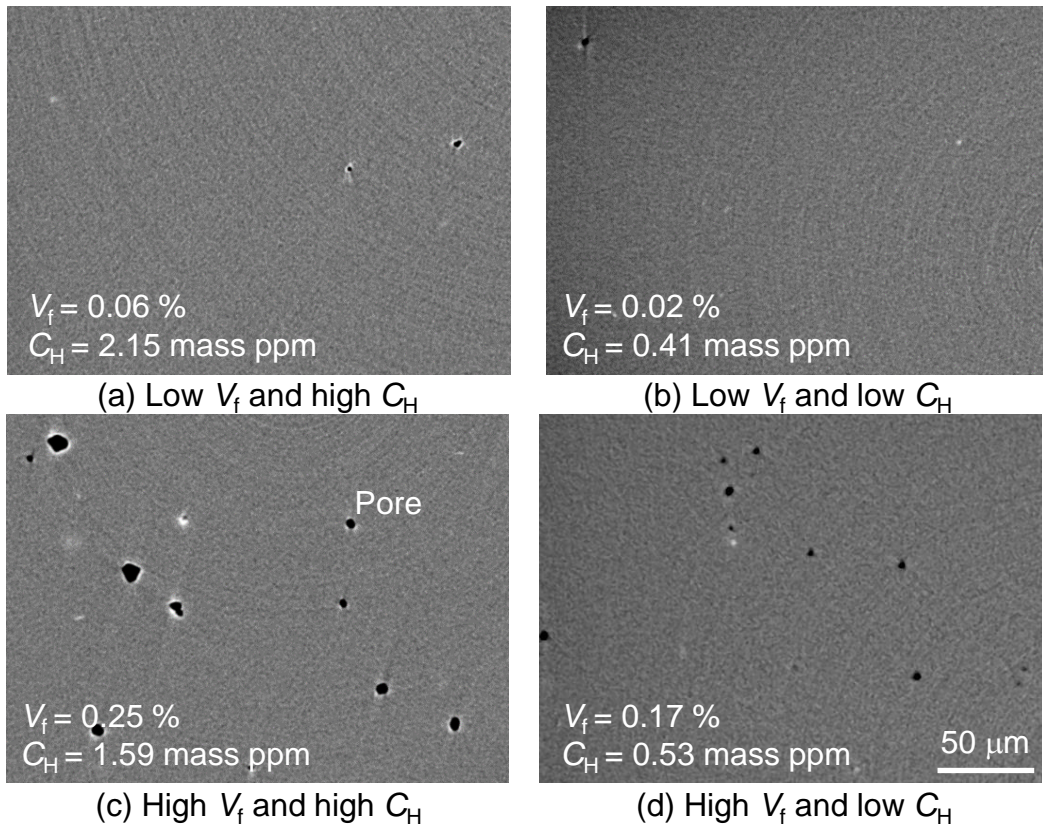


Fig. 3. Virtual cross-sections of a 3D tomographic image at different volume fractions of pores, V_f , and hydrogen content, C_H , in Al-10.1Zn-1.2Mg alloys. Each image was captured in the unloaded state. The preparation processes in (a-d) correspond to Fig. 1 (a-d), respectively.



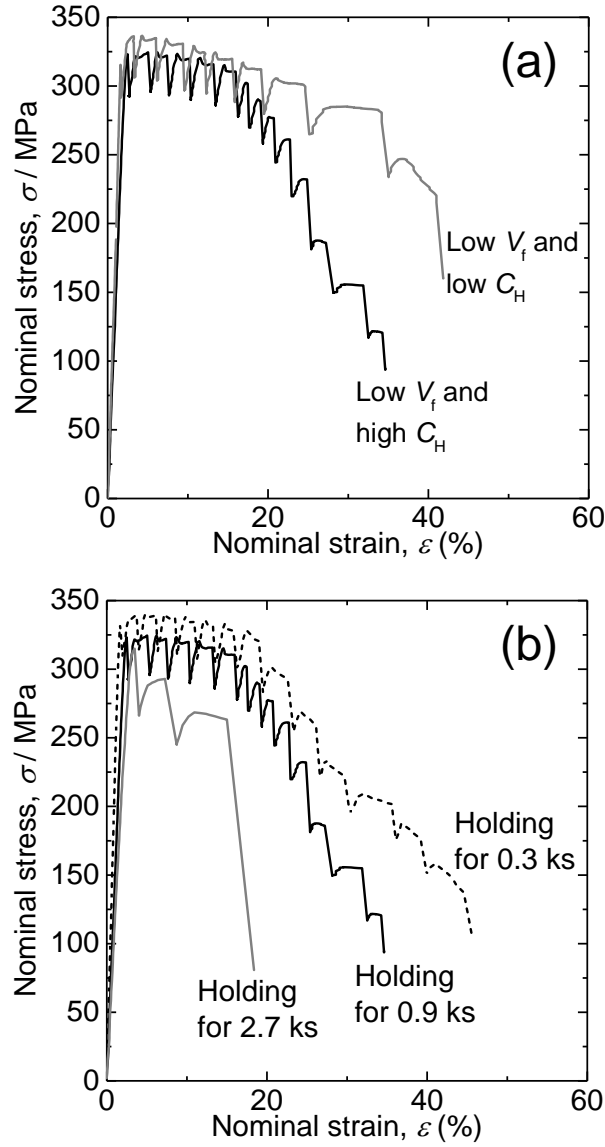


Fig. 4. Nominal stress-strain curves obtained by in situ tensile tests. The curves in Fig. 4 (a) were obtained from a low V_f and high C_H alloy and a low V_f and low C_H alloy shown in Fig. 3 (a) and (b), respectively, at the holding time of 0.9 ks. Fig. 4 (b) was obtained from low V_f and high C_H alloys shown in Fig. 3 (a) at the different holding times of 0.3, 0.9 and 2.7 ks.

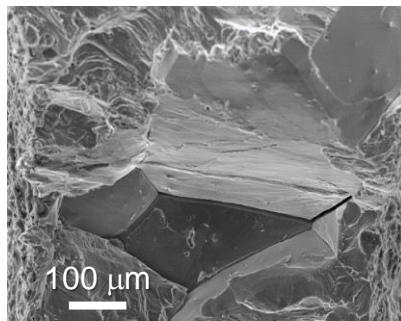

(a) Low V_f and high C_H

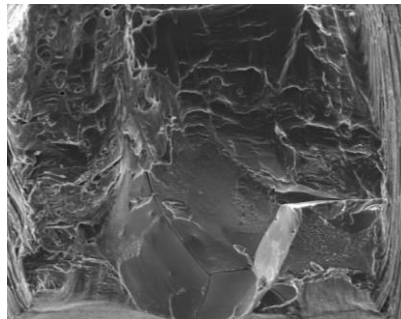

(b) Low V_f and low C_H

Fig. 5. Fracture surfaces of the (a) low V_f and high C_H alloy and (b) low V_f and low C_H alloy shown in Fig. 3 (a) and (b) after in situ tensile tests, respectively, with a holding time of 0.9 ks.

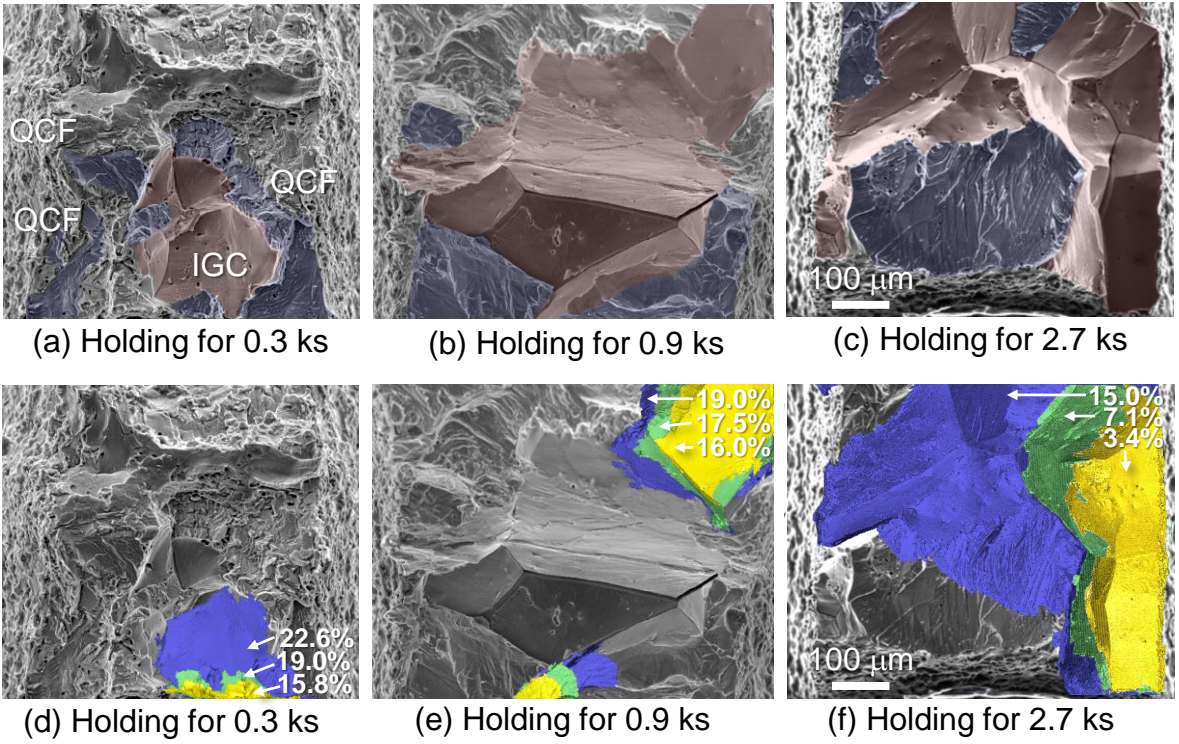


Fig. 6. Fracture surface of tensile specimens at different holding times. In Fig. 6 (a-c), Intergranular and quasi-cleavage fractured regions are indicated in red and blue, respectively. In Fig. 6 (d-f), cracks visualized by projection-type tomography at each strain are superimposed as yellow, green, and blue. Nominal strains are also indicated when each crack was visualized by projection-type tomography.

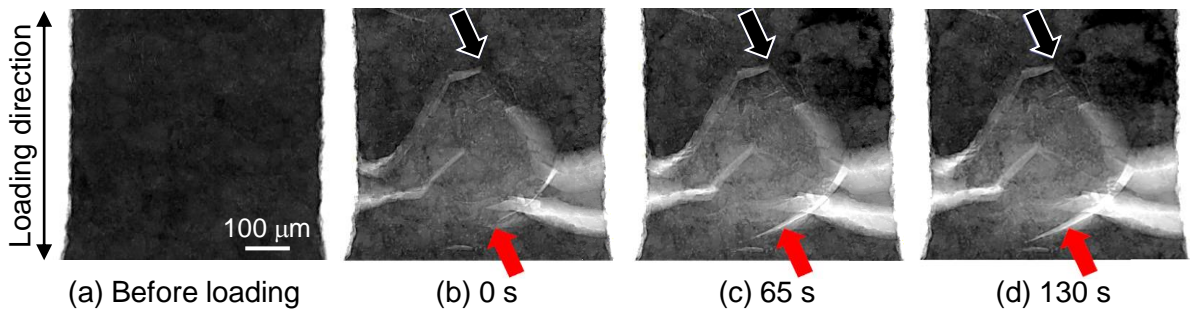


Fig. 7. 2D projection images of specimen (a) before loading at (b) 0, (c) 65, and (d) 130 s after holding the displacement. The crack indicated by the black arrow was arrested, and the crack indicated by the red arrow grew even though the displacement was constant.



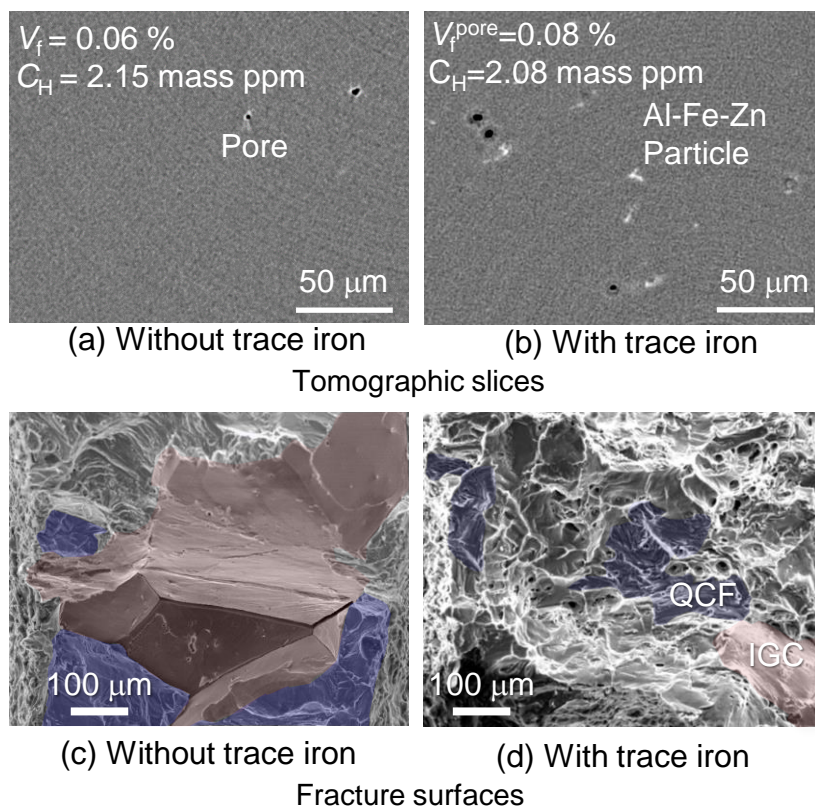


Fig. 8. Tomographic slices and fracture surfaces of Al-10.1Zn-1.2Mg alloys (a and c) without and (b and d) with trace iron, respectively. The fracture surface without trace iron corresponds to Fig. 6 (b). The intergranular and quasi-cleavage fractured regions are shown in red and blue, respectively.

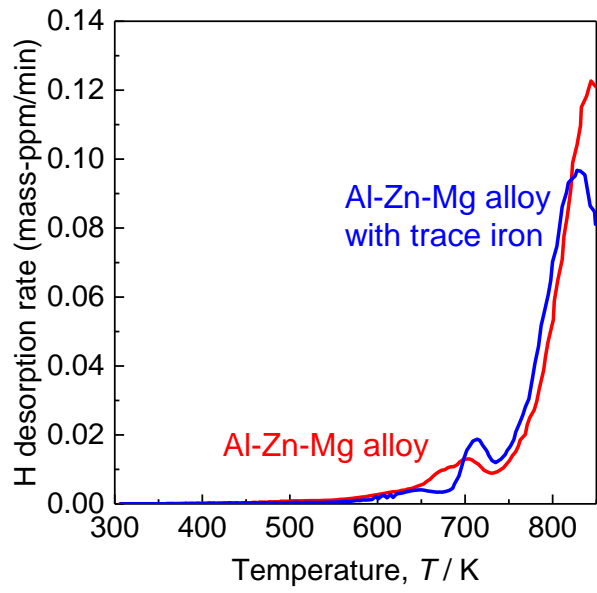

(a) Overall view of TDA curves

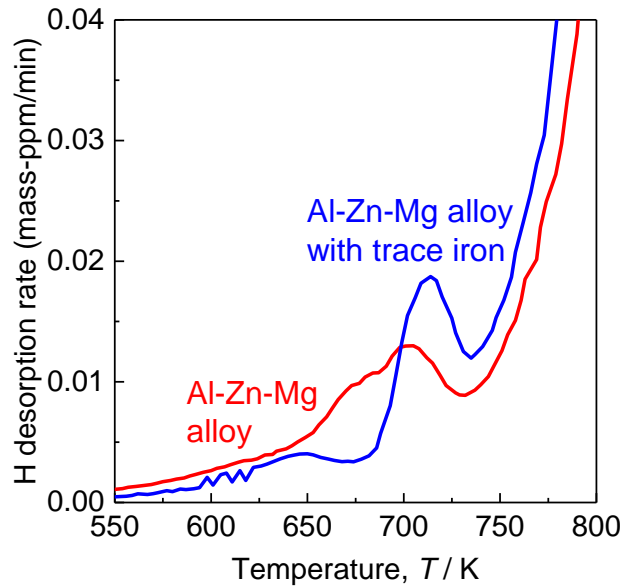

(b) Enlarged view of (a)

Fig. 9. Thermal desorption curves of the Al-Zn-Mg alloy and Al-Zn-Mg alloy with trace iron. Fig. 9 (a) is an overall view of thermal desorption curves. Fig. 9 (b) is an enlarged view of Fig. 9 (a) in the temperature range 550-800 K.

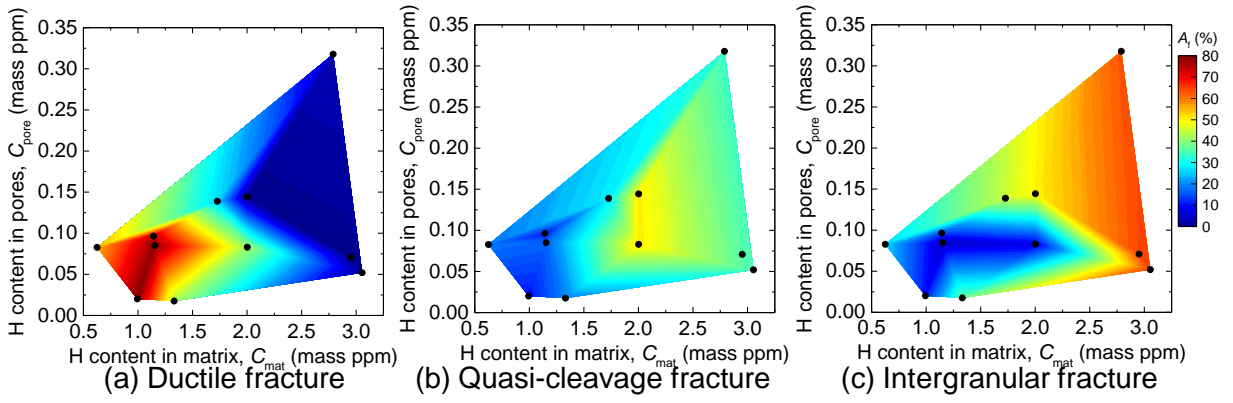


Fig. 10. Contour map of the area fraction, A_f , of (a) ductile, (b) quasi-cleavage, and (c) intergranular fractured regions on the fracture surface. The hydrogen content in the pores was analyzed by 3D tomographic images; the hydrogen content in the matrix, C_{mat} , is equal to the total hydrogen content minus the hydrogen content in the pores.

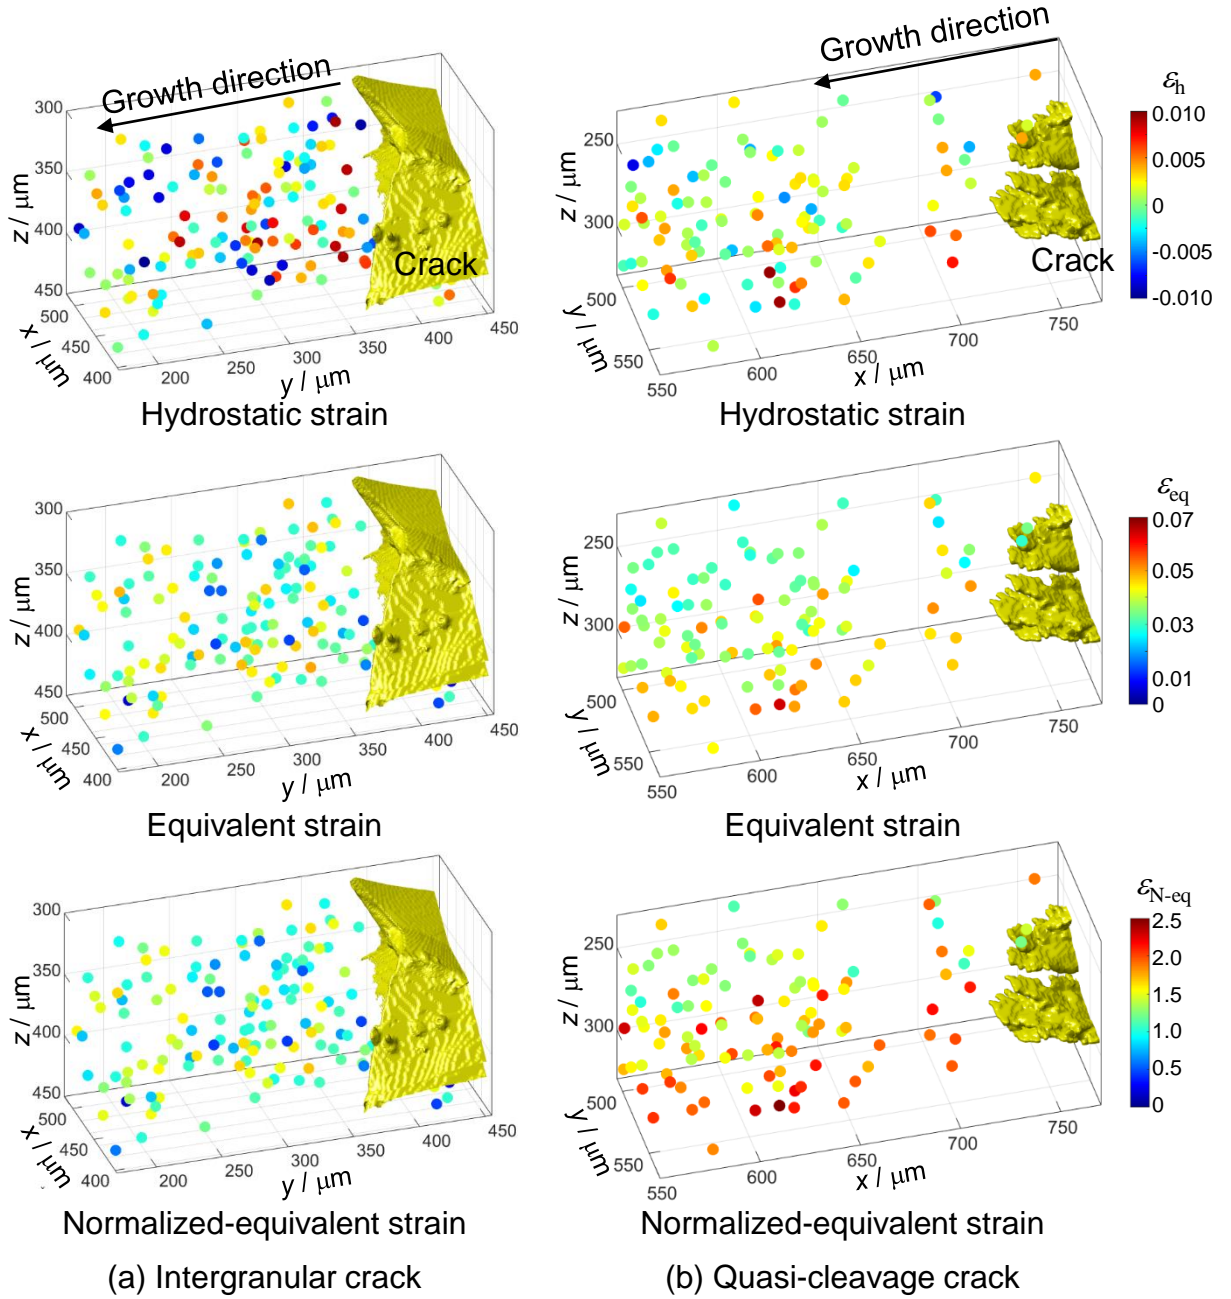


Fig. 11. 3D strain mapping of hydrostatic, equivalent, and normalized-equivalent strains.

Each strain component around a crack tip corresponding to (a) intergranular and (b) quasi-cleavage cracks is represented. The position of each marker is the position of the center of gravity of a tetrahedron composed of pores and particles; the color corresponds to the value of each strain component indicated by the color map.

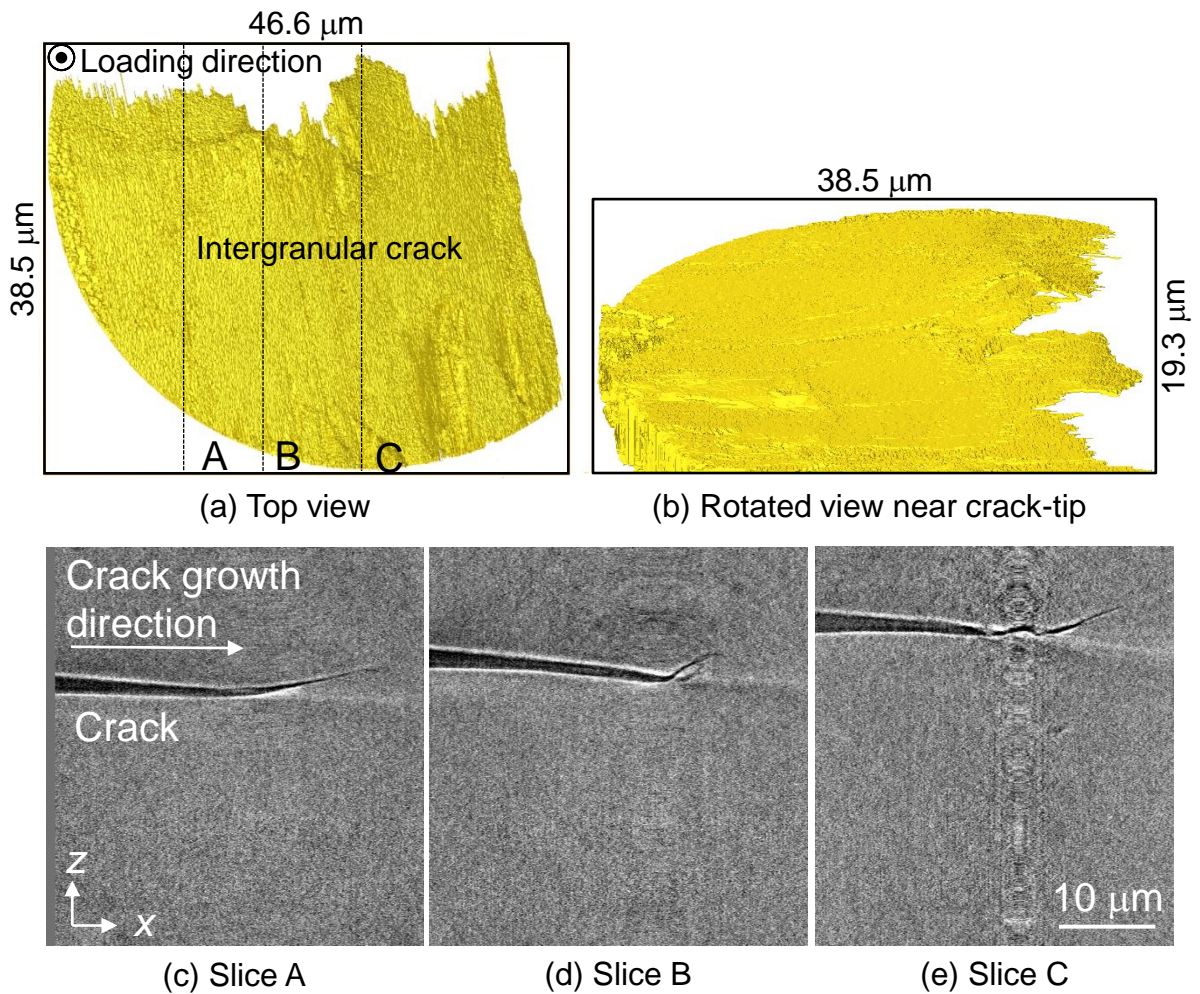


Fig. 12. 3D tomographic images of an intergranular crack ((a) top and (b) side views). In Fig. 12 (c~e), the 2D virtual cross-sections of A, B, and C correspond to the dashed line in the top view.



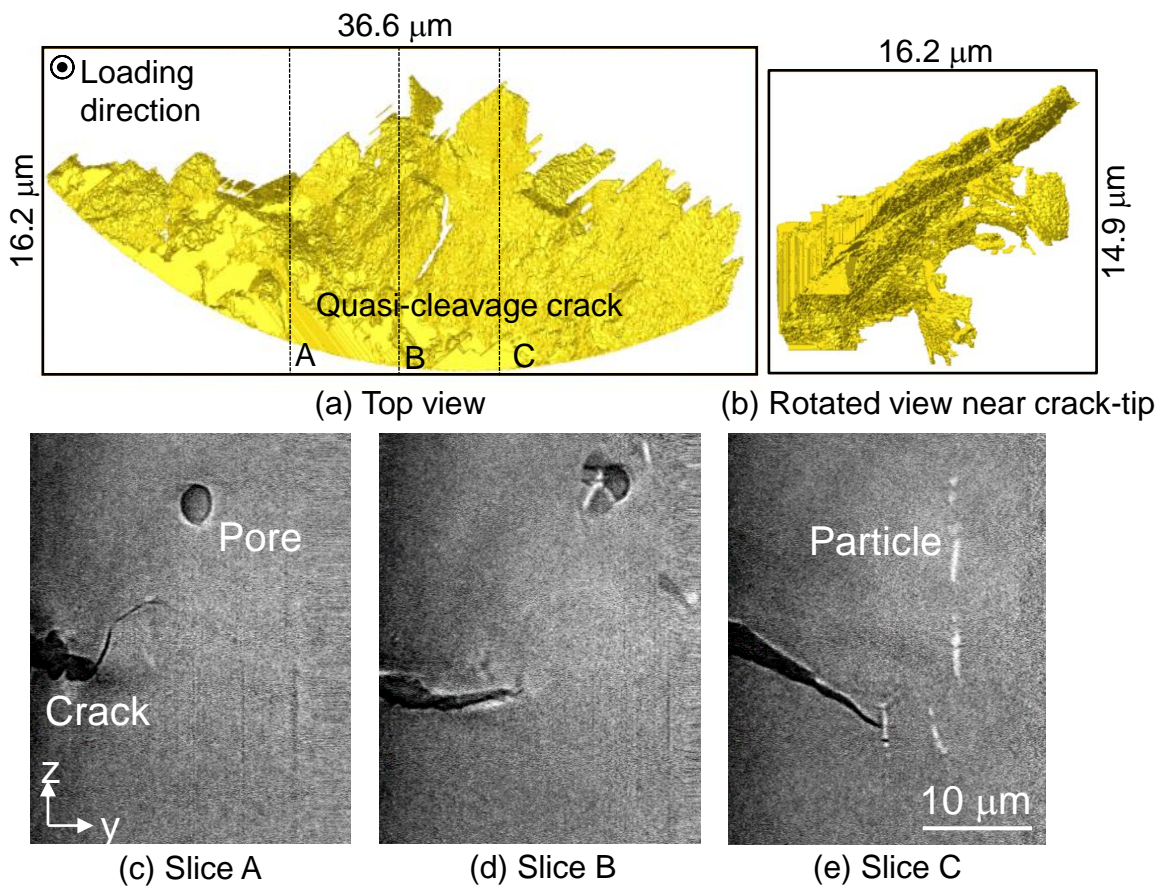


Fig. 13. 3D tomographic images of a quasi-cleavage crack ((a) top and (b) side views). In Fig. 13 (c~e), the 2D virtual cross-sections of A, B, and C correspond to the dashed line in the top view.

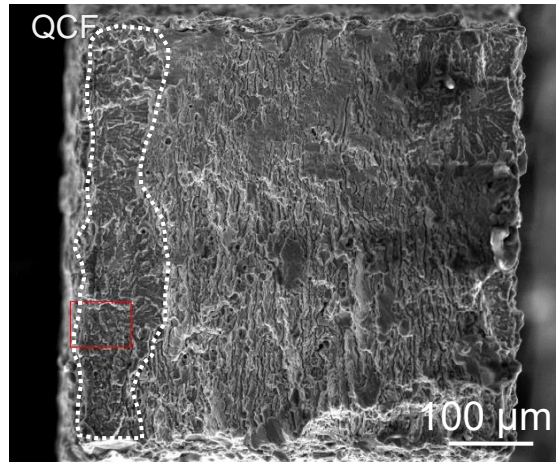

(a) Overall view

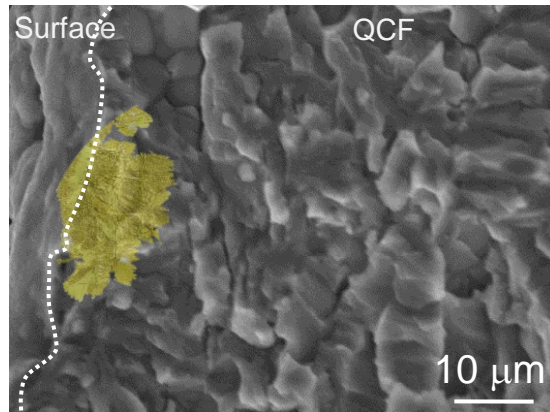

(b) Enlarged view of rectangular region in (a)

Fig. 14. Fracture surface of Al-9.9Zn-2.3Mg-1.4Cu alloy observed by SEM. Fig. 14 (a) is the overall view of fracture surface and (b) is enlarged view of rectangular region in (a). In Fig. 14 (b), the quasi-cleavage crack captured by imaging-type tomography is superimposed.

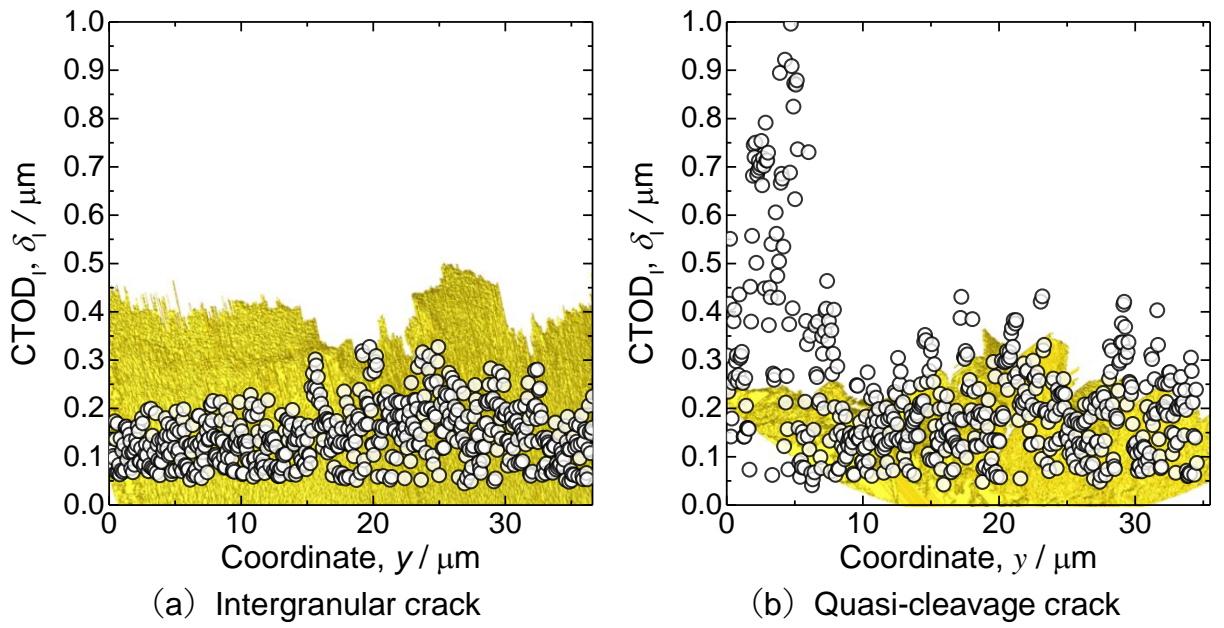


Fig. 15. Variations in local crack driving forces, $CTOD_I$, along the (a) intergranular and (b) quasi-cleavage crack front line. $CTOD_I$ is directly analyzed from the crack tip morphology.

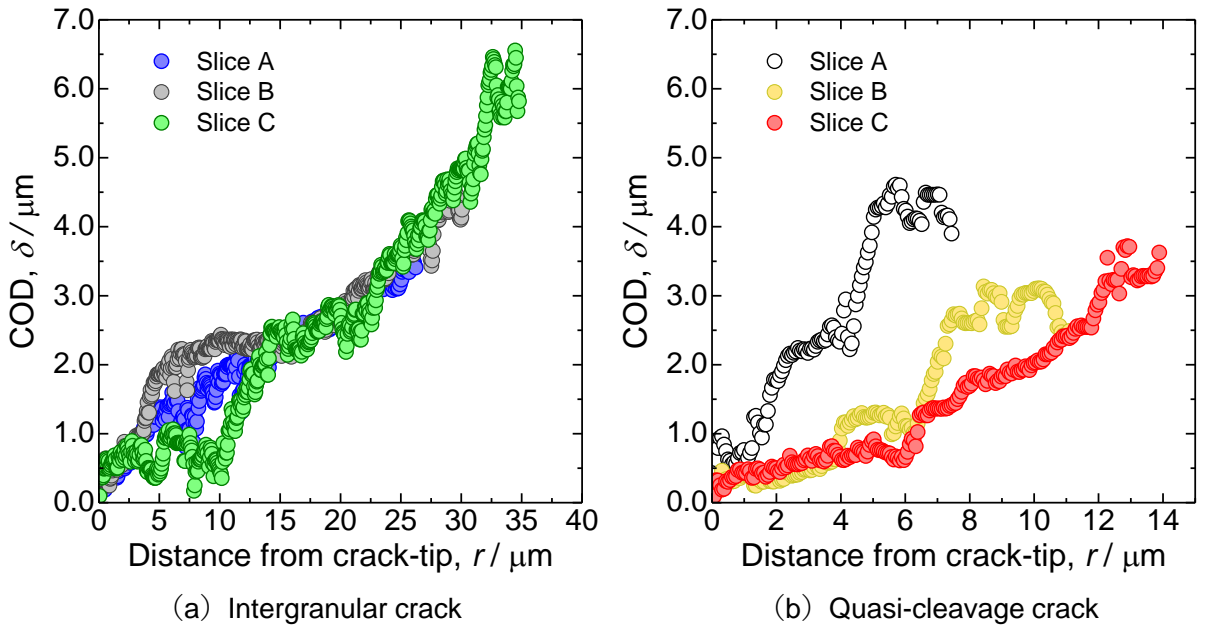


Fig. 16. Variation of the crack opening displacement from the crack tip, which was obtained from slices A, B, and C in Figs. 12 and 13. Fig. 16 (a) and (b) correspond to intergranular and quasi-cleavage cracks, respectively.

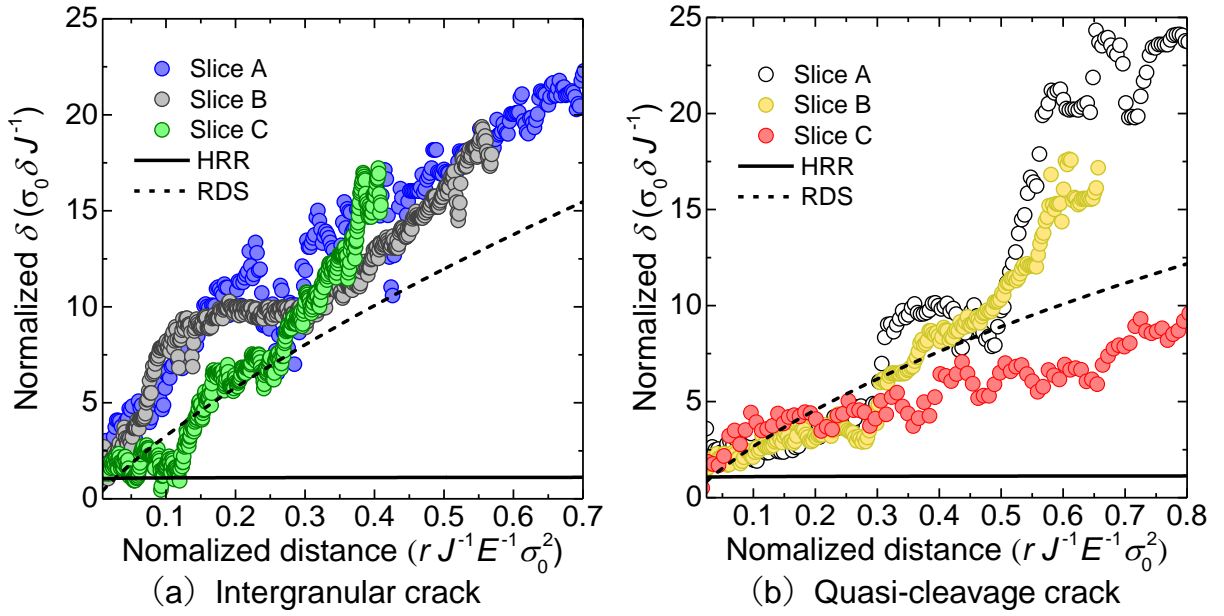


Fig. 17. Normalized crack opening profile as a function of normalized distance for the (a) intergranular and (b) quasi-cleavage crack tips.