

## Cost-effective Synthesis of CeO<sub>2</sub>-SiO<sub>2</sub> Based on Oil Palm Leaves for the Removal of Toxic Compounds

Salprima Yudha S

Department of Chemistry, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu  
Jalan W.R

Banon, Charles

Department of Chemistry, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu  
Jalan W.R

Pertiwi, Reza

Department of Pharmacy, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu  
Jalan W.R

Deni Agus Triawan

Department of Science Laboratory, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu, Jalan W.R

他

<https://doi.org/10.5109/7151676>

---

出版情報 : Evergreen. 10 (3), pp.1307-1312, 2023-09. 九州大学グリーンテクノロジー研究教育センター

バージョン :

権利関係 : Creative Commons Attribution-NonCommercial 4.0 International



# Cost-effective Synthesis of $\text{CeO}_2\text{-SiO}_2$ Based on Oil Palm Leaves for the Removal of Toxic Compounds

Salprima Yudha S<sup>1,2,\*</sup>, Charles Banon<sup>1</sup>, Reza Pertiwi<sup>3</sup>,  
Deni Agus Triawan<sup>4</sup>, Jeong In Han<sup>5</sup>

<sup>1</sup>Department of Chemistry, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu  
Jalan W.R. Supratman, Kandang Limun, Kota Bengkulu 38122, Indonesia

<sup>2</sup>Research Center of Sumatera Natural Products and Functional Materials, Universitas Bengkulu  
Jalan W.R. Supratman, Kandang Limun, Kota Bengkulu 38122, Indonesia

<sup>3</sup>Department of Pharmacy, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu  
Jalan W.R. Supratman, Kandang Limun, Kota Bengkulu 38122, Indonesia

<sup>4</sup>Department of Science Laboratory, Faculty of Mathematics and Natural Sciences, Universitas Bengkulu,  
Jalan W.R. Supratman, Kandang Limun, Kota Bengkulu 38122, Indonesia

<sup>5</sup>Department of Chemical and Biochemical Engineering, Dongguk University-Seoul,  
30, Pildong-ro 1 gil, Jung-gu, Seoul, 04620, Republic of Korea

\*Author to whom correspondence should be addressed:

E-mail: [salprima@unib.ac.id](mailto:salprima@unib.ac.id); [sp.yudha.s.2022@gmail.com](mailto:sp.yudha.s.2022@gmail.com)

(Received February 17, 2023; Revised April 22, 2023; accepted July 4, 2023).

**Abstract:** Using cerium nitrate as a cerium source and oil palm leaves (OPL) as the main silica ( $\text{SiO}_2$ ) source,  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  powder was synthesized via calcination at 900 °C under air conditions. An X-ray diffraction analysis of the as-prepared product revealed the formation of  $\text{CeO}_2$  supported on cristobalite  $\text{SiO}_2$  along with some other minor element oxides. The Fourier transform infrared spectra showed peaks attributable to the Si–O–Si and Ce–O bonds of the binary oxide. According to a scanning electron microscopy analysis, the solid materials produced via calcination were in aggregated form. The solid, which was easily powdered by grinding in a mortar, was studied for the removal of methylene blue (MB) and phenol compounds from aqueous solution. The results showed that the  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  material could remove MB up to 62.6% but was ineffective for phenol removal under various conditions.

Keywords: ceria; silica; oil palm leaves; toxic compounds; composite

## 1. Introduction

The combination of ceria ( $\text{CeO}_2$ ) and silica ( $\text{SiO}_2$ ) has attracted much interest owing to its various applications. For instance, a binary  $\text{CeO}_2\text{-SiO}_2$  material was found to be an effective supporting solid material for nickel catalysts in the dry reforming of methane gas with better results than  $\text{CeO}_2$  or  $\text{SiO}_2$  alone<sup>1</sup>. Similar results were obtained using nano-sized  $\text{CeO}_2\text{-SiO}_2$ , which was synthesized via a wetness method and utilized as a pyrolytic catalyst to convert waste engine oil into diesel fuel<sup>2</sup>.  $\text{CeO}_2\text{-SiO}_2$  has been also prepared by soft chemical routes followed by thermal treatment, achieving an oxygen storage capacity higher than that of cerium oxide ( $\text{CeO}_2$ )<sup>3</sup>, and via thermal decomposition in the presence of PEG-600 to furnish a product that serves as an electrochemical sensor<sup>4</sup>.  $\text{CeO}_2\text{-SiO}_2$  materials prepared using a precipitation method from tetraethyl orthosilicate

(TEOS) and cerium nitrate<sup>5</sup> or cerium chloride and silico fluoric<sup>6</sup> proved to be effective for chemical mechanical polishing. Furthermore, the applicability of  $\text{CeO}_2\text{-SiO}_2$  as an adsorbent of fluoride ions in solution was also demonstrated<sup>7</sup>.

A number of synthesis procedures for  $\text{CeO}_2\text{-SiO}_2$  composites with diverse applications have been developed. For example, a  $\text{CeO}_2\text{-SiO}_2$  composite was prepared as a new type of precursor for the preparation of thin-film indium tin oxide via a sol-gel process<sup>8</sup>. Similarly, a water-in-oil microemulsion of  $\text{CeO}_2\text{-SiO}_2$  was deposited via dip-coating on a glass or  $\text{SiO}_2$  substrate<sup>9</sup>.  $\text{CeO}_2\text{-SiO}_2$  prepared in a single step using a microwave-induced combustion solution was used as a catalyst for carbon monoxide oxidation<sup>10</sup>. A core-shell  $\text{CeO}_2\text{-SiO}_2$  structure having high dispersibility was synthesized via chemical precipitation<sup>11</sup>. Other studies have demonstrated the

successful preparation of  $\text{CeO}_2\text{-SiO}_2$  for methylene blue (MB) degradation using TEOS and cerium nitrate as precursors in the presence of hexadecyltrimethylammonium bromide as a surfactant under microwave irradiation<sup>12</sup>).

Using natural  $\text{SiO}_2$  or industrial waste  $\text{SiO}_2$  instead of commercially available  $\text{SiO}_2$  as the precursor for the synthesis of advanced materials is attracting intense research attention from the viewpoint of sustainability<sup>13,14,15</sup>). For example,  $\text{CeO}_2\text{-SiO}_2$  was synthesized via a sol-gel method using  $\text{CeCl}_3\cdot 7\text{H}_2\text{O}$  and  $\text{SiO}_2$  extracted from rice husk in the presence of sodium dodecyl sulfate. The resulting material was useful in the photocatalytic degradation of the chlorpyrifos pesticide<sup>16</sup>).  $\text{SiO}_2$  extracted from blast furnace slag was also used as a precursor in combination with  $\text{CeO}_2$  extracted from radioactive cerium nitrate solution<sup>17</sup>). Using rice husk as an  $\text{SiO}_2$  precursor also provided a  $\text{CeO}_2\text{-SiO}_2$  composite that was effective in antibiotic removal<sup>18,19</sup>). In line with these reports, we previously reported the use of oil palm leaves (OPL) as a supporting material in the high-temperature synthesis of  $\text{Au-SiO}_2$  composites<sup>20</sup>), which is one of the few studies on the utility of OPL as an  $\text{SiO}_2$  precursor for the development of advanced materials.

In this work, we further exploit the ready availability of OPL from oil palm plantations and use it as a sustainable  $\text{SiO}_2$  source for the synthesis of a  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  binary oxide via a cost-effective and simple single step sintering reaction between OPL and cerium nitrate salt. OPL are one of the by-products of managing oil palm plantations due to pruning activities. Therefore, the results of this research in general also support environmental sustainability. The obtained product was studied as an adsorbent of toxic compounds including MB and phenol from aqueous environments

## 2. Materials and Methods

### 2.1 Materials

Cerium nitrate and methanol were purchased from Merck (Singapore) and used as received. To ensure that the glass material was free from impurities, it was washed with aqua-regia solution prior to use. OPL were obtained from oil palm smallholder farms in the district closest to Universitas Bengkulu (Kota Bengkulu, Indonesia) and subjected to separation from the stem, washing with distilled water, cutting using scissors, air drying for one week, and crushing using a juicer mixer grinder. After cleaning the obtained powder using a sieve, it was ready to be used for the experiments.

### 2.2 Methods

Cerium nitrate (2 mmol) was dissolved in 50 mL of ethanol in a crucible, and 4 g of dried OPL powder was subsequently added to the solution. The mixture was then allowed to stand for one night for the methanol to evaporate slowly and to mediate the interaction between


Si complexes and cerium nitrate. The crucible was then placed into a furnace, which was heated from room temperature to 900 °C for 2 h, followed by maintaining this temperature for 5 h. Then, the mixture was cooled down gradually to room temperature. The obtained powder was subjected to characterization and application experiments. For comparative purposes,  $\text{SiO}_2(\text{OPL})$  was synthesized following a similar procedure, which involved heating at 900 °C for 5 h. The obtained materials were characterized via X-ray diffraction (XRD; X'PERT Powder-PANalytical PW 30/60), scanning electron microscopy (SEM) coupled with energy dispersive X-ray (EDX) spectroscopy (JEOL JSM 6510 LA), and Fourier transform infrared (FTIR) spectroscopy (Bruker, USA).

To evaluate the performance of the obtained materials in the removal of MB, a series of MB solutions in demineralized water (2, 6, 10, 14, and 200 ppm) were prepared and subjected to ultraviolet-visible (UV-vis) spectrophotometry analysis to obtain the corresponding absorbances, which were used to construct a plot of the MB concentration against absorbance using Microsoft Excel software. The corresponding regression formula was used to calculate the initial and final concentrations of the treated MB solutions. Meanwhile, two bottle samples were filled up with 10 mL of MB solution (16 ppm), and each solution was treated with 25 mg of adsorbent, i.e.,  $\text{SiO}_2(\text{OPL})$  and  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$ , at room temperature and without any additional light. The absorbance of the treated and untreated solutions was measured using a UV-vis spectrophotometer. A similar procedure was applied to a series of phenol standard solutions (50, 100, 150, and 200 ppm). For the adsorption experiments, some bottle samples were filled up with 10 mL of phenol solution (150 ppm) and treated with 25 mg of  $\text{SiO}_2(\text{OPL})$  or  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$ .


## 3. Results and Discussion

The OPL powder was obtained following the procedure described in the experimental section. The preparation of the  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  composite is illustrated in Fig. 1. When the OPL powder (Fig. 1a) was mixed with cerium nitrate salt (Fig. 1b) and subjected to calcination at 900 °C, the product shown in Fig. 1c was obtained. The product is obtained when the organic compounds in OPL are decomposed and cerium nitrate is changed into  $\text{CeO}_2$ .

Next, the as-prepared material was characterized. The XRD pattern of the product obtained from the reaction of cerium nitrate and OPL at 900 °C is shown in Fig. 2.

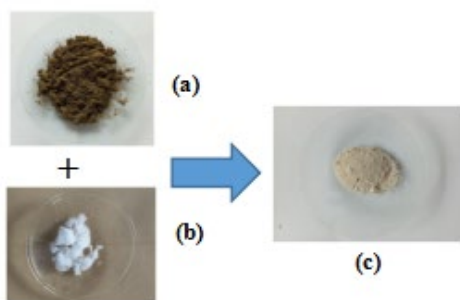


**Fig.1:** Preparation steps of as-prepared powder; (a) oil palm leaf powder, (b) cerium nitrate, (c)  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  powder

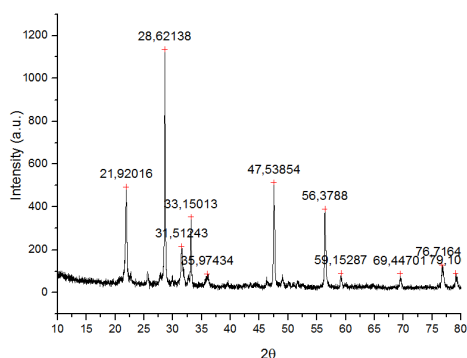

**Fig. 2:** XRD pattern of  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  prepared from OPL and cerium nitrate


The sharp peaks at  $28.6^\circ$ ,  $33.2^\circ$ ,  $47.5^\circ$ , and  $56.4^\circ$  indicated the formation of  $\text{CeO}_2$  in the crystalline phase (JCPDS No. 34-0394), and the peaks at  $21.9^\circ$ ,  $28.3^\circ$ ,  $31.5^\circ$ , and  $35.9^\circ$  revealed the presence of amorphous cristobalite  $\text{SiO}_2$ <sup>5)</sup>. This result demonstrates that the obtained product contained crystalline  $\text{CeO}_2$  and cristobalite  $\text{SiO}_2$ , which was further supported by the FTIR spectra (Fig. 3). Thus, the peaks at  $1087\text{ cm}^{-1}$  and  $793\text{ cm}^{-1}$  can be attributed to the vibration of the Si-O-Si bonds, and those between  $500$  and  $750\text{ cm}^{-1}$  are related to Ce-O bonds. The latter peaks are very clear due to the formation of crystalline  $\text{CeO}_2$ . These results are in agreement with those of previous studies<sup>21,22,23)</sup>.

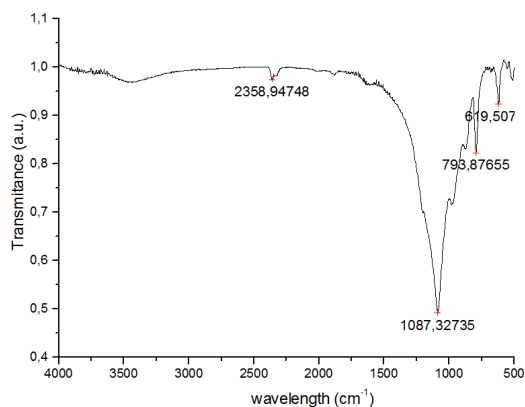


**Fig. 3:** FTIR pattern of  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  prepared from OPL and cerium nitrate

The SEM and EDX results shown in Fig. 4 and Fig. 5

reveal the morphology and elemental content of the materials, respectively. Specifically, Fig. 4a displays an SEM image ( $1000\times$  magnification) of the  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  product obtained after calcination at  $900^\circ\text{C}$ , showing that  $\text{CeO}_2$  particles were combined with  $\text{SiO}_2$  particles and distributed in blocks. The higher magnified image shown in Fig. 4b ( $10000\times$  magnification) revealed the occurrence of aggregation of the  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  powders. As suggested in previous studies, a high calcination temperature does not necessarily result in clearly separated particles in the powder, and the surface is not always clearly identifiable<sup>24,25)</sup>.

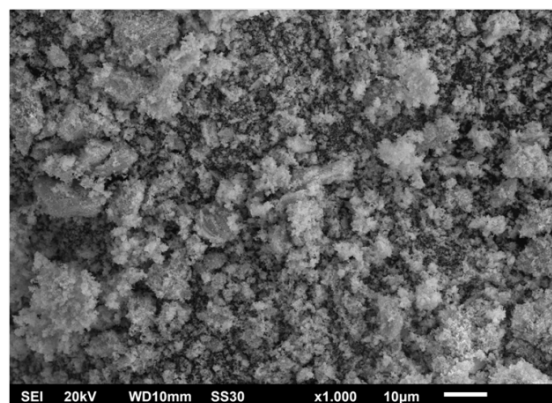

(a)

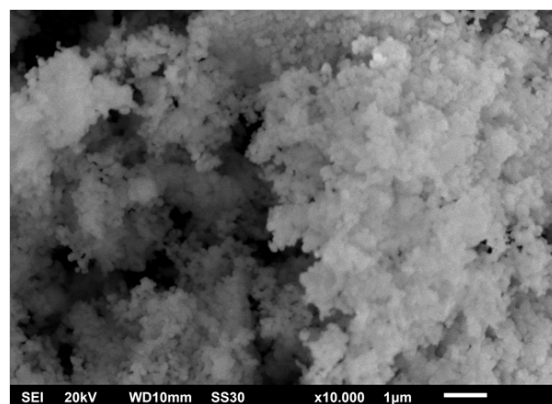


(b)

**Fig.4:** SEM analysis of  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  prepared from OPL and cerium nitrate (a)  $1000\times$  magnification, (b)  $10000\times$  magnification

The presence of Ce and Si elements in the as-prepared material was confirmed by the EDX results shown in Fig. 5 and Table 1, which showed representative peaks for Ce (25%), Si (15%), and O (43%). The presence of minor elements, which are most likely also in the form of oxides, stems from other minor minerals in OPL.

Fig. 6 shows the results of an MB removal experiment performed using the prepared material. Good activity was observed even in the absence of UV - vis or sunlight irradiation.

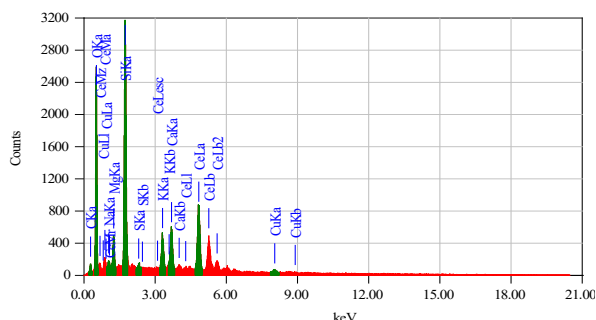


**Fig. 5:** EDX pattern of  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  prepared from OPL and cerium nitrate

**Table 1.** EDX analysis of the prepared  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$

Element	K(eV)	% mass
C	0.277	6.27
O	0.525	43.41
Na	1.041	0.61
Mg	1.253	2.41
Si	1.739	14.89
S	2.303	0.23
K	3.312	2.72
Ca	3.690	3.19
Ce	4.837	25.22
Cu	8.040	1.04

Using the linear regression equations obtained as described in the experimental section, the final concentration of each solution after treatment was obtained. The removal capacity was then calculated using the initial MB concentration before treatment and the final MB concentration according to the formula:

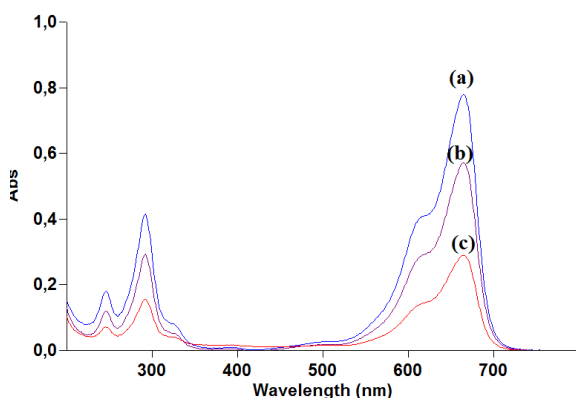

**Fig. 6:** UV-vis spectrophotometer analysis of (a) untreated MB solution, (b) MB treated with silica (OPL), and (c) MB treated with  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$

Using the linear regression equations obtained as described in the experimental section, the final concentration of each solution after treatment was obtained. The removal capacity was then calculated using the initial MB concentration before treatment and the final MB concentration according to the formula:

$$\text{Removal capacity (\%)} =$$

$$\frac{(\text{Initial concentration} - \text{final concentration}) \times 100\%}{\text{Initial concentration}}$$

$\text{CeO}_2\text{-SiO}_2(\text{OPL})$  and  $\text{SiO}_2(\text{OPL})$  exhibited removal capacities of 62.6% and 26.6%, respectively. This result demonstrates that  $\text{SiO}_2(\text{OPL})$  produced from the degradation of OPL can remove MB molecules even without the effect of light irradiation, which may be due to the adsorption process that occurs on the surface of the  $\text{SiO}_2$  solid materials. The higher MB removal capacity of  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  compared with  $\text{SiO}_2(\text{OPL})$  indicates that there is a synergistic effect on the adsorption of MB molecules between  $\text{SiO}_2$  and  $\text{CeO}_2$ , which could be trapped in the  $\text{SiO}_2$  matrix or attached to the surface of the  $\text{SiO}_2$  particles. Previous research suggested that adding silica to a nanocomposite could improve MB adsorption because it increases the nanocomposite's surface area<sup>26</sup>. It is also possible that this synergistic effect is achieved through the basicity of the  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  composite. As previously reported, the basicity of  $\text{CeO}_2$  particles depends on their size<sup>27</sup>. The basicity of the reaction medium can accelerate the photolysis of MB molecules in aqueous solution<sup>28</sup>. The presence of minor alkali compounds formed from Ca and Mg might also help achieve the observed performance. This is in line with previous studies showing that doping  $\text{CeO}_2$  nanoparticles with alkaline metal ions (Mg, Ca, Sr, and Ba) enhanced the photodegradation of MB compared with that of pure  $\text{CeO}_2$  nanoparticles<sup>29</sup>. Furthermore, the high heating temperature used in the preparation of the composite might also affect the adsorption performance of  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$ , as was demonstrated in previous works reporting that  $\text{CeO}_2$  nanofibers obtained at 800 °C afforded a photodegradation rate of up to 98%, whereas that of the material prepared at 500 °C was 67%<sup>30</sup>.

In contrast, the as-prepared material was not effective for the removal of phenol either in the dark or under sunlight irradiation. Only a small decrease in absorbance was observed after treatment, which was indicative of a low phenol removal capacity. This result could be due to inactivation of the  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  material as a result of a decrease in the basicity of the composite in the presence of acidic phenol. The degradation of phenol has been previously reported to be affected by the solution pH<sup>31,32</sup>.

#### 4. Conclusion

$\text{CeO}_2\text{-SiO}_2(\text{OPL})$  was obtained as a major product by heating a mixture of cerium nitrate and OPL at 900 °C, as demonstrated by means of XRD, FTIR, and EDX analyses. The morphology of  $\text{CeO}_2\text{-SiO}_2(\text{OPL})$  was investigated via SEM, revealing that the powder material was in aggregated form and showed an irregular surface. The as-prepared material could adsorb MB from aqueous

solutions with good activity but was not effective for phenol removal.

### Acknowledgements

All of us as authors are very grateful to the Ministry of Education, Culture, Research, and Technology of the Republic of Indonesia and the Indonesia Endowment Funds for Education (LPDP), which have provided funding assistance to develop cooperation between universities through the World Class Professor (WCP) Program for the 2022 fiscal year. We also thank everyone who has helped with the technical parts of the WCP program at Universitas Bengkulu.

### References

- 1) Y. Taufiq-Yap, Sudarno, U. Rashid, and Z. Zainal "CeO<sub>2</sub>-SiO<sub>2</sub> supported nickel catalysts for dry reforming of methane towards syngas production". *Applied Catalysis A: General* **468** (5) 359–369 (2013) doi: <https://doi.org/10.1016/j.apcata.2013.09.020>
- 2) N. Zandi-Atashbar, A.A. Ensafi, and Ahoor, "Nano-CeO<sub>2</sub>/SiO<sub>2</sub> as an efficient catalytic conversion of waste engine oil into liquid fuel. *Journal of Cleaner Production*, **166**, 1010–1019 (2017). doi: <https://doi.org/10.1016/j.jclepro.2017.08.103>
- 3) B.M. Reddy and A. Khan, "Nanosized CeO<sub>2</sub>-SiO<sub>2</sub>, CeO<sub>2</sub>-TiO<sub>2</sub>, and CeO<sub>2</sub>-ZrO<sub>2</sub> mixed oxides: influence of supporting oxide on thermal stability and oxygen storage properties of ceria" *Catalysis Surveys from Asia*, **9**(3) 155–171 (2005). doi: <https://doi.org/10.1007/s10563-005-7552-1>
- 4) A. Padmanaban, T. Dhanasekaran, R. Manigandan, S.P. Kumar, G. Gnanamoorthy, A. Stephen, and V. Narayanan, "Synthesis, characterization and electrochemical sensing properties of CeO<sub>2</sub>@SiO<sub>2</sub>" *International J. Scientific & Eng. Research*, **6** (12) 60–63 (2015). url: [https://www.ijser.org/researchpaper/Synthesis-Characterization-and-Electrochemical-Sensing-Properties-of-CeO<sub>2</sub>-SiO<sub>2</sub>.pdf](https://www.ijser.org/researchpaper/Synthesis-Characterization-and-Electrochemical-Sensing-Properties-of-CeO2-SiO2.pdf)
- 5) X. Zhao, R. Long, Y. Chen, and Z. Chen, "Synthesis, characterization of CeO<sub>2</sub>@SiO<sub>2</sub> nanoparticles and their oxide CMP behavior". *Microelectronic Engineering* **87**, 1716–1720 (2010). doi: <https://doi.org/10.1016/j.mee.2009.09.012>
- 6) Q. He, "Experimental study on polishing performance of CeO<sub>2</sub> and nano-SiO<sub>2</sub> mixed abrasive". *Applied Nanoscience* **8**, 163–171 (2018). DOI: <https://doi.org/10.1007/s13204-018-0657-4>
- 7) J. Lin, Y. Wu, A. Khayambashi, X. Wang, and Y. Wei, "Preparation of a novel CeO<sub>2</sub>/SiO<sub>2</sub> adsorbent and its adsorption behavior for fluoride ion" *Adsorption Science & Technology*, **36** (1–2) 743–761 (2018). doi: <https://doi.org/10.1177/2F0263617417721588>
- 8) B. Zhu, Z. Luo, C. Xia, "Transparent conducting CeO<sub>2</sub>-SiO<sub>2</sub> thin films". *Materials Research Bulletin* **34**(10/11), 1507–1512 (1999). doi: [https://doi.org/10.1016/S0025-5408\(99\)00185-3](https://doi.org/10.1016/S0025-5408(99)00185-3)
- 9) F. Grasset, R. Marchand, A.M. Marie, and D. Fauchadour, F. Fajardie, "Synthesis of CeO<sub>2</sub>@SiO<sub>2</sub> core-shell nanoparticles by water-in-oil microemulsion. Preparation of functional thin film". *J. Coll. and Interface Science*, **299**, 726–732 (2006). doi: <https://doi.org/10.1016/j.jcis.2006.02.028>
- 10) B.M. Reddy, G.K. Reddy, I. Ganesh, and J.M.F. Ferreira "Single step synthesis of nanosized CeO<sub>2</sub>-M<sub>x</sub>O<sub>y</sub> mixed oxides (M<sub>x</sub>O<sub>y</sub> = SiO<sub>2</sub>, TiO<sub>2</sub>, ZrO<sub>2</sub>, and Al<sub>2</sub>O<sub>3</sub>) by microwave induced solution combustion synthesis: characterization and CO oxidation" *J Mater Sci* **44**, 2743–2751 (2009). DOI: <https://doi.org/10.1007/s10853-009-3358-2>
- 11) J. Mao, Y. Bai, L. Gu, P.A. van Aken, M.J. Tu, "Preparation and characterization of size-controlled CeO<sub>2</sub> nanoparticles coated with SiO<sub>2</sub>. *J. Nanopart. Res.* **12**, 2045–2049 (2010). doi: <https://doi.org/10.1007/s11051-009-9762-3>
- 12) R.M. Mohamed, and E.S. Aazam "Synthesis and characterization of CeO<sub>2</sub>-SiO<sub>2</sub> nanoparticles by microwave-assisted irradiation method for photocatalytic oxidation of methylene blue dye" *International J. Photoenergy*, **Vol. 2012**, Article ID 928760, 9 pages (2012). doi: <https://doi.org/10.1155/2012/928760>
- 13) H.A. Hijri, J.F. Fatriansyah, N. Sofyan, and D. Dhaneswara "Potential use of corn cob waste as the base material of silica thin films for anti-reflective coatings" *Evergreen* **9**(1) 102–108 (2022). doi: <https://doi.org/10.5109/4774221>
- 14) S. Hanif, M. Sultan, T. Miyazaki, and S. Koyama "Steady-state Investigation of Desiccant Drying System for Agricultural Applications" *Evergreen* **5**(1) 33–42 (2018). doi: <https://doi.org/10.5109/1929728>
- 15) S. Silviana, A.G. Hasega, A.R.N Hanifah, and A.N. Sa'adah "Synthesis of Silica Coating Derived from Geothermal Solid Waste Modified with 3-Aminopropyl Triethoxysilane (APTES) and Silver Nano Particles (AgNPs)" *Evergreen* **9**(4) 1224-1230 (2022). doi: <https://doi.org/10.5109/6625733>
- 16) M.A. Farrukh, K.M. Butt, A. Altaf, and S. Khadim, "Influence of pH and temperature on structural, optical and catalytical investigations of CeO<sub>2</sub>-SiO<sub>2</sub> nanoparticles" *Silicon* **11**, 2591–2598 (2019). doi: <https://doi.org/10.1007/s12633-018-0050-7>
- 17) A.S. Dhmees, A.M. Rashada, A.A. Eliwab, and M.F. Zawrah "Preparation and characterization of nano SiO<sub>2</sub>@CeO<sub>2</sub> extracted from blast furnace slag and uranium extraction waste for wastewater treatment. *Ceramics International* **45**, 7309–7317 (2019). doi: <https://doi.org/10.1016/j.ceramint.2019.01.014>
- 18) T.-M.-A. Le, T.-M.-Q. Pham, T.-D. Nguyen, and T.-D. Pham, "Adsorption characteristics of amoxicillin antibiotic on CeO<sub>2</sub>-coated SiO<sub>2</sub> nanomaterials. *Vietnam J. Catalysis and Adsorption*, **9** (4), 111–116

- (2020). doi: <https://doi.org/10.51316/jca.2020.079>
- 19) T.-D. Pham, T.-M.-A. Le, T.-M.-Q. Pham, V.H. Dang, K.-L. Vu, T.-K. Tran, and T.-H. Hoang, "Synthesis and Characterization of Novel Hybridized CeO<sub>2</sub>@SiO<sub>2</sub> Nanoparticles Based on Rice Husk and Their Application in Antibiotic Removal, *Langmuir*, **37**, 2963–2973 (2021). doi: <https://doi.org/10.1021/acs.langmuir.0c03632>
- 20) S.Yudha S., A. Falahudin, Asdim, and J.I. Han, "In Situ Preparation of gold-silica particles from a mixture of oil palm leaves and chloroauric acid for reduction of nitroaromatic compounds in water. *Waste Biomass Valor*, **12**, 3773–3780 (2021). doi: <https://doi.org/10.1007/s12649-020-01273-1>
- 21) B. Sarkar, R.K. Singha, R. Tiwari, S. Ghosh, S.S. Acharyya, C. Pendem, L.N.S. Konathala, and R. Bal "Preparation of CeO<sub>2</sub> nanoparticles supported on 1-D silica nanostructures for room temperature selective oxidation of styrene" *RSC Advance*, **4L**, 5453–5456 (2014). doi: <https://doi.org/10.1039/C3RA46179C>
- 22) X. Zhong, Y. Zhou, M. He, Y. Tong, L. Fan, and Z. Cai "Synthesis of organosiloxane-coated SiO<sub>2</sub>/CeO<sub>2</sub> with multilayered hierarchical structure and its application in optical diffusers" *J. Mater. Sci.*, **52**, 12806–12817 (2017). doi: <https://doi.org/10.1007/s10853-017-1281-5>
- 23) Z. Pang, Q. Nie, Y. Zhu, M. Ge, and M. Chen, "Enhanced ammonia sensing characteristics of CeO<sub>2</sub> decorated SiO<sub>2</sub>/PANI free-standing nanofibrous membranes, *Mater. Sci.*, **54**, 2333–2342 (2019). doi: <https://doi.org/10.1007/s10853-018-2981-1>
- 24) S. Phanichphant, A. Nakaru, and D. Channei, "Photocatalytic activity of the binary composite CeO<sub>2</sub>/SiO<sub>2</sub> for degradation of dye" *Applied Surface Science*, **387**, 21–220 (2016). doi: <http://dx.doi.org/10.1016/j.apsusc.2016.06.072>
- 25) M. Wei, L. Sun, C. Zhang, P. Qi, and J. Zhu, "Shear-thickening performance of suspensions of mixed ceria and silica nanoparticles" *J. Mater. Sci.*, **54**, 346–355 (2019). doi: <https://doi.org/10.1007/s10853-018-2873-4>
- 26) I.H.Dwirekso, M. Ibadurrohman, and Slamet "Synthesis of TiO<sub>2</sub>-SiO<sub>2</sub>-CuO Nanocomposite Material and Its Activities for Self-cleaning" *Evergreen*, **07**(2) 285–291 (2020). doi: <https://doi.org/10.5109/4055234>
- 27) Z. Cui, J. Gan, J. Fan, and Y. Xue, and R. Zhang, "Size-dependent surface basicity of nano-CeO<sub>2</sub> and the desorption kinetics of CO<sub>2</sub> on its surface. *Ind. Eng. Chem. Res.*, **57** (32), 10977–10984 (2018). doi: <https://doi.org/10.1021/acs.iecr.8b01247>
- 28) T. Soltani, and M.H. Entezari, Photolysis and photocatalysis of methylene blue by ferrite bismuth nanoparticles under sunlight irradiation. *J. Molecular Catalysis A: Chemical*, **377**, 197–203 (2013). doi: <http://dx.doi.org/10.1016/j.molcata.2013.05.004>
- 29) R. Murugana, L. Kashinath, R. Subasha, P. Sakthivel K. Byrappa, S. Rajendran, and G. Ravia, "Pure and alkaline metal ion (Mg, Ca, Sr, Ba) doped cerium oxide nanostructures for photo degradation of methylene blue" *Mater. Res. Bull.* **97**, 319–325 (2018). doi: <https://doi.org/10.1016/j.materresbull.2017.09.026>
- 30) X. Yang, Y. Liu, J. Li, and Y. Zhang, "Effects of calcination temperature on morphology and structure of CeO<sub>2</sub> nanofibers and their photocatalytic activity". *Mater. Lett.*, **241**, 76–79 (2019). doi: <https://doi.org/10.1016/j.matlet.2019.01.006>
- 31) N. Graham, C.-C. Jiang, X.-Z., Li, J.-Q. Jiang, and J. Ma, "The influence of pH on the degradation of phenol, and chlorophenols by potassium ferrate" *Chemosphere* **56**, 949–956 (2004). doi: <https://doi.org/10.1016/j.chemosphere.2004.04.060>
- 32) A. Mohamed, S. Yousef, W.S. Nasser, T.A. Osman, A. Knebel, E.P.V. Sánchez, and T. Hashem "Rapid photocatalytic degradation of phenol from water using composite nanofibers under UV." *Environ. Sci. Eur.*, **32**, 160 (2020). doi: <https://doi.org/10.1186/s12302-020-00436-0>