

Influence of Lubrication on Vibration Response and Surface Roughness in Milling of Aluminum 6061

Aziz, Amiruddin

Research Center for Process and Manufacturing Industry Technology, National Research and Innovation Agency (BRIN), Indonesia

Azka, Muizuddin

Research Center for Process and Manufacturing Industry Technology, National Research and Innovation Agency (BRIN), Indonesia

Nur Cholis Majid

Research Center for Process and Manufacturing Industry Technology, National Research and Innovation Agency (BRIN), Indonesia

Mahfudz Al Huda

Research Center for Structural Strength Technology, National Research and Innovation Agency (BRIN), Indonesia

他

<https://doi.org/10.5109/7151725>

出版情報 : Evergreen. 10 (3), pp.1762-1769, 2023-09. 九州大学グリーンテクノロジー研究教育センター

バージョン :

権利関係 : Creative Commons Attribution-NonCommercial 4.0 International



Influence of Lubrication on Vibration Response and Surface Roughness in Milling of Aluminum 6061

Amiruddin Aziz¹, Muizuddin Azka^{1,*}, Nur Cholis Majid¹, Mahfudz Al Huda², Agus Susanto³, Khairul Jauhari⁴, Achmad Zaki Rahman⁴, Ratna Nurmayni⁵

¹Research Center for Process and Manufacturing Industry Technology,
National Research and Innovation Agency (BRIN), Indonesia

²Research Center for Structural Strength Technology,
National Research and Innovation Agency (BRIN), Indonesia

³Department of Railway Engineering, State Polytechnic of Madiun, Indonesia

⁴Laboratory for Machine Tool, Production, and Automation,
National Research and Innovation Agency (BRIN), Indonesia

⁵Research Center for Transportation Technology,
National Research and Innovation Agency (BRIN), Indonesia

E-mail: muizuddin.azka@brin.go.id

(Received March 3, 2023; Revised June 19, 2023; accepted July 14, 2023).

Abstract: Aluminum is used widely for components of renewable energy, such as wind and hydro turbines. Some of these components require a milling process to improve surface quality. This research presented the influence of lubrication on vibration and surface roughness in the milling process. The first step, the modal parameters data were obtained by the impulse response method using a hammering test with an impulse hammer, then the milling tests experiment were conducted in three different cutting conditions i.e. dry cutting, wet cutting with coolant and oil. The three-axis accelerometer was used to collect acceleration signals of milling test. The collected acceleration signals then were analyzed using Fast Fourier Transform (FFT) to first transform the signals into frequency domain and after that more phenomenon of the milling process in frequency domain were analyzed. Then, the surface roughness was measured using a surface roughness tester. The results showed that the amplitude of signal is lower in milling with lubricant than dry cutting. The cutting condition was stable in wet cutting for both types of lubricant while the chatter occurs in dry cutting. Then, the surface roughness for wet cutting is better than dry cutting and the best of roughness is wet cutting with lubricant of coolant in this experiment.

Keywords: Lubrication; Milling Process; Aluminum; Vibration Response; Surface Roughness

1. Introduction

Based on the General National Energy Plan, Indonesia has commitment to makes an energy transition towards new and renewable energy. The target of renewable energy implementation in Indonesia based on the General National Energy Plan is 25% of the total energy demand in Indonesia in 2025, increasing to 35% in 2050^{1,2)}. Indonesia has a potential energy mix from renewable energy to wind energy and hydro energy power generation. Indonesia has applied hydro energy for renewable energy mix with a value of 17.8% in 2018³⁾. However, it still can be improved, which has extensive potential resources from the current capacity. Wind energy also has a high potential to be applied in Indonesia. Wind energy application is still low at 0,1% of the total energy used in

2018. Besides, the potential for wind energy and solar application is much greater than what has been applied at this time and can still be improved further⁴⁾.

Applying wind and hydro energy technology requires a precision milling process to produce suitable components. In the wind turbine and hydro energy components, the results of the milling process with smooth surface roughness are very necessary because it will affect the turbine performance⁵⁾. One of the materials used for components of wind turbines and hydro turbines is aluminum alloy⁶⁻⁸⁾. It is one of the materials that are easy to machines with a relatively lightweight^{9,10)}. Aluminum 6061 and Titanium 6Al-4V are usually used as material for gas turbines and has perform life prediction with good result¹¹⁾. Furthermore, aluminum 6061 is recommended as material for wind turbine edges since it has excellent

erosion resistance, durable, high strength-to-weight ratio, and cannot react to air¹²).

The milling process will meet the problem of excessive vibration or called chatter. The chatter that arises will cause productivity and quality to decline¹³. It causes the worst surface roughness, which will interfere with the function of the component⁵. In general, excessive vibration is a very dangerous phenomenon that also leads to tool wear¹⁴. There are several influencing parameters to avoid large vibrations in the milling, such as depth of cut (DoC), spindle speed, feed rate, lubrication, etc. It is significant to research the effect of changing these parameters¹⁵.

From several studies that have been carried out, lubrication is one of the parameters that affect the roughness of the workpiece. Lubrication needs to diminish wear and excessive friction and also significantly affects the surface roughness of the milling process¹⁶. Lubrication in the milling process has a positive impact on preventing excessive vibration or chatter. It will also affect surface roughness results and dimensional accuracy¹⁷. To mitigate excessive vibration problems, machinists usually execute the operation in the milling process with conservative process parameters, such as reducing feed rate, cutting depth, and cutting width¹⁸. However, it will decrease the material removal rate, leading to a longer time and a less efficient milling process¹⁹.

For monitoring milling operations based on spectral analysis, Fast Fourier Transform (FFT) can be used where this method transforms vibration signals in the time domain into signals in the frequency domain²⁰. FFT could be utilized to analyze cutting force signals that are used to detect chatter²¹. FFT is employed to analyze sound signals, which are obtained during the machining process²². FFT is also used to identify chatter vibration which uses acceleration signals^{23,24}.

This research compares several lubrication methods and various radial depths of cut to examine their effect on vibration and surface roughness in the milling process of aluminum 6061. This has several processes, firstly, we execute hammering tests to obtain modal parameters of workpieces. Next, we carry out a milling experiment on the workpieces which has set the milling conditions, dry and wet conditions with soluble oil and oil. This process is recorded by a 3-axis accelerometer and data storage acquisition then processed with FFT. To compare the roughness surface for each milling condition, we measure the machined surface using a roughness tester and take 100 times magnification photographs. Thus, we can conclude from those data, the influence of lubrication on vibration response and surface roughness in the milling of aluminum 6061. This research is conducted to find the relation between milling condition, vibration response, and surface roughness.

2. Methodology

2.1 Modal Parameters Using FRF

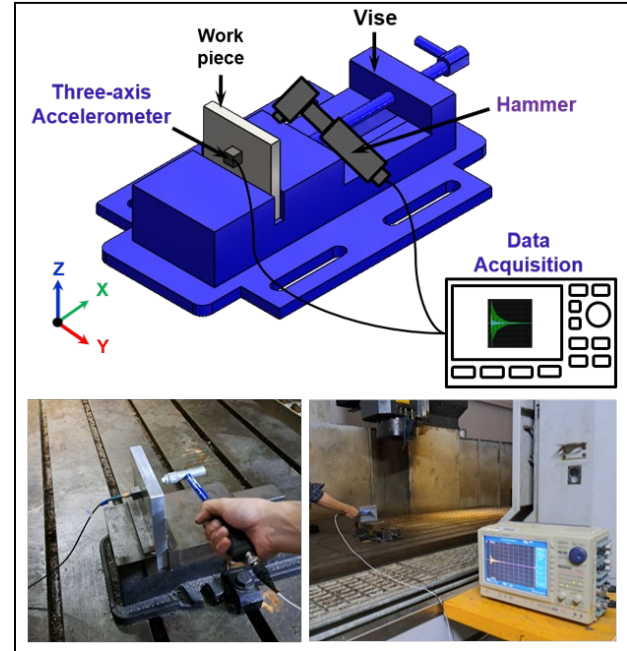


Fig. 1: Hammering Test Set Up

The impulse hammering test was carried out to collect the modal parameters of workpieces such as natural frequency, stiffness, and damping ratio. **Fig. 1** showed the illustration and the photograph of hammering test in this experiment, the hammer hit a workpiece in the X-axis, Y-axis, and Z-axis direction and the three-axis accelerometer sensor sticks on the workpiece. The hammering test is repeated three times in every axis direction. The data storage acquisition Yokogawa DL750 was used to collect the impulse force and the acceleration signals^{23,25,26}. The sampling rate of data storage acquisition was set at 200 kHz. In this experiment, the type of hammer was Dytran 5800B3, and the three-axis accelerometer sensor was Dytran 3413A2^{27,28}.

The results of impulse force and the acceleration signals can be constructed to be a frequency response function (FRF)^{29,30}. The FRF can be expressed as :

$$H_{ij}(f) = \sum_{r=1}^N \frac{\phi_{ir} \phi_{jr}}{k_r (1 - \lambda_r^2 + j2\xi_r \lambda_r)} \quad (1)$$

Where K_r , ξ_r , and ϕ_r are the stiffness, damping ratio, and mode shape of the r -th mode, $\lambda_r = f/f_r$ and f_r is the natural frequency of the r -th mode. The natural frequency can be got as:

$$f_n = f_r \quad (2)$$

Where f_r is the frequency at point f in the **Fig. 2**, and the damping ratio ξ could be expressed below:

$$\xi = (f_e - f_d)/2f_f \quad (3)$$

Where f_d and f_e are the frequency at the amid points, between points d and e, the stiffness k could be expressed below :

$$k = 1/2\xi H_{if} \quad (4)$$

Where H_{if} is the imaginary graph value at point f, the minimum value on the imaginary frequency function curve.

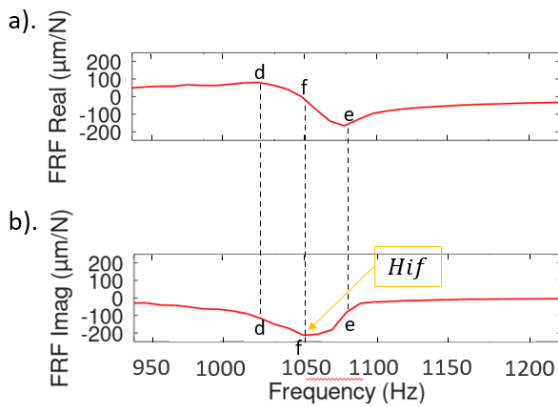


Fig. 2: The FRF on X-axis;
a) Real and b) Imaginary of a workpiece

In the hammering tests experiment, the values of FRF were determined on X-axis, Y-axis, and Z-axis direction, and then the value with the lowest stiffness was observed. The results showed that the lowest value of stiffness was found on the X-axis direction as can be seen in **Fig. 2**. Furthermore, the modal parameters such as stiffness, natural frequency, and damping ratio can be calculated using the curve of FRF. The values of modal parameters were listed in Table 1.

Table 1. Modal Parameters

Natural Frequency f (Hz)	Stiffness k ($\frac{N}{\mu m}$)	Damping Ratio ζ (%)
1050	0,095	0,024

2.2 Fast Fourier Transform

The FFT is used to analyze the vibration response in the feature of vibration in the frequency domain. It will use to determine milling states. For the defined signal $x(t)$ in a sampling period T , with the data length is N , the FFT is expressed below⁽³⁰⁾ :

$$X(n) = \sum_{j=1}^N x(j) e^{-i2\pi(n-1)\frac{j-1}{J}} \quad (5)$$

FFT analysis was carried out to detect the chatter frequency (f_c), tooth-passing (f_T), natural frequency (f_n), and its harmonics are shown in **Fig. 6**, **Fig. 7**, and **Fig. 8**. For the tooth-passing frequency was calculated as follows^(25,31) :

$$f_T = \frac{n}{60} Nt \quad (6)$$

Where n and N_T are the spindle rotation and the number of flutes. The natural frequency is obtained from FRF.

2.3 Lubrication in Milling Process

Cutting fluid is used to improve milling capabilities so that the process is more efficient and better than without cutting fluid. Increased efficiency in milling will increase tool life, increase surface roughness, increase milling accuracy, reduce cutting forces, and reduce vibration in milling^(14,31). Low vibration in the milling process will have a positive impact because vibration in the milling process will cause tool wear and worst surface roughness^(14,32).

In this experiment, the influence of lubrication on vibration response and surface roughness in milling process was investigated. So that we choose the cutting conditions are dry cutting, wet cutting with coolant, and wet cutting with oil. In our experiment, coolant is a mixture of water and straight-cutting oil by comparison 50:50, or in some cases called soluble oil⁽⁶⁾. The properties of coolant as shown in table 2. Then, the oil we used in this experiment is engine lubrication of SAE 0W-20 fully synthetic motor oil.

Table 2. Coolant Properties – Dromus Oil

Appearance	Dark Amber, Clear
Specific Gravity @20°C	0.92
PH @5% Emulsion	8.9
Emulsion Type	Fine milky emulsion
Corrosion Test	30/1

2.4 Experimental Setup

Experiments were carried out on the KAFO K4122 CNC machine (dimensions of 4100 in length, 2200 mm in width, and 1000 mm in height) using Aluminum material to investigate the effect of lubrication and radial depth to vibration response and machined surface roughness of milling process. The type of aluminum used is 6061, which is one of the most commonly used due to its lightweight, durable, and functional properties⁽³³⁾. This material can also be used for wind turbine components^(6,7) and hydro turbine components materials^(8,10). A 12 mm of diameter end-mill with 4 flutes was used, the

specifications related to the specifications of the tools and the milling conditions used are shown in Table 3 and 4 below.

Table 3. Tool Parameters

Tools Parameters	Value
Diameter of Tool	12 mm
Number of Flutes	4
Helix Angle	30 degree
Material	Carbide
Tool Length	90 mm
Overhang	45 mm

Table 4. Milling Conditions

Cutting Conditions	Value
Spindle Rotation n (min^{-1})	2000
Feed per Tooth f_z	0.066 mm/tooth
Feed Speed f	500 mm/min
Axial DoC	12 mm
Radial DoC	1 mm, 2 mm, 3 mm

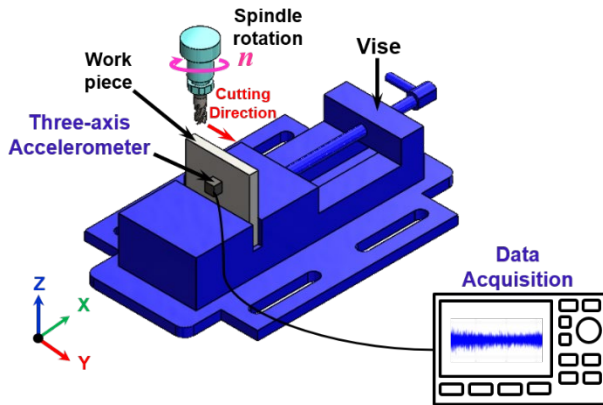


Fig. 3: Milling Test Experiment Setup

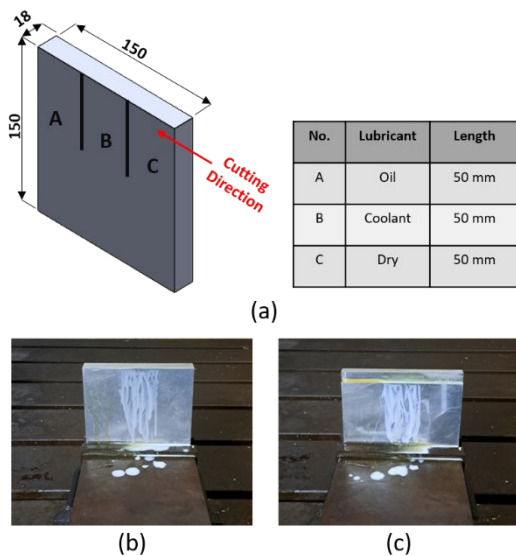


Fig. 4: Workpiece of Aluminum 6061 (a) illustration of lubrication method, (b) before milling, and (c) after milling

The dimension of the workpiece is 150 mm in length, 150 mm

in height, and 18 mm in width. The rotation of spindle is clockwise and the direction is displayed in Fig. 3. The milling experiments perform continuously from dry cutting to wet cutting. The surface of the workpiece divides into three different lubrication parameters with a length of 50 mm as shown in Fig. 4. In this experiment, coolant and oil are rubbed onto the material surface. Then, the milling experiment is repeated three times for each milling condition.

3. Results and Discussion

3.1 Acceleration Signal

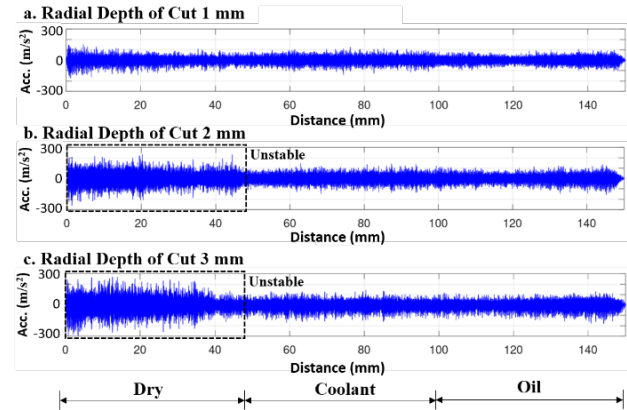


Fig. 5: Acceleration Signal acquired in milling test

As shown in the Fig. 5, the acceleration signal in milling test with 1 mm radial DoC has no significant difference. However, there was a significant difference for the 2 mm and 3 mm DoC, the signal amplitude was high in dry cutting but low in wet cutting. For dry cutting, it indicates an unstable condition of vibration. The existence of unstable vibrations will result in chatter. This chatter will cause the milling results to be worst^{13,20}.

3.2 FFT Spectra

Figs. 6, 7, and 8 show the frequency spectra by FFT for three variations of radial DoC 1 mm, 2 mm, and 3 mm, respectively. The FFT graph can identify the tooth-passing frequency (f_t), natural frequency (f_n), and chatter frequency (f_c). From Eq. 6, the value of tooth passing frequency (f_t) is 133 Hz. Then, the natural frequency can be obtained from the calculation of the FRF graph. The natural frequency f_n is 1050 Hz in this experiment as shown in Table 1.

In the FFT analysis, we separate the signals became three groups of cutting conditions: dry cutting, wet cutting with coolant, and wet cutting with oil. As shown in Fig. 6, the tooth-passing frequency, its harmonics, and the natural frequency were identified for DoC cut 1 mm and the amplitude is almost similar for three conditions. However, there is a large difference in amplitude between the dry cutting and wet cutting for DoC 2 mm and 3 mm as shown in Figs. 7 and 8. For DoC 2 mm in dry cutting (Fig. 7), it is found that the slightly chatter frequency begins to occurs at a frequency of 1000 Hz. Commonly, chatter occurred

close to the natural frequency^{20,31}). And, the results of FFT spectra showed that the chatter frequency identified before and has a lower amplitude than the natural frequency at 1050 Hz for DoC 2 mm. Furthermore, the chatter frequency amplitude become higher than the natural frequency for DoC 3 mm in dry cutting as shown in Fig. 8. Besides, for wet cutting with the same DoC, the chatter frequency was not found.

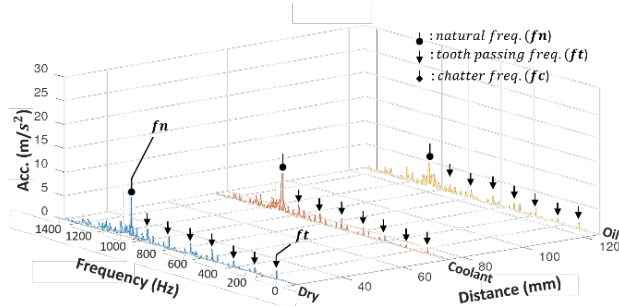


Fig. 6: Frequency spectra by FFT with Radial DoC 1 mm

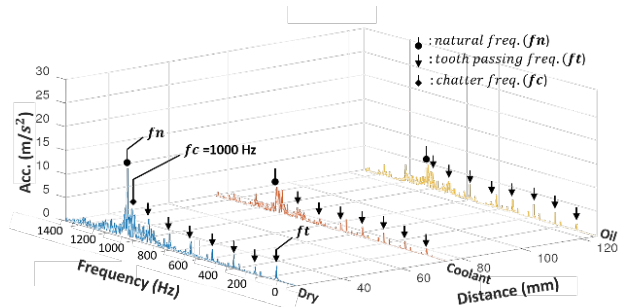


Fig 7: Frequency spectra by FFT with Radial DoC 2 mm

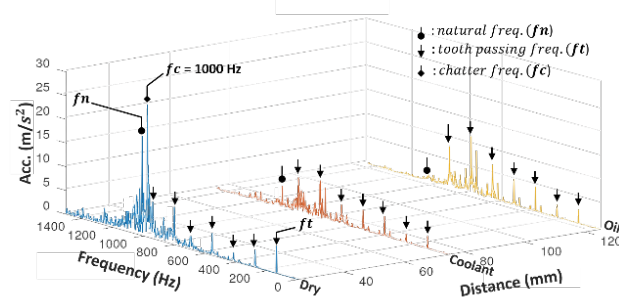


Fig. 8: Frequency spectra by FFT with Radial DoC 3 mm

3.3 Surface Roughness

Fig. 9 showed the roughness of the machined surface for dry cutting and wet cutting with coolant and oil. The surface roughness test is executed with portable surface roughness tester Mitutoyo SJ-301^{34,35}). The test is repeated three times for each milling condition. The photograph of the machined surface is taken using Keyence VHX 7000 with 100 times zooming^{36,37}). As shown in the Fig. 9, the roughness increases with radial DoC for dry cutting while it is almost constant with radial DoC for wet cutting. From these results, roughness in wet cutting tends to be stable than dry cutting. This shows that there is correlation

between the increase in chatter frequency amplitude to surface roughness.

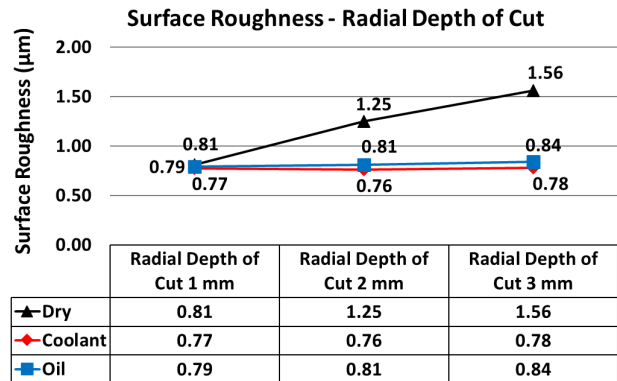


Fig 9: Surface Roughness of Aluminum Workpiece Surface

Figs. 10, 11, and 12 show the photographs of machined surfaces for aluminum workpieces after the milling process with 100 times magnification. Based on the photograph of the machined surface for Radial DoC 1 mm (Fig. 10), the pattern of cutting in the machined surface is nearly uniform and smooth for dry cutting, and wet cutting with coolant and oil. This is a similar trend with surface roughness values as shown in Fig. 9. For the Radial DoC 2 mm, the pattern of the machined surface for dry cutting looks rougher compared to wet cutting as shown in Fig. 11. The wet cutting with coolant has the best pattern in this experiment. Furthermore, for the Radial DoC 3 mm, the pattern of machined surface in milling under dry cutting shows the roughest surface in this experiment. The pattern of surface in milling under wet milling using coolant looks consistent with the three variations of Radial DoC and corresponds to the roughness values which tend to be stable as shown in Fig. 9. Milling process under wet cutting with coolant produces a smoother surface compared to milling under dry cutting^{16,31}).

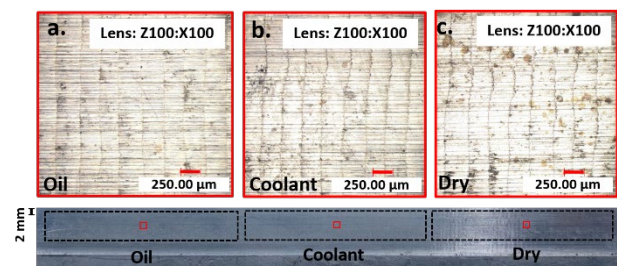


Fig 10: Photographs of Machined Surface for Radial DoC 1mm and 100 Times Magnification Image of the machined surface on (a) Wet Cutting with Oil, (b) Wet Cutting with Coolant, (c) Dry Cutting

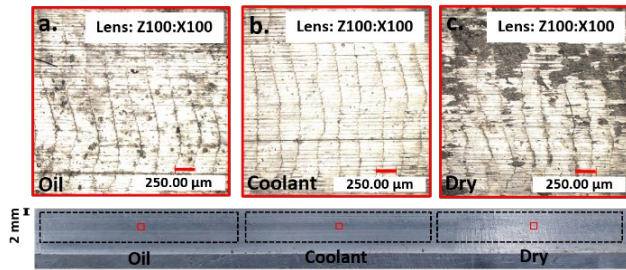


Fig. 11: Photographs of Machined Surface for Radial DoC 2mm and 100 Times Magnification Image of the machined surface on (a) Wet Cutting with Oil, (b) Wet Cutting with Coolant, (c) Dry Cutting

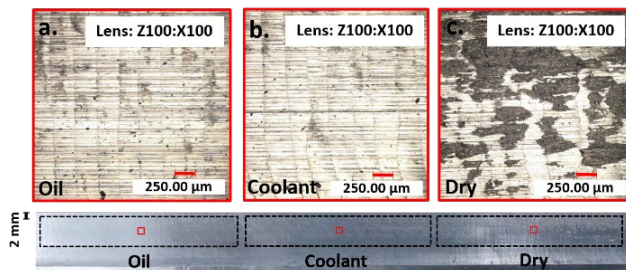


Fig 12: Photographs of Machined Surface for Radial DoC 3mm and 100 Times Magnification Image of the machined surface on (a) Wet Cutting with Oil, (b) Wet Cutting with Coolant, (c) Dry Cutting

4. Conclusion

In this paper, the influence of lubrication on vibration and surface roughness in milling process of aluminum 6061 was analyzed. The amplitude of acceleration signal for dry cutting is higher than wet cutting at every radial depth of cut. Based on vibration analysis by FFT, the chatter frequency occurs for dry cutting at radial depth of cut 2 and 3 mm while for wet cutting no chatter occurs at the same radial depth of cut. The radial depth of cut also affects the vibration, the greater the radial depth of cut causes an increase in vibration. The surface roughness results showed that wet cutting tends to be stable than dry cutting. For dry cutting, the roughness increases with radial depth of cut while for wet cutting it is almost constant with radial depth of cut. The results of the photograph, wet cutting has a better pattern of work surface than dry cutting, and the best of pattern is wet cutting with lubrication using coolant.

We conclude that the lubrication in milling of aluminum 6061 reduces the vibration response both in time and frequency domain, while no chatter detected. The surface roughness produced from wet cutting was smoother than dry cutting for every experiment depth of cut.

Acknowledgements

Thanks to Process and Manufacture Technology Research Center (PRTIPM), Research Organization for

Energy and Manufacture (OREM), National Research and Innovation Agency (BRIN) for supporting this research. All authors have contributed equally to this research work and discussed the results, implication and commented on the manuscript at all stages.

References

- 1) J. Langer, J. Quist, and K. Blok, "Review of renewable energy potentials in indonesia and their contribution to a 100% renewable electricity system," *Energies (Basel)*, **14** (21) (2021). doi:10.3390/en14217033.
- 2) P.J. Burke, J. Widnyana, Z. Anjum, E. Aisbett, B. Resosudarmo, and K.G.H. Baldwin, "Overcoming barriers to solar and wind energy adoption in two asian giants: india and indonesia," *Energy Policy*, **132** 1216–1228 (2019). doi:10.1016/j.enpol.2019.05.055.
- 3) R. of I. Ministry of Energy and Mineral Resources, "Handbook of Energy & Economic Statistics of Indonesia," 2021.
- 4) M. Maulidia, P. Dargusch, P. Ashworth, and F. Ardiansyah, "Rethinking renewable energy targets and electricity sector reform in indonesia: a private sector perspective," *Renewable and Sustainable Energy Reviews*, **101** 231–247 (2019). doi:10.1016/j.rser.2018.11.005.
- 5) M. Darbandi, A. Mohajer, A. Behrouzifar, R. Jalali, and G.E. Schneider, "Evaluating the effect of blade surface roughness in megawatt wind turbine performance using analytical and numerical approaches," (2014).
- 6) S. Ravikumar, V. Jaswanthvenkatram, Y.J.N.V. Sai Kumar, and S.M. Sohaib, "Design and Analysis of Wind Turbine Blade Hub using Aluminium Alloy AA 6061-T6," in: IOP Conf Ser Mater Sci Eng, Institute of Physics Publishing, 2017. doi:10.1088/1757-899X/197/1/012044.
- 7) I.P. Okokpujie, U.C. Okonkwo, C.A. Bolu, O.S. Ohunakin, M.G. Agboola, and A.A. Atayero, "Implementation of multi-criteria decision method for selection of suitable material for development of horizontal wind turbine blade for sustainable energy generation," *Heliyon*, **6** (1) (2020). doi:10.1016/j.heliyon.2019.e03142.
- 8) W.S. Ebhota, and F. Inambao, "Design basics of a small hydro turbine plant for capacity building in sub-saharan africa," *African Journal of Science, Technology, Innovation and Development*, **8** (1) 111–120 (2016). doi:10.1080/20421338.2015.1128039.
- 9) S. Kathiresan, K.S. Sreenivasan, R. Muthukrishnan @sriram, and M. Chandrasekaran, "Experimental investigation of lubrication system of milling operation on aluminum alloy 6060," *IOSR Journal of Mechanical and Civil Engineering*, 29–45 (2014). www.iosrjournals.org.
- 10) P. Sritram, W. Treedet, and R. Suntivarakorn, "Effect

- of turbine materials on power generation efficiency from free water vortex hydro power plant,” in: IOP Conf Ser Mater Sci Eng, Institute of Physics Publishing, 2015. doi:10.1088/1757-899X/103/1/012018.
- 11) O.E. Scott-Emuakpor, H. Shen, T. George, and C. Cross, “An energy-based uniaxial fatigue life prediction method for commonly used gas turbine engine materials,” *J Eng Gas Turbine Power*, **130** (6) (2008). doi:10.1115/1.2943152.
 - 12) I.P. Okokpujie, and L.K. Tartibu, “Aluminum alloy reinforced with agro-waste, and eggshell as viable material for wind turbine blade to annex potential wind energy: a review,” *Journal of Composites Science*, **7** (4) (2023). doi:10.3390/jcs7040161.
 - 13) G. Quintana, and J. Ciurana, “Chatter in machining processes: a review,” *Int J Mach Tools Manuf*, **51** (5) 363–376 (2011). doi:10.1016/j.ijmachtools.2011.01.001.
 - 14) W. Zhong, D. Zhao, and X. Wang, “A comparative study on dry milling and little quantity lubricant milling based on vibration signals,” *Int J Mach Tools Manuf*, **50** (12) 1057–1064 (2010). doi:10.1016/j.ijmachtools.2010.08.011.
 - 15) A.K. Srivastava, M. Maurya, A. Saxena, N.K. Maurya, and S.P. Dwivedi, “Statistical optimization by response surface methodology of process parameters during the cnc turning operation of hybrid metal matrix composite,” *Evergreen*, **8**(1) 51–62 (2021). doi:10.5109/4372260.
 - 16) L.J. Drambi, and Y. Mohammed, “Effects of neem, straight and soluble oils as cutting fluids on tool wearing during metalwork practicals in technical colleges in kano state, nigeria,” *International Journal of Engineering Technologies and Management Research*, **6** (6) 166–177 (2020). doi:10.29121/ijetmr.v6.i6.2019.405.
 - 17) A.C. Opia, M.K.A. Hamid, S. Syahrullail, A.I. Ali, C.N. Johnson, I. Veza, M.I. Izmi, C.D.Z. Hilmi, and A.B. Abd Rahim, “Tribological behavior of organic anti-wear and friction reducing additive of zddp under sliding condition: synergism and antagonism effect,” *Evergreen*, **9**(2) 246–253 (2022). doi:10.5109/4793628.
 - 18) S. Abhijit, C. Satyajit, and B.K. Goutam, “Investigation of effect of cnc milling parameters on cylindricity and perpendicularity of milled circular pockets using cmm,” *Evergreen*, **9**(3) 745–751 (2022). doi:10.5109/4843108.
 - 19) S. Maslo, B. Menezes, P. Kienast, P. Ganser, and T. Bergs, “Improving dynamic process stability in milling of thin-walled workpieces by optimization of spindle speed based on a linear parameter-varying model,” *Procedia CIRP*, **93** 850–855 (2020). doi:10.1016/j.procir.2020.03.092.
 - 20) A. Susanto, M. Azka, K. Yamada, K. Sekiya, P. Novia, R. Tanaka, and M.D. Prasetyo, “Analysis of Transient Signal using Hilbert-Huang Transform for Chatter Monitoring in Turning Process,” in: International Conference on Information Technology, Information Systems and Electrical Engineering, 2019: pp. 26–30.
 - 21) Y. Altintas, G. Stepan, D. Merdol, and Z. Dombovari, “Chatter stability of milling in frequency and discrete time domain,” *CIRP J Manuf Sci Technol*, **1** (1) 35–44 (2008). doi:10.1016/j.cirpj.2008.06.003.
 - 22) A. Comak, and E. Budak, “Modeling dynamics and stability of variable pitch and helix milling tools for development of a design method to maximize chatter stability,” *Precis Eng*, **47** 459–468 (2017). doi:10.1016/j.precisioneng.2016.09.021.
 - 23) M. Azka, K. Mani, K. Yamada, M. Al Huda, R. Tanaka, and K. Sekiya, “Influence of Tool Inclination on Chatter Vibration in Ball-End Milling,” in: The Proceedings of Conference of Chugoku-Shikoku Branch, 2018.
 - 24) M. Azka, K. Yamada, M. Al Huda, R. Tanaka, and K. Sekiya, “Influence of tool posture and position on stability in milling with parallel kinematic machine tool,” *International Journal of Precision Engineering and Manufacturing*, **21** (12) 2359–2373 (2020). doi:10.1007/s12541-020-00416-7.
 - 25) M. Azka, K. Yamada, M. Al Huda, K. Mani, R. Tanaka, and K. Sekiya, “Hilbert-huang transform analysis of machining stability in ball-nose end-milling of curved surface,” *International Journal of Automation Technology*, (2020). doi:10.20965/IJAT.2020.P0500.
 - 26) A. Susanto, C.H. Liu, K. Yamada, Y.R. Hwang, R. Tanaka, and K. Sekiya, “Application of hilbert–huang transform for vibration signal analysis in end-milling,” *Precis Eng*, **53** 263–277 (2018). doi:10.1016/j.precisioneng.2018.04.008.
 - 27) M. Akbulut, and H. Erol, “Damping layer application in design of robust battery pack for space equipment,” *Applied Acoustics*, **150** 81–88 (2019). doi:10.1016/j.apacoust.2019.01.036.
 - 28) D. Pop, L. Morar, E. Campean, and T. Ionela, “EXPERIMENTAL modal analysis of a milling machine spindle -tool holder - cutter assembly,” *ACTA TECHNICA NAPOCENSIS*, **55** (1) 233–238 (2021).
 - 29) Z. Li, Z. Wang, and X. Shi, “Fast prediction of chatter stability lobe diagram for milling process using frequency response function or modal parameters,” *International Journal of Advanced Manufacturing Technology*, **89** (9–12) 2603–2612 (2017). doi:10.1007/s00170-016-9959-4.
 - 30) A. Susanto, C.H. Liu, K. Yamada, Y.R. Hwang, R. Tanaka, and K. Sekiya, “Milling process monitoring based on vibration analysis using hilbert-huang transform,” *International Journal of Automation Technology*, **12** (5) 688–698 (2018). doi:10.20965/ijat.2018.p0688.
 - 31) M.A. Xavier, and M. Adithan, “Determining the

- influence of cutting fluids on tool wear and surface roughness during turning of aisi 304 austenitic stainless steel,” *J Mater Process Technol*, **209** (2) 900–909 (2009). doi:10.1016/j.jmatprotec.2008.02.068.
- 32) Md Sazzad Hossain Ador, S. Kabir, F. Ahmed, F. Ahmad, and S. Adil, “Effects of minimum quantity lubrication (mql) on surface roughness in milling al alloy 383 / adc 12 using nano hybrid cutting fluid,” *Evergreen*, **9**(4) 1003–1020 (2022). doi:10.5109/6625790.
- 33) S.P. Dwivedi, M. Maurya, and S.S. Chauhan, “Mechanical, physical and thermal behaviour of sic and mgo reinforced aluminium based composite material,” *Evergreen*, **8**(2) 318–327 (2021). doi:10.5109/4480709.
- 34) O. Unsal, and N. Ayilmis, “Variations in compression strength and surface roughness of heat-treated turkish river red gum (eucalyptus camaldulensis) wood,” *Journal of Wood Science*, **51** (4) 405–409 (2005). doi:10.1007/s10086-004-0655-x.
- 35) D.S. Korkut, and B. Guller, “The effects of heat treatment on physical properties and surface roughness of red-bud maple (acer trautvetteri medw.) wood,” *Bioresour Technol*, **99** (8) 2846–2851 (2008). doi:10.1016/j.biortech.2007.06.043.
- 36) M.A. Rahman, M.Z. Islam, L. Gibbon, C.A. Ulven, and J.J. La Scala, “3D printing of continuous carbon fiber reinforced thermoset composites using uv curable resin,” *Polym Compos*, **42** (11) 5859–5868 (2021). doi:10.1002/pc.26266.
- 37) T. Ouyang, Y. Shen, R. Yang, L. Liang, H. Liang, B. Lin, Z.Q. Tian, and P.K. Shen, “3D hierarchical porous graphene nanosheets as an efficient grease additive to reduce wear and friction under heavy-load conditions,” *Tribol Int*, **144** (2020). doi:10.1016/j.triboint.2019.106118.