

Experimental Investigation on the Mechanical and Abrasive Properties of Ceramic Particulate Filled Basalt Fiber Reinforced Epoxy Polymer Composites

Meena, Manmohan
Mechanical Engineering Department, NITTTR Chandigarh

B.S. Pabla
Mechanical Engineering Department, NITTTR Chandigarh

Sharma, Vikas
Mechanical Engineering Department, Malaviya National Institute of Technology

Saraswat, Praveen
Department of Mechanical Engineering, Swami Keshvanand Institute of Technology, Management and Gramothan

<https://doi.org/10.5109/7160922>

出版情報 : Evergreen. 10 (4), pp.2645-2653, 2023-12. 九州大学グリーンテクノロジー研究教育センター
バージョン :
権利関係 : Creative Commons Attribution 4.0 International

Experimental Investigation on the Mechanical and Abrasive Properties of Ceramic Particulate Filled Basalt Fiber Reinforced Epoxy Polymer Composites

Manmohan Meena^{1,*}, B.S. Pabla¹, Vikas Sharma², Praveen Saraswat³

¹Mechanical Engineering Department, NITTTR Chandigarh, India

²Mechanical Engineering Department, Malaviya National Institute of Technology, Jaipur

³Department of Mechanical Engineering, Swami Keshvanand Institute of Technology, Management and Gramothan, Jaipur

E-mail: meena.manmohan@gmail.com

(Received March 20, 2023; Revised December 19, 2023; accepted December 19, 2023).

Abstract: The properties of Composite Materials can be consequentially influenced by addition of particulate fillers, which can lead to tailor made specific uses of these composites. Composites materials are widely used materials in automobiles, aviation, defense as well as sport goods industries, due to their properties being at par with traditional engineering materials and sometimes superior as well. In this study, basalt fiber laminates were fabricated by addition of a particulate filler namely Marble Dust, by conventional hand lay-up method. Further, these composite laminates were analyzed for their mechanical (tensile, flexural, impact strength, hardness and density) and three body abrasive wear performance. The analysis indicated that strong impact on properties of composites after the addition of particulate fillers. Moreover, this study also focuses on use of waste Marble dust and stone dust such as Kota Stone Dust for use as particulate filler in composites.

Keywords: Composites, Basalt fiber, Marble Dust, Three body abrasive wear, Flexural strength

1. Introduction

A composite material is an interaction of mediums, i.e. a fiber and a matrix; and its properties can be impacted by inclusion of one more medium in the interphase in form of a particulate filler. When combined, they derive a conglomeration of properties of all the elements which they don't possess when acting alone¹.

A vibrant attribute of composite materials that makes them very pivotal and optimistic engineering material is their trait to tailor make their characteristic properties. This can be achieved via changing of fiber orientation, stacking and layering, hybridization, use of various matrices or by introduction of particulate filler materials in the interphase^{2, 3}. With the possibility of various changes of properties as well as functionalities, composite materials create a very particular niche among available engineering materials. All these traits opens up a wide future scope and material science applications for composite materials as well as opens up a chance to replace orthodox materials currently under distinct/specific use⁴⁻⁷.

Basalt fiber is one of the most basic yet very functional fiber material used in composites. It provides a wide range of modifications to a composite simply by virtue of change in fiber orientation, weave matting type and

weight implications. All these factors play a very vast role in characteristic properties of Basalt fiber composites. Furthermore, various recycled Basalt fiber types are making an entry into already available materials making path for more renewable and environment friendly options for future use⁸⁻¹¹.

The matrix material influences the properties of a material manufactured by composites. It not only secures the fiber reinforcement, transfers load between fibers, but also provides the composite with its penultimate shape and determines its surface grade and finish¹²⁻¹³. In accordance with this, epoxy resin, which is a polymer matrix provides composite materials with a vast variety of properties; i.e. superior mechanical, thermal and electrical properties¹⁴⁻¹⁵. Thus epoxy resin creates a very specific niche in high performance applications such as aviation parts, sports equipment's, body armour etc.¹⁶⁻¹⁷.

Particulate filler particles are also introduced in the composite interphase to elevate various properties¹⁸. Inclusion of filler particles improves toughness, stiffness, hardness; thermal properties for a composite material depending upon its individual attribute¹⁹. Solid particulate fillers such as titanium oxide, aluminum oxide, and waste Marble dust such as Kota stone dust are being used these days to consequentially refine mechanical properties, wear resistance, temperature & water

resistance for various polymer matrix composites²⁰⁻²¹). Composites with particulate fillers have also shown notable improvement in real time operational conditions²²⁻²³).

Titanium oxide (TiO₂) as a filler material impacts the mechanical properties of a composite²⁴). While, wear resistance, strength, stiffness, temperature & chemical resistance for a composite material also increases when aluminum oxide (Al₂O₃) is used as filler²⁵).

Waste marble and stone dust such as Kota stone powder, when used as particulate filler have also shown a notable impact on properties of composites. Moreover, composites have shown greater temperature and chemical resistance when Kota Stone Dust was used as filler²⁶). Moreover, the particulate fillers generated as a water byproduct of various marble and stone industries can be used to replace many conventional particulate types of filler currently under practical use; simply because of the fact that this process is more ergonomically. As well as this practice can have a positive environmental effect and can be a solution to the waste problems related with stone and marble industries²⁷). Various industries have already demonstrated the noteworthiness of particulate fillers in composite materials vastly due to the strong impact it depicts on material properties. Furthermore, they can be effectively utilized to tailor make the composite properties as per the user and practical requirement²⁸⁻³¹). The implementation of composite materials in aerospace & aviation, automobile, sports and biomedical applications have been on the rise since past few years, and with continuous research and experimentation, this trend of using composites in place of traditional materials is only going to escalate in the fore-coming years³²⁻³⁴). The objective of this analysis is to scrutinize the impact of particulate fillers i.e. TiO₂, Al₂O₃ and especially Marble Dust on Basalt fiber polymer composites³⁵⁻³⁶). For this purpose, hand lay-up technique was used to fabricate composites³⁷⁻³⁸). The particulate fillers were added as 8%, 16% & 24% of fiber weight ratio. The samples were then analyzed for tensile, compressive and hardness inspection while their toughness and density were depicted using standard theoretical approach³⁹⁻⁴¹). Despite all the advancements and research work in composite's material science, the impact of particulate filler generated as a by-product from stone and marble industry is yet to be researched rigorously. Therefore, this study and research work is mainly focused on role of Marble Dust as particulate filler in composite materials.

2. Experimental Procedure

2.1 Materials

Basalt fiber composites of 4 variations were put together for this research work. Plain weave basalt fiber of 600GSM was procured from Carbon Black Composites. Epoxy laminating resin and hardener combination of 2:1 mixture ratio was also supplied by Carbon Black

Composites and is used as the matrix material. Particulate filler were used for composite fabrication, i.e. Marble dust which was sieved to the particle size of 420 microns prior to use. Marble Stone dust was collected from Shree Ram Industries. The 4 composites prepared for this study are identified as EBM 0, EBM 8, EBM 16, and EBM 24. The exact compositions and designations are mentioned in Table 1.

2.2 Fabrication of composite

Basalt fiber composite laminates were prepared and were isolated for 48 hours for proper curing at room temperature. Fiber and epoxy matrix were kept in equal parts i.e. fiber loading was kept at 50% for all samples. No particulate filler was added in the EBM 0 composite. Thereafter, other composite samples contained particulate fillers in 8%, 16% & 24% epoxy weight ratios respectively, thus making up a total of 4 composite laminates. The laminates EBM 8, EBM 16 & EBM 24 contained marble dust as filler in 8%, 16% & 24% proportions respectively. Diamond cutter trimmer is used for identification and testing of samples and specimens.

3. Physical and Mechanical Testing

3.1 Hardness

The laminates were analyzed for surface toughness using Rockwell Hardness Scale. This test wedges a conical shaped perforator of steel or diamond against a test specimen and assesses the hardness as indexed by developed indentation depth. Higher HR value represents hard material. In this test, a smaller load of 10 Kgf is first executed, and the test dial is set to zero. Then to create a complete indentation, a load of 60 Kgf is executed. The higher load is reverted to the smaller load, and the change in depth is measured. The perforator is generally 1.588 mm in caliber, and for composite materials, this test was processed on the HRF scale of the Rockwell Hardness Test.

3.2 Density and Voids Content

The manufactured composite comprises of Matrix material, including fibre and embedded with particulate filler material.

Therefore, the theoretical density (ρ_{ct}) is analysed via Eq. 1.1 (Agarwal and Broutman):

$$\rho_{ct} = \frac{1}{\frac{P_{fr}}{\rho_{fr}} + \frac{P_{mm}}{\rho_{mm}} + \frac{P_{pfm}}{\rho_{pfm}}} \quad (1.1)$$

Where,

P = weight fraction

ρ = density of the ingredients

pfm = particulate filler materials

fr = fiber reinforcement

mm = matrix material

Simple water immersion method is used to analyze the experimental density (ρ_{ex}) of the sample and voids fraction (Δv) present is normalized by using Eq. 1.2 [19].

$$\Delta v = \left[\frac{\rho_{ct} - \rho_{ex}}{\rho_{ct}} \right] \quad (1.2)$$

3.3 Tensile and Flexural Strength

The tensile strength (T.S.) of composite specimen is calculated by Universal Testing Machine (UTM). The tensile test is carried on specimen of specific sizes as per ASTM standard D3039. A uniaxial load is provided on both the edges of sample with cross head velocity of 2 mm/min during analysis. The tensile strength is calculated by using the achieved results.

Flexural test standard follows ASTM D7264. Flexural test sample's dimension is 80 mm × 10 mm × 4 mm. Eqs. 1.3 And 1.4 are used to determine Flexural strength and flexural modulus respectively.

$$F S = \frac{3WD}{2bt^2} \quad (1.3)$$

$$F M = \frac{D^3 m}{4bt^3} \quad (1.4)$$

Where,

W = Maximum applied load

D = Span length

m = Slope of tangent

b = sample width

t = sample thickness

3.4 Impact Strength

Pendulum type impact tester is utilised according to ASTM D256 specification to calculate Impact energy.

3.5 Three-Body Abrasive Wear Analysis

As per ASTM G65 specifications, sample is tested for three-body abrasive wear behaviour. Figure 1 shows the setup for this and Input variables are shown in Table 2. The rectangular moulds with size of 75 × 25 × 12 mm³ is used. From the nozzle, particles are flown into the hopper at the feed speed of 255 ± 5 g/min². The weights are noted prior and post of the experiment by use of electronic balance and then change is noted. Using Eq. 1.5 Abrasive behaviour is measured¹⁹.

$$W_a = \frac{\Delta V}{\rho \times W_n \times S_d} \quad (\text{mm}^3/\text{N-m}) \quad (1.5)$$

Where,

W_a = Abrasive wear rate (mm³/N-m)

ρ = Experimental density of composite (g/cc)

W_n = Normal load (N)

S_d = Sliding distance (m)

3.6 Practical based on Taguchi's design

Conventional method needs a large number of experiments for various inputs at various levels. So by using Taguchi's design, number of recordings can be reduced for finding optimum value. Table 2 shows the i/p control factors at various stages. From this experiment, parameter can be identified which affects wear characteristics. Simulation using Minitab 17 software was done. There are 4 input variable and 4 stages, so L₁₆ (4⁴ = 16) matrix is used and output are changed into signal-to-noise (S/N) value. For minimum wear characteristics, smallest S/N value is used.

$$\frac{S}{N} = -10 \log \frac{1}{n} \sum Y^2 \quad (1.6)$$

Where, n represent number of observations, and Y represent observed data.

After that, analysis of variance (ANOVA) is used to find optimal value. By using ANOVA and S/N ratio optimal level and its effect can be identified.

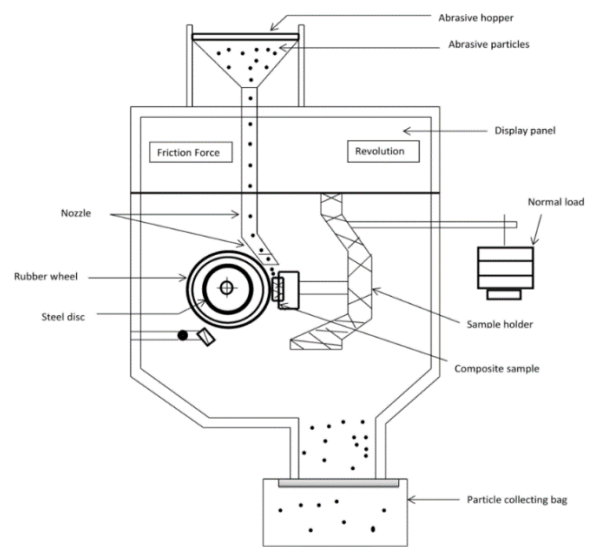


Fig. 1: Abrasion experiment setup

4. Results and Discussions

4.1 Density and void content characteristics

The concept behind evaluation of density and void content of composites is that how the composite performs when subjected to mechanical tests. Figure 2 and Table 3 shows the results of experimental density and void content

of unfilled and marble dust filled basalt fiber-reinforced epoxy composites. Density of composites found to increase with increase in filler content in the range of 1.3129-1.4226 g/cm³. Marble dust filler have higher density than the epoxy resin; this may be the reason of increasing in density of composites with addition of marble dust filler.

Table 1: Identification & Detailed Composition of Composites

| Designation | Composition |
|-------------|---|
| EBM 0 | Epoxy + Basalt Fiber |
| EBM 8 | Epoxy + Basalt Fiber + 8 wt. % Marble dust |
| EBM 16 | Epoxy + Basalt Fiber + 16 wt. % Marble dust |
| EBM 24 | Epoxy + Basalt Fiber + 24 wt. % Marble dust |

Table 2: Abrasion experiment setup variables

| Control factors | Levels | | | | Units |
|---------------------|--------|------|------|------|-------|
| | I | II | III | IV | |
| A: Filler loading | 0 | 8 | 16 | 24 | wt. % |
| B: Normal load | 20 | 40 | 60 | 80 | N |
| C: Sliding distance | 500 | 1000 | 1500 | 2000 | m |
| D: Abrasive size | 100 | 200 | 300 | 400 | μm |

Table 3: Theoretical and actual density of the composites

| Characteristics | Composite | | | |
|-----------------------------|-----------|--------|--------|--------|
| | EBM 0 | EBM 8 | EBM 16 | EBM 24 |
| Experimental density (g/cc) | 1.3129 | 1.3475 | 1.3875 | 1.4226 |
| Theoretical density (g/cc) | 1.3374 | 1.3865 | 1.4394 | 1.4961 |
| Voids content (%) | 1.70 | 2.62 | 3.37 | 4.60 |
| Micro-hardness (Hv) | 30 | 33 | 37 | 43 |

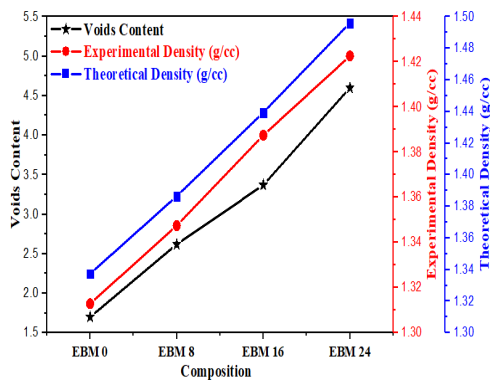


Fig. 2: Theoretical, actual density & void content of composites

4.2 Hardness

Hardness of composites is the ability to resist indentation. Harder surface of composite indicates the better wear resistance of its. Generally, the fiber reinforcement improves the hardness of composites, but particulate filler improves the hardness of composites higher than fiber reinforcement. The variation in hardness with marble dust filler of sample are shown in Figure 3 & Table 3. Hardness of sample rises as marble dust percentage rises from 0 to 24 wt. %. Sample with 24 wt. % marble dust filler has hardness value of 43 which is maximum.

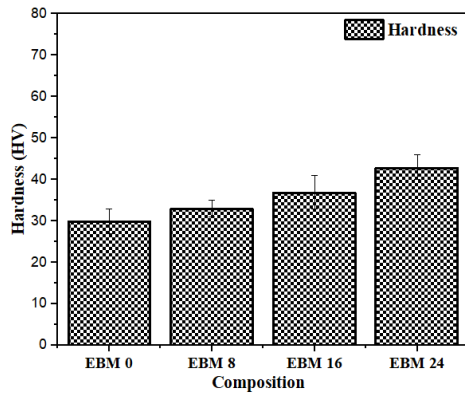


Fig. 3: Hardness of filled and unfilled sample

4.3 Tensile strength

The ratio of the maximum weight and cross section area of composite indicates ultimate tensile strength of material. Tensile strength of polymer matrix can be enhanced by fibre reinforcement. The inclusion of particulate filler enhances the tensile load bearing capacity of composite as well as tensile strength and modulus of composites. Graph shows the variation of tensile strength with marble dust content. Composite with 16 wt. % marble dust shows highest tensile strength (56.33 MPa) which is 39.31% higher than virgin (EBM 0) composite, respectively. Further, addition of marble dust content (24 wt. %) decrease the value of tensile strength.

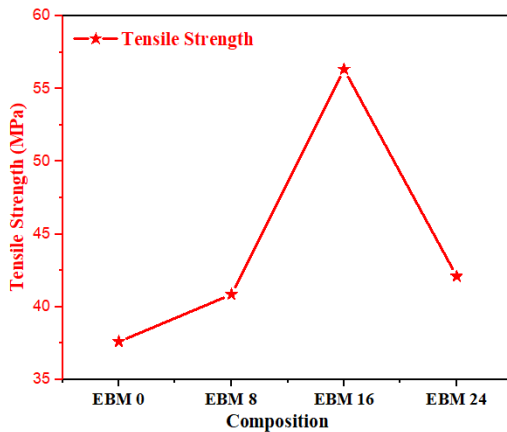


Fig. 4: Variation in tensile strength of composites

4.4 Flexural strength

There are many important properties of fiber/filler reinforced polymer composites one of them is flexural strength. Composites are failing during bending due to high ratio value of lateral dimension and thickness. The flexural strength of marble dust-filled basalt-epoxy composites are depicted in Figure 5 and Table 4. Flexural strength of composite increased marble dust reinforcement percentage up to 16 wt. %; more

increment in dust percent decreases the flexural strength of composites. Basalt-epoxy composite with 16 wt.% marble dust (EBM 16) shows maximum flexural strength (155.8 MPa) which is 13.31% higher than virgin composite (EBM 0), respectively.

4.5 Impact strength

Figure 6 and Table 4 represents the impact strength of prepared composite samples with rise in the percentage of marble dust filler. Impact strength rises with more addition of filler up to 16 wt. %, and then it starts decreasing till 24 wt. % marble dust.

4.6 Taguchi's design and ANOVA analysis

With the help of L16 Taguchi's orthogonal array abrasive behaviour is analysed and the S/N values of composite samples is shown in Table 5 and Figure 7.

The overall average value for S/N ratio for all experiments is 40.59 dB as shown in Figure 7.

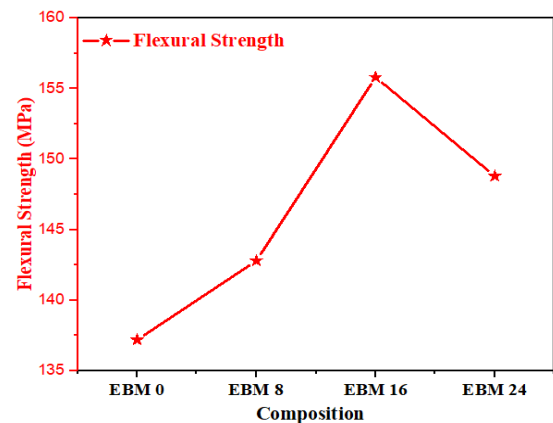


Fig. 5: Variation in flexural strength of composites

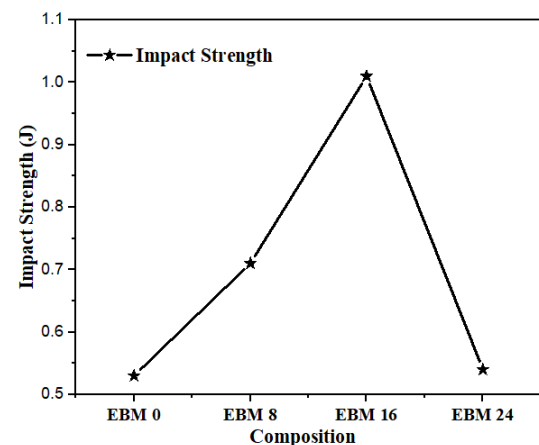


Fig. 6: Variation in impact strength of composites

Table 6 represents the ranking order of input variable. From Table 6 it is concluded that the descending order of effect on abrasive behaviour of sample is sliding distance, normal load, filler loading, and abrasive size.

The ANOVA analysis results are shown in Table 7. As per ANOVA analysis for various composition of Marble dust filled basalt-epoxy samples, ranking of the control variables in ascending order are abrasive size, filler loading, normal load and Sliding distance.

5. Conclusions

On the basis of work carried out in this study the following important outcomes were made

- When particulate filler content in composite increases, its hardness increases.

- At 16 wt. % of marble dust filler the basalt epoxy composite shows the maximum tensile strength, flexural strength and impact strength.
- In the Taguchi experimental analysis, the ascending order of effect of input variable are: sliding distance, normal load, filler loading, and abrasive size.

Table 4: Characteristics of unfilled and filled basalt-epoxy sample

| Characteristics | Unit | Composite | | | |
|--------------------------|------|-----------|-------|--------|--------|
| | | EBM 0 | EBM 8 | EBM 16 | EBM 24 |
| Tensile Strength | MPa | 37.61 | 40.86 | 56.33 | 42.1 |
| Flexural Strength | MPa | 137.2 | 142.8 | 155.8 | 148.8 |
| Impact Strength | J | 0.53 | 0.71 | 1.01 | 0.54 |

Table 5: Taguchi's L16 orthogonal array based design

| Exp. No. | A: Filler Loading | B: Normal Load | C: Sliding distance | D: Abrasive Size | Abrasive Wear Rate | S/N Ratio (dB) |
|----------|-------------------|----------------|---------------------|------------------|--------------------|----------------|
| 1 | 0 | 20 | 500 | 100 | 0.0107580 | 39.3654 |
| 2 | 0 | 40 | 1000 | 200 | 0.0100679 | 39.9412 |
| 3 | 0 | 60 | 1500 | 300 | 0.0061733 | 44.1897 |
| 4 | 0 | 80 | 2000 | 400 | 0.0062460 | 44.0879 |
| 5 | 8 | 20 | 1000 | 300 | 0.0105009 | 39.5755 |
| 6 | 8 | 40 | 500 | 400 | 0.0350950 | 29.0951 |
| 7 | 8 | 60 | 2000 | 100 | 0.0099539 | 40.0401 |
| 8 | 8 | 80 | 1500 | 200 | 0.0062982 | 44.0156 |
| 9 | 16 | 20 | 1500 | 400 | 0.0029356 | 50.6461 |
| 10 | 16 | 40 | 2000 | 300 | 0.0076723 | 42.3015 |
| 11 | 16 | 60 | 500 | 200 | 0.0102409 | 39.7932 |
| 12 | 16 | 80 | 1000 | 100 | 0.0089076 | 41.0048 |
| 13 | 24 | 20 | 2000 | 200 | 0.0040720 | 47.8039 |
| 14 | 24 | 40 | 1500 | 100 | 0.0104427 | 39.6238 |
| 15 | 24 | 60 | 1000 | 400 | 0.0199987 | 33.9800 |
| 16 | 24 | 80 | 500 | 300 | 0.0199658 | 33.9942 |

Table 6: Input variable ranking order of effect

| Level | A: Filler Loading | B: Normal Load | C: Sliding Distance | D: Abrasive Size |
|-------|-------------------|----------------|---------------------|------------------|
| 1 | 41.90 | 44.35 | 35.56 | 40.01 |
| 2 | 38.18 | 37.74 | 38.63 | 42.89 |
| 3 | 43.44 | 39.50 | 44.62 | 40.02 |
| 4 | 38.85 | 40.78 | 43.56 | 49.45 |
| Delta | 5.25 | 6.61 | 9.06 | 3.44 |
| Rank | 3 | 2 | 1 | 4 |

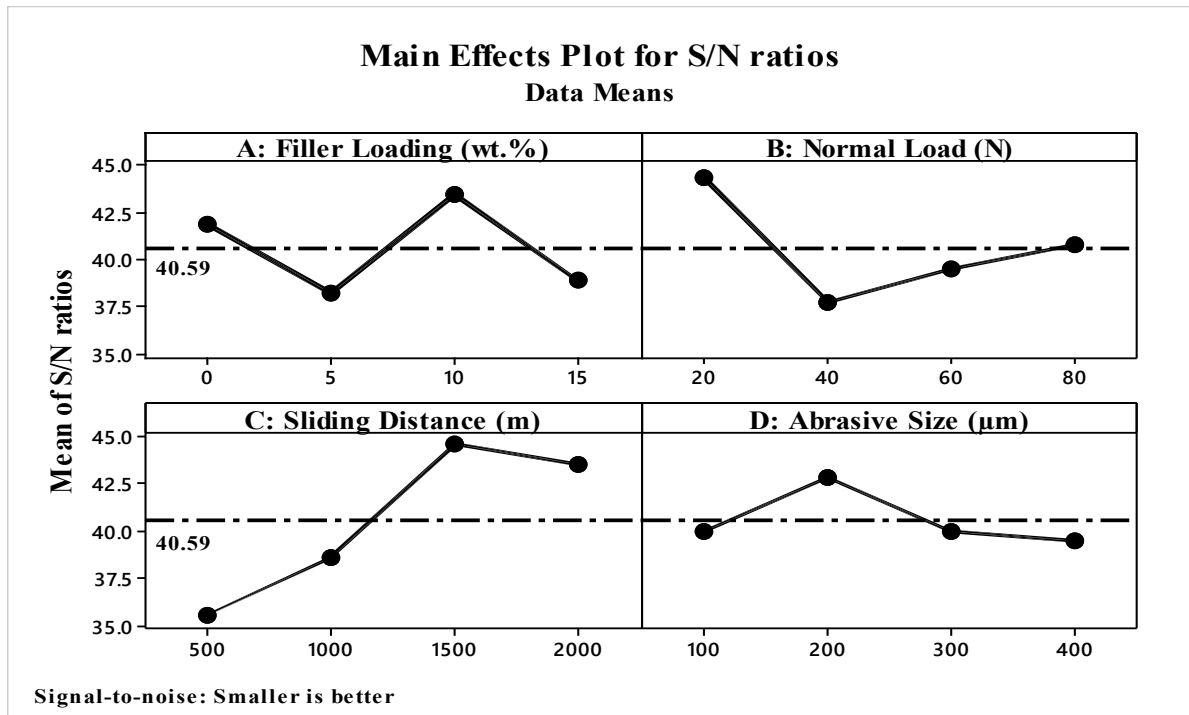


Fig. 7: Effect of input variable on abrasive behaviour of marble dust Filled BFRP samples

Table 7: ANOVA analysis for abrasive behaviour

| Input control factors | DF | Adj. SS | Adj. MS | F-value | p-value | P (%) |
|-----------------------|----|---------|---------|---------|---------|-------|
| A: Filler Loading | 3 | 74.537 | 24.846 | 22.97 | 0.014 | 17.85 |
| B: Normal Load | 3 | 93.847 | 31.282 | 28.92 | 0.010 | 22.48 |
| C: Sliding Distance | 3 | 216.733 | 72.244 | 66.78 | 0.003 | 51.93 |
| D: Abrasive Size | 3 | 28.984 | 9.661 | 8.93 | 0.053 | 6.94 |
| Error | 3 | 3.245 | 1.082 | | | |
| Total | 15 | 417.346 | | | | |

References

- 1) TP Sathishkumar, S Satheeshkumar, J Naveen. Glass fiber-reinforced polymer composites - a review, Journal of Reinforced Plastics and Composites, 2014, Volume 33, Issue 13, Pages 1258-1275. DOI: 10.1177/0731684414530790.
- 2) Amar Patnaik, Alok Satyapathy, SS Mahapatra, RR Dash. A comparative study on different ceramic fillers affecting mechanical properties of glass-pollster composites, Journal of Reinforced Plastics

- and Composites, 2009, Volume 28, Issue 11, Pages 1305-1314. DOI:10.1177/0731684407086589.
- 3) Alok Satapathy, Amar Patnaik, Manoj Kumar Pradhan. A study on processing, characterisation and erosion behaviour of fish (labeo-rohita) scale filled epoxy matrix composites, Materials and Design, 2009, Volume 30, Pages 2359-2371. DOI:10.1016/j.matdes.2008.10.033.
- 4) SS Godara, PK Mahato. Potential applications of hybrid nano composites, Materials Today: Proceedings, 2019, Volume 18, Pages 5327-5331. DOI:10.1016/j.matpr.2019.07.557.
- 5) J Karger-Kocsis, Haroon Mahmood, Alessandro Pegoretti. Recent advances in fiber/matrix interphase engineering for polymer composites, Progress in Materials Science, 2015, Volume 73, Pages 1-43. DOI:10.1016/j.pmatsci.2015.02.003
- 6) K Friedrich. Polymer composites for tribological applications, Advanced Industrial and Engineering Polymer Research, 2018, Pages 1-37. DOI:10.1016/j.aiepr.2018.05.001.
- 7) Mushtaque Lakho, M Tarique Bhatti, Altaf Hussain Rajpar, Manthar Ali Khoso, Ishfaq Ali Qazi. Comparative tensile behaviour study of locally developed jute reinforced composite materials with conventional composite materials, Advances in Materials and Processing Technologies, 2018, Volume 4, Issue 3, Pages 370-377. DOI:10.1080/2374068X.2018.1440867.
- 8) MS Wazery, MI Elamy, SH Zoalfakar. Mechanical properties of glass fiber reinforced polymer composites, International Journal of Applied Science and Engineering, 2017, Volume 14, Issue 3, Pages 121-131. DOI:10.6703/IJASE.2017.14(3).121.
- 9) K Devendra, T Rangaswamy. Strength characterisation of e-glass fiber reinforced epoxy composites with filler materials, Journal of Minerals and Materials Characterisation and Engineering, 2013, Volume 1, Pages 353-357. DOI:10.4236/jmmce.2013.16054.
- 10) MR Sanjay, B Yogesha. Studies on mechanical properties of jute/e-glass fiber reinforced epoxy hybrid composites, Journal of Minerals and Materials Characterization and Engineering, 2016, Volume 4, Pages 15-25. DOI:10.4236/jmmce.2016.41002.
- 11) Satnam Singh, Pradeep Kumar, SK Jain. An experimental and numerical investigation of mechanical properties of glass fiber reinforced epoxy composites, Advanced Materials Letters, 2013, Volume 4, Issue 7, Pages 567-572. DOI:10.5185/amlett.2012.11475.
- 12) David A Jesson, John F Watts. The interface and interphase in polymer matrix composites: effect on mechanical properties and methods for identification, Polymer Reviews, 2012, Volume 52, Issue 3-4, Pages 321-354. DOI:10.1080/15583724.2012.710288.
- 13) Shahida Begum, Sabrina Fawzia, MSJ Hashmi. Polymer matrix composite with natural and synthetic fibers, Advances in Materials and Processing Technologies, 2020, Volume 6, Issue 3, Pages 547-564. DOI:10.1080/2374068X.2020.1728645.
- 14) Naked Saba, Mohameed Jawaaid, Othman Y Alothman, MT Paridah, Azman Hassan. Recent advances in epoxy resin, natural fiber-reinforced epoxy composites and their applications, Journal of Reinforced Plastics and Composites, 2015, Volume 35, Issue 6, Pages 447-470. DOI:10.1177/0731684415618459
- 15) RS Rana, Archana Nigrawal, Saraswati Rana, Rajesh Purohit. Design and development of epoxy hybrid composite gears for low-powered applications, Advances in Materials and Processing Technologies, 2020, Volume 6, Issue 2, Pages 328-337. DOI:10.1080/2374068X.2020.1731154.
- 16) Zineb Benzait, Levent Trabzon. A review of recent research on materials used in polymer-matrix composites for body armor application, Journal of Composite Materials, 2018, Volume 52, Issue 23, Pages 3241-3263. DOI:10.1177/0021998318764002.
- 17) S. S. Godara, Abhishek Yadav, Bharat Goswami, RS Rana. Review on history and characterisation of polymer composite materials, Materials Today: Proceedings, 2021, Volume 44, Part 1, Pages 2674-2677. DOI:10.1016/j.matpr.2020.12.680.
- 18) B Suresha, BN Ravi Kumar, M Venkataramareddy, T Jayaraju. Role of micrp/nano fillers on mechanical and tribological properties of polyamide66/polypropylene composites, Materials and Design, 2010, Volume 31, Issue 4, Pages 1993-2000. DOI: 10.1016/j.matdes.2009.10.031.
- 19) MD Kiran, K Govindraju, T Jaysraju, Nithin Kumar. Review-effect of fillers on mechanical properties of polymer matrix composites, Materials Today: Proceedings, 2018, Volume 5, Issue 10, Part 3, Pages 22421-22424. DOI:10.1016/j.matpr.2018.06.611.
- 20) Mahavir Choudhary, Tej Singh, Maheshwar Dwivedi, Amar Patnaik. Waste marble dust-filled glass fiber-reinforced polymer composite Part-1: physical, thermomechanical and erosive wear properties, Polymer Composites, 2019, Volume 40, Issue 10, Pages 4113-4124. DOI:10.1002/pc.25272.
- 21) Mahavir Choudhary, Tej Singh, Ankush Sharma, Maheshwar Dwivedi, Amar Patnaik. Evaluation of some mechanical characterisation and optimisation of waste marble dust filled glass fiber reinforced polymer composite, Materials Research Express,

- 2019, Volume 6, Number 10, DOI:10.1088/2053-1591/ab3675.
- 22) Amar Patnaik, Alok Satapathy, SandhyaRani Biswas. Investigations on three-body abrasive wear and mechanical properties of particulate filled glass epoxy composites, *Malaysian Polymer Journal*, 2010, Volume 5, Number 2, Pages 37-48. DOI:bit.ly/3oZ6IaN.
- 23) S Vigneshwaran, M Uthayakumar, V Arumugaprabu, R Johnson. Influence of filler on erosion behaviour of polymer composites: a comprehensive review, *Journal of Reinforced Plastics and Composites*, 2018, Volume 37, Issue 15, Pages 1011-1019. DOI: 10.1177/073168441877711.
- 24) G Seshanandan, D Ravindran, T Sornakumar. Mechanical properties of nano titanium oxide particles- hybrid jute-glass FRP composites, *Materials Today: Proceedings*, Volume 3, Issue 6, Pages 1383-1388. DOI:10.1016/j.matpr.2016.04.019.
- 25) Ascender Ozsoy, Askin Demirkol, Abdullah Mimaroglu, Huseyin Unal, Zafer Demir. The influence of micro and nano-filler content on the mechanical properties of epoxy composites, 2015, Volume 61, Issue 10, Pages 601-609. DOI:10.5545/sv-jme.2015.2632.
- 26) S. S. Godara, Abhishek Yadav, Ved Pratap Singh, Characterisation of glass fiber reinforced composite materials with use of Kota stone dust, *Materials Today: Proceedings*, 2021, Volume 44, Part 1. DOI:10.1016/j.matpr.2020.12.634.
- 27) Virendra Rajput, Sunil Kumar Somani, Alok Agarwal, Vikas Pagey. Mechanical properties of epoxy composites filled with micro sized Kota stone dust, *Materials Today: Proceedings*, 2021, ISSN 2214-7853. DOI:10.1016/j.matpr.2021.02.701.
- 28) S Srinivasa Moorthy, K Manonmani. Fabrication and characterisation of TiO₂ particulate filled glass fiber reinforced polymer composite, *Materials Physics and Mechanics*, 2013, Volume 18, Pages 28-34. DOI:bit.ly/3fVw7Vq.
- 29) Vijay Chaudhary, Akash Kumar Rajput, Parmendra Bajpai. Effect of particulate filler on mechanical properties of polyester based composites, *Materials Today: Proceedings*, 2017, Volume 4, Issue 9, Pages 9893-9897. DOI:10.1016/j.matpr.2017.06.289.
- 30) K Srinivas, MS Bhagyashekar. Wear behaviour of epoxy hybrid particulate composites, *Procedia Engineering*, 2014, 97, Pages 488-494. DOI:10.1016/j.proeng.2014.12.273.
- 31) Nurkan Calis Acikbas, Gokhan Acikbas. Epoxy matrix composites containing urea formaldehyde waste particulate filler, *Waste Biomass Valor* 8, 2017, Pages 669-678. DOI:10.1007/s12649-016-9651-9.
- 32) MR Sanjay, B Yogesha. Studies on natural/glass fiber reinforced polymer hybrid composites: an evolution, *Materials Today: Proceedings*, 2017, Volume 4, Issue 2, Part A, Pages 2739-2747. DOI:10.1016/j.matpr.2017.02.151.
- 33) S. S. Godara, P. K. Mahato. Potential applications of hybrid nano composites, *Materials Today: Proceedings*, 2019, Volume 18, Part 7, Pages 5327-5331. DOI:10.1016/j.matpr. 2019.07.557.
- 34) S. S. Godara, P. K. Mahato. Micro mechanical technique based prediction of effective properties for hybrid smart nano composites, *Mechanics of Advanced Materials and Structures*, 2020. DOI: 10.1080/15376494.2020.1851827.
- 35) K Devendra, T Rangaswamy. Evaluation of thermal properties of e-glass epoxy composites filled by different filler materials, *International Journal of Computational Engineering Research*, 2012, Volume 2, Issue 5, Pages 1708-1714. DOI:bit.ly/3oZiHVP.
- 36) M Awang, WR Wan Mohd. Comparative studies of titanium dioxide and zinc oxide as a potential filler in polypropylene reinforced husk composite, *IOP Conference Series: Materials Science and Engineering*, 2018, Volume 342. DOI: 10.1088/1757-899X/342/1/012046.
- 37) K Balasubramanian, Mohamed TH Sultan, N Rajeshwari. Manufacturing techniques of composites for aerospace applications, *Sustainable Composites for Aerospace Applications*, 2018, Pages 55-67. DOI:10.1016/B978-0-08-102131-6.00004-9.
- 38) CN Aiza Jaffar, I Zainol, MA muhammad Rizal. Preparation and characterisation of epoxy/silica/kenaf composite using hand lay-up method, *Conference of the Microscopy Society*, 2018, Volume 27. DOI:bit.ly/2TtAPeH.
- 39) S. S. Godara, Mukesh. A review of mechanical properties of jute-glass and luffa-glass fiber reinforced epoxy hybrid composites, *International Journal of Theoretical and Applied Mechanics*, 2018, Volume 3, Pages 36-41. DOI:bit.ly/3wLIJyv.
- 40) Raghvendra Subramanya, DN Subba Reddy, Prabhakara Shimoga. Tensile, impact and fracture toughness properties of banana fiber reinforced polymer composited, *Advances in Materials and Processing Technologies*, 2020, Volume 6, Issue 4, Pages 661-668. DOI:10.1080/2374068X.2020.1734350.
- 41) Mukesh, S. S. Godara. Comparative study of mechanical properties of natural fibers, *Advances in Mechanical Processing and Design*, 2020, Pages 441-448. DOI:10.1007/978-981-15-7779-6